WEAR
CONTAMINATION
FLUID CONDITION


NORMAL NORMAL NORMAL



## LIEBHERR R914 056971-1511

Left Final Drive

PETRO CANADA TRAXON SY	NTHETIC 75	W90	( GAL	)			
RECOMMENDATION	Test	UOM	Method	Limit/Abn	Current	History1	History2
Confirm the source of the lubricant being utilized for top-up/fill. Resample at the next service interval to monitor.	Sample Number		Client Info		LH0284029		
	Sample Date		Client Info		14 Feb 2024		
	Machine Age	hrs	Client Info		480		
	Oil Age	hrs	Client Info		0		
	Filter Age	hrs	Client Info		0		
	Oil Changed		Client Info		Changed		
	Filter Changed		Client Info		N/A		
	Sample Status				NORMAL		
WEAR	Iron	ppm	ASTM D5185(m)	>500	121		
All component wear rates are normal.	Chromium	ppm	ASTM D5185(m)		2		
	Nickel	ppm	ASTM D5185(m)		<1		
	Titanium	ppm	ASTM D5185(m)	710	0		
	Silver	ppm	ASTM D5185(m)		0		
	Aluminum	ppm	` '	>25	7		
	Lead	ppm	ASTM D5185(m)	>25	<1		
	Copper	ppm	` '	>50	<1		
	Tin	ppm	ASTM D5185(m)	>10	0		
	Vanadium	ppm	ASTM D5185(m)		0		
	White Metal	scalar	Visual*	NONE	NONE		
	Yellow Metal	scalar	Visual*	NONE	NONE		
CONTANUNATION							
CONTAMINATION	Silicon	ppm	ASTM D5185(m)	>75	22		
There is no indication of any contamination in the oil.	Potassium	ppm	\ /	>20	4		
	Water		WC Method	>0.2	NEG		
	Silt	scalar	Visual*	NONE	NONE		
	Debris	scalar	Visual*	NONE	VLITE		
	Sand/Dirt	scalar	Visual*	NONE	NONE		
	Appearance	scalar	Visual*	NORML	NORML		
	Odor Emulsified Water	scalar	Visual* Visual*	NORML >0.2	NORML NEG		
	Linuisilled Water	scalar	····				
FLUID CONDITION	Sodium	ppm	ASTM D5185(m)		8		
Additive levels indicate the addition of a different brand, or type of oil. The condition of the oil is acceptable for the time in service.	Boron	ppm	ASTM D5185(m)	328	5		
	Barium	ppm	ASTM D5185(m)	1	17		
	Molybdenum	ppm	ASTM D5185(m)		0		
	Manganese	ppm	ASTM D5185(m)		1		
	Magnesium	ppm	ASTM D5185(m)		2		
	Calcium	ppm	ASTM D5185(m)		33		
	Phosphorus	ppm	\ /	1145	1185		
	Zinc	ppm	ASTM D5185(m)		37		
	Sulfur	ppm		17909	24355		
	Visc @ 40°C	cSt	ASTM D7279(m)	99.6	197		

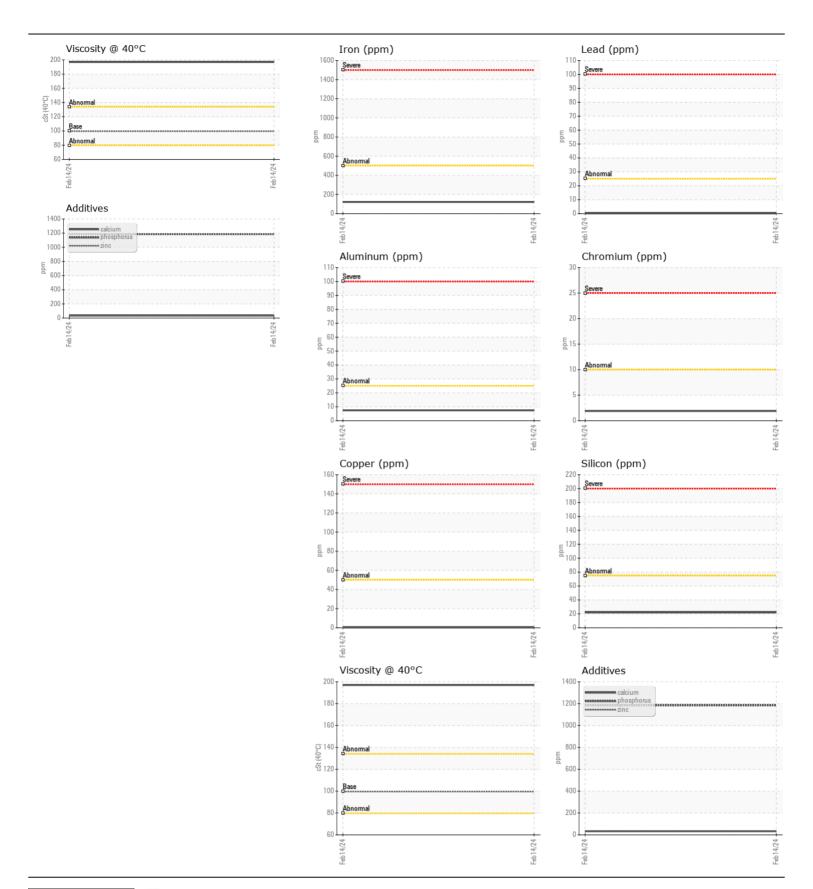



CALA ISO 17025:2017 Accredited Laboratory

Laboratory Sample No.

Lab Number : 02616415 Unique Number : 5733525 Test Package : MOB 1

: WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 : LH0284029

Received **Tested** 

: 16 Feb 2024 : 16 Feb 2024 Diagnosed

: 16 Feb 2024 - Wes Davis

To discuss this sample report, contact Customer Service at 1-800-268-2131. Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.

Validity of results and interpretation are based on the sample and information as supplied.

**WEKA HOLDINGS LTD** 2754 WOODLAND DRIVE VANCOUVER, BC **CA V5N 3P8** 

Contact: Cam Turtle

T: F: