



# LIEBHERR

## OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area  
**(348279)**  
Machine Id  
**LIEBHERR LH50M 129938-1216**  
Component  
**Splitter Box**  
Fluid  
**LIEBHERR GEAR BASIC 90 LS (--- GAL)**

### RECOMMENDATION

Confirm the source of the lubricant being utilized for top-up/fill.  
Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LH0284371	LH	---
Sample Date		Client Info		15 Feb 2024	18 Jun 2023	---
Machine Age	hrs	Client Info		3030	2442	---
Oil Age	hrs	Client Info		0	0	---
Filter Age	hrs	Client Info		0	0	---
Oil Changed		Client Info		Changed	Changed	---
Filter Changed		Client Info		N/A	N/A	---
Sample Status				NORMAL	NORMAL	---

### WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185(m)	>80	13	8	---
Chromium	ppm	ASTM D5185(m)	>2	0	0	---
Nickel	ppm	ASTM D5185(m)	>2	<1	0	---
Titanium	ppm	ASTM D5185(m)		0	0	---
Silver	ppm	ASTM D5185(m)		0	0	---
Aluminum	ppm	ASTM D5185(m)	>5	2	<1	---
Lead	ppm	ASTM D5185(m)	>2	0	0	---
Copper	ppm	ASTM D5185(m)	>10	1	<1	---
Tin	ppm	ASTM D5185(m)	>2	0	0	---
Vanadium	ppm	ASTM D5185(m)		0	0	---
White Metal	scalar	Visual*	NONE	NONE	NONE	---
Yellow Metal	scalar	Visual*	NONE	NONE	NONE	---

### CONTAMINATION











There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185(m)	>10	2	<1	---
Potassium	ppm	ASTM D5185(m)	>20	2	2	---
Water		WC Method	>0.1	NEG	NEG	---
Silt	scalar	Visual*	NONE	NONE	NONE	---
Debris	scalar	Visual*	NONE	NONE	NONE	---
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE	---
Appearance	scalar	Visual*	NORML	NORML	NORML	---
Odor	scalar	Visual*	NORML	NORML	NORML	---
Emulsified Water	scalar	Visual*	>0.1	NEG	NEG	---

### FLUID CONDITION

Additive levels indicate the addition of a different brand, or type of oil.  
The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185(m)	>25	<1	1	---
Boron	ppm	ASTM D5185(m)	0	1	4	---
Barium	ppm	ASTM D5185(m)	0	0	0	---
Molybdenum	ppm	ASTM D5185(m)	0	<1	0	---
Manganese	ppm	ASTM D5185(m)	0	<1	1	---
Magnesium	ppm	ASTM D5185(m)	<1	22	1	---
Calcium	ppm	ASTM D5185(m)	<1	32	6	---
Phosphorus	ppm	ASTM D5185(m)	2143	2169	2348	---
Zinc	ppm	ASTM D5185(m)	<1	44	15	---
Sulfur	ppm	ASTM D5185(m)	23468	24638	29476	---
Visc @ 40°C	cSt	ASTM D7279(m)	170	182	179	---

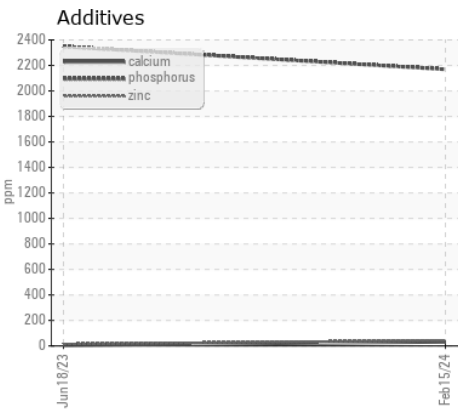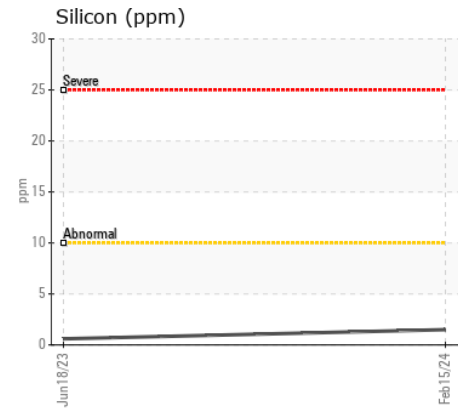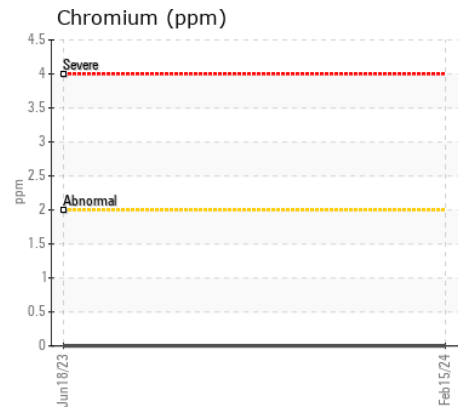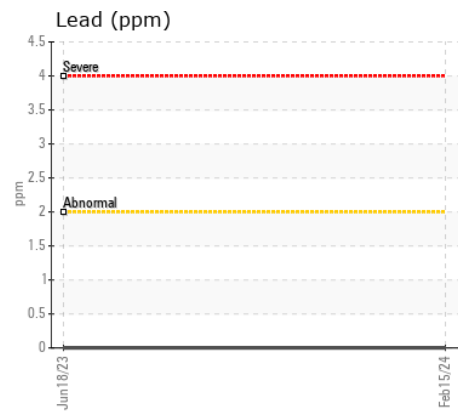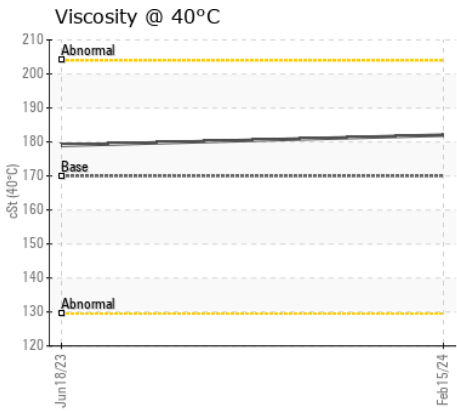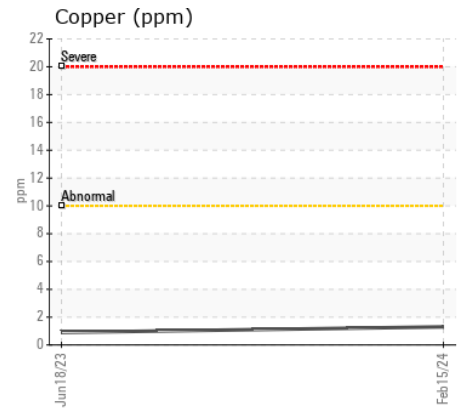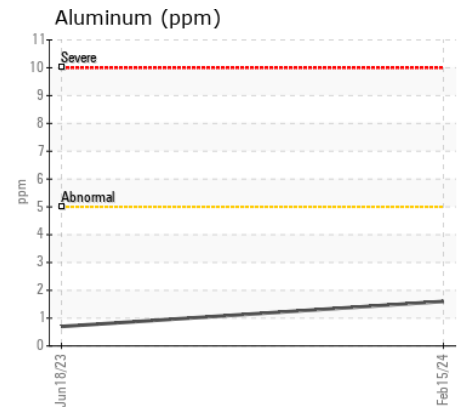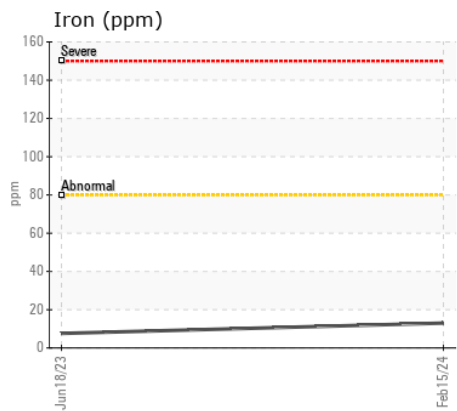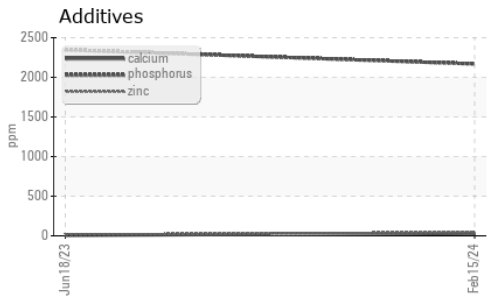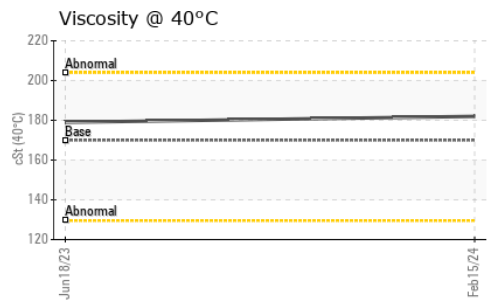

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : LH0284371  
**Lab Number** : 02616742  
**Unique Number** : 5733852  
**Test Package** : MOB 1  
**Received** : 20 Feb 2024  
**Tested** : 20 Feb 2024  
**Diagnosed** : 20 Feb 2024 - Wes Davis

**METAUX 139 INC.**  
 86 RTE MARIE-VICTORIN  
 PIERREVILLE, QC  
 CA J0G 1J0  
 Contact: Service Manager

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.

T:  
F: