

Machine Id
811030
Component
Transmission (Auto)
Fluid
DEXRON III (--- GAL)

RECOMMENDATION

Nous vous recommandons de vidanger le fluide de ce composant si vous ne l'avez pas déjà fait. Nous vous recommandons d'échantillonner de nouveau dès que possible afin de contrôler la situation. Le fluide n'était pas spécifié, toutefois, une comparaison avec d'autres fluides indiquent que ce fluide est du (GENERIC) DEXRON III. Veuillez confirmer.

WEAR

Usure de disque d'embrayage.











CONTAMINATION

Il n'y a aucun indice de contamination dans le fluide.

FLUID CONDITION

Le fluide n'est plus en état de service en raison d'une usure anormale et/ou sévère.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		GFL0096615	GFL0080348	GFL0044367
Sample Date		Client Info		11 Dec 2023	20 Sep 2023	20 Mar 2023
Machine Age	kms	Client Info		119893	104081	69506
Oil Age	kms	Client Info		0	0	0
Filter Age	kms	Client Info		0	0	0
Oil Changed		Client Info		Not Changed	Not Changed	Not Changed
Filter Changed		Client Info		Not Changed	Not Changed	Not Changed
Sample Status				ABNORMAL	NORMAL	ABNORMAL
Iron	ppm	ASTM D5185(m)	>160	140	78	91
Chromium	ppm	ASTM D5185(m)	>5	<1	<1	<1
Nickel	ppm	ASTM D5185(m)	>5	<1	0	<1
Titanium	ppm	ASTM D5185(m)		0	0	0
Silver	ppm	ASTM D5185(m)	>5	0	<1	0
Aluminum	ppm	ASTM D5185(m)	>50	44	49	▲ 58
Lead	ppm	ASTM D5185(m)	>50	▲ 98	6	11
Copper	ppm	ASTM D5185(m)	>225	91	13	13
Tin	ppm	ASTM D5185(m)	>10	7	3	4
Vanadium	ppm	ASTM D5185(m)		0	0	0
White Metal	scalar	Visual*	NONE	VLITE	NONE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE	NONE
Silicon	ppm	ASTM D5185(m)	>20	7	13	8
Potassium	ppm	ASTM D5185(m)	>20	5	3	5
Water		WC Method	>0.1	NEG	NEG	NEG
Silt	scalar	Visual*	NONE	NONE	VLITE	NONE
Debris	scalar	Visual*	NONE	NONE	VLITE	VLITE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.1	NEG	NEG	NEG
Sodium	ppm	ASTM D5185(m)		11	8	10
Boron	ppm	ASTM D5185(m)		139	63	77
Barium	ppm	ASTM D5185(m)		<1	<1	0
Molybdenum	ppm	ASTM D5185(m)		<1	0	<1
Manganese	ppm	ASTM D5185(m)		2	<1	2
Magnesium	ppm	ASTM D5185(m)		1	3	<1
Calcium	ppm	ASTM D5185(m)		97	107	66
Phosphorus	ppm	ASTM D5185(m)		380	227	270
Zinc	ppm	ASTM D5185(m)		9	10	8
Sulfur	ppm	ASTM D5185(m)		1687	1198	881
Visc @ 40°C	cSt	ASTM D7279(m)	26.0	34.3	33.5	34.7

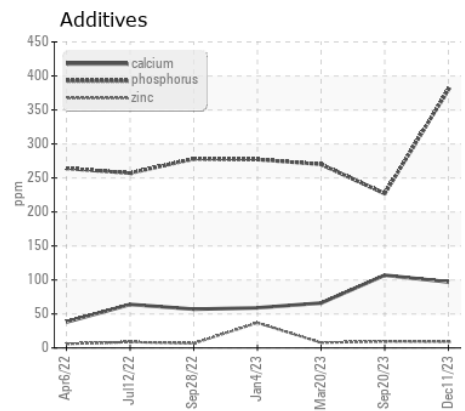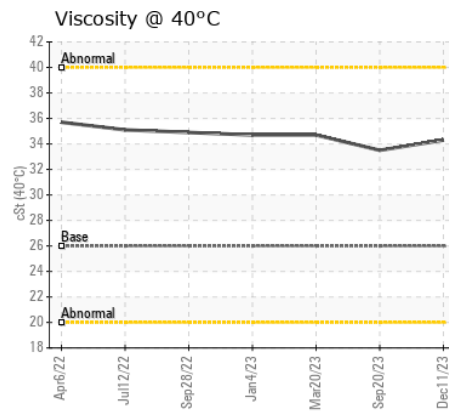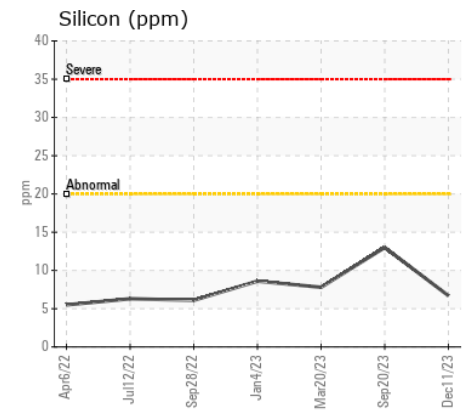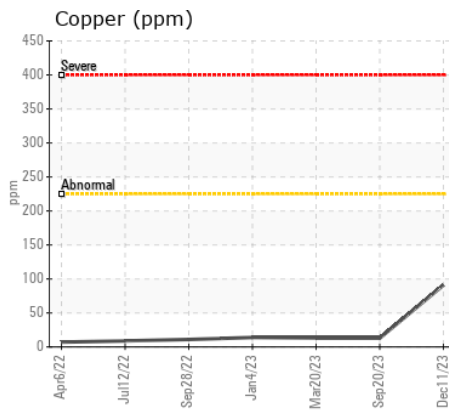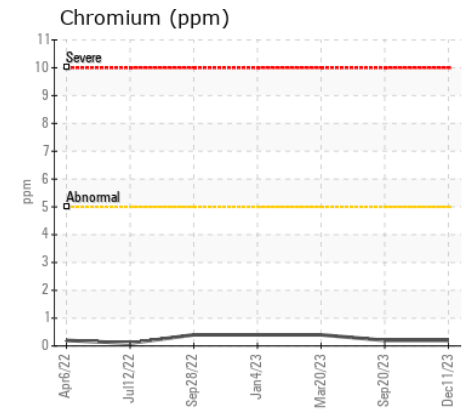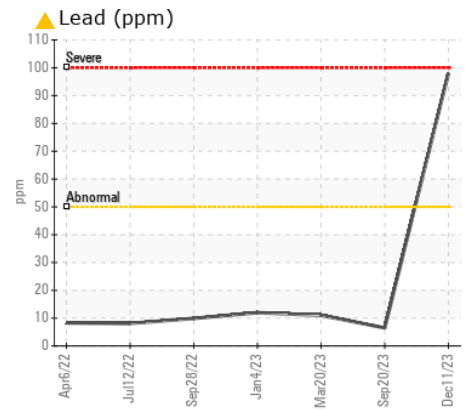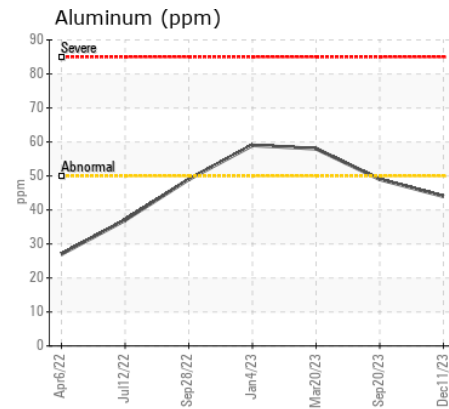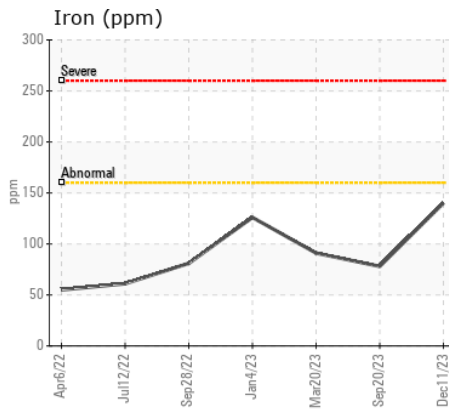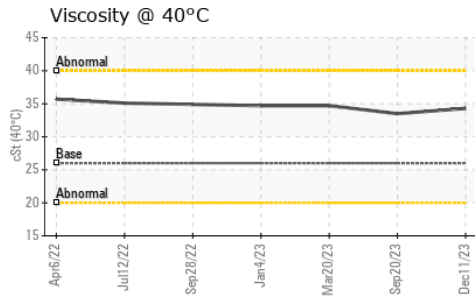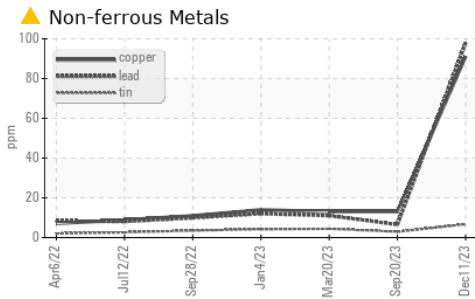

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : GFL0096615
Lab Number : 02617169
Unique Number : 5734279
Test Package : MOB 1

Received : 21 Feb 2024
Tested : 22 Feb 2024
Diagnosed : 23 Feb 2024 - Kevin Marson

GFL Environmental - 730 - Chicoutimi - Hauling
 3199 Boul. Talbot
 Chicoutimi, QC
 CA G7H 5B1
 Contact: Yan Houde
 yhoude@matrec.ca
 T: (418)549-8074
 F: (418)549-7973

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.