



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
7763
 Component
Diesel Engine
 Fluid
PETRO CANADA DURON SHP 15W40 (40 LTR)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		GFL0113171	GFL0101085	GFL0097019
Sample Date		Client Info		01 Mar 2024	14 Dec 2023	26 Sep 2023
Machine Age	kms	Client Info		30832	276848	271890
Oil Age	kms	Client Info		276848	0	0
Filter Age	kms	Client Info		276848	0	0
Oil Changed		Client Info		N/A	Changed	Changed
Filter Changed		Client Info		N/A	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185(m)	>165	14	13	18
Chromium	ppm	ASTM D5185(m)	>5	<1	<1	<1
Nickel	ppm	ASTM D5185(m)	>4	0	0	0
Titanium	ppm	ASTM D5185(m)	>2	0	0	0
Silver	ppm	ASTM D5185(m)	>2	0	<1	<1
Aluminum	ppm	ASTM D5185(m)	>20	2	2	2
Lead	ppm	ASTM D5185(m)	>150	<1	1	2
Copper	ppm	ASTM D5185(m)	>90	2	3	10
Tin	ppm	ASTM D5185(m)	>5	0	0	0
Vanadium	ppm	ASTM D5185(m)		0	0	0

CONTAMINATION










There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185(m)	>35	4	4	4
Potassium	ppm	ASTM D5185(m)	>20	1	0	2
Fuel		WC Method	>3.0	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	ASTM D7844*	>7.5	0.7	0.8	1.1
Nitration	Abs/cm	ASTM D7624*	>20	7.9	8.1	10.2
Sulfation	Abs/.1mm	ASTM D7415*	>30	20.2	20.7	22.5
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG	NEG

FLUID CONDITION

The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185(m)		5	7	9
Boron	ppm	ASTM D5185(m)	0	5	2	2
Barium	ppm	ASTM D5185(m)	0	0	<1	<1
Molybdenum	ppm	ASTM D5185(m)	60	61	62	64
Manganese	ppm	ASTM D5185(m)	0	0	0	0
Magnesium	ppm	ASTM D5185(m)	1010	971	987	1010
Calcium	ppm	ASTM D5185(m)	1070	1099	1109	1094
Phosphorus	ppm	ASTM D5185(m)	1150	1022	997	1017
Zinc	ppm	ASTM D5185(m)	1270	1197	1219	1251
Sulfur	ppm	ASTM D5185(m)	2060	2712	2469	2421
Oxidation	Abs/.1mm	ASTM D7414*	>25	14.7	15.2	17.0
Visc @ 100°C	cSt	ASTM D7279(m)	15.4	13.6	14.0	14.1

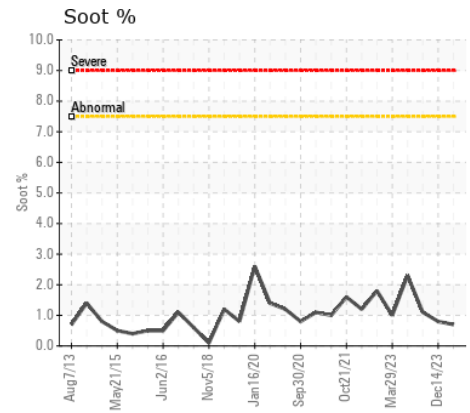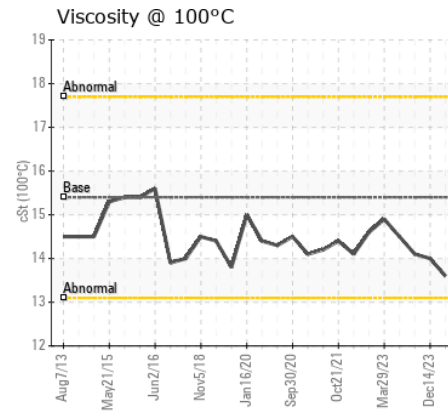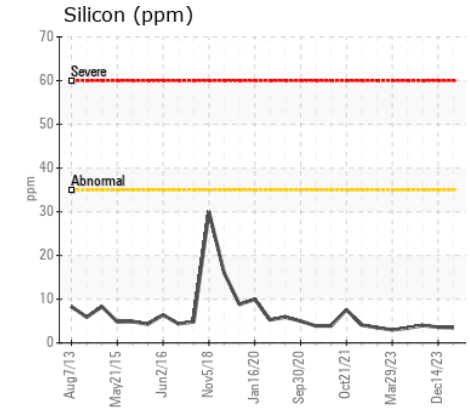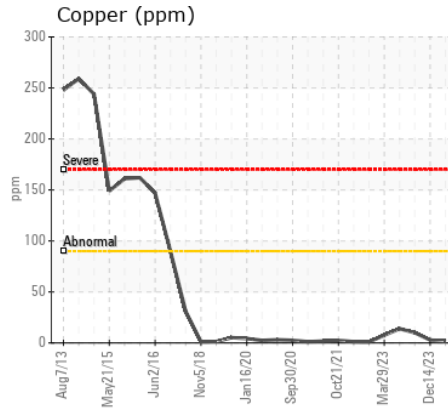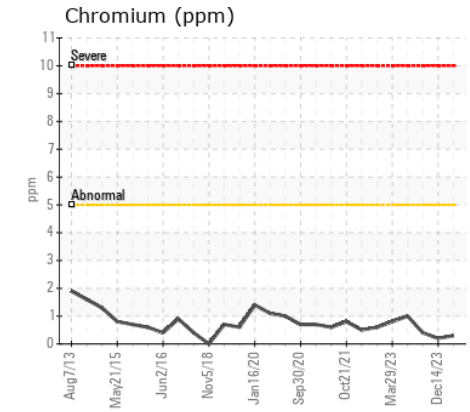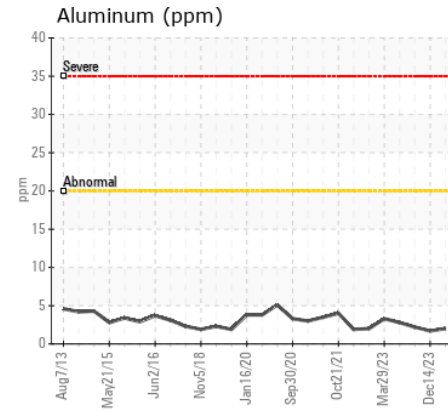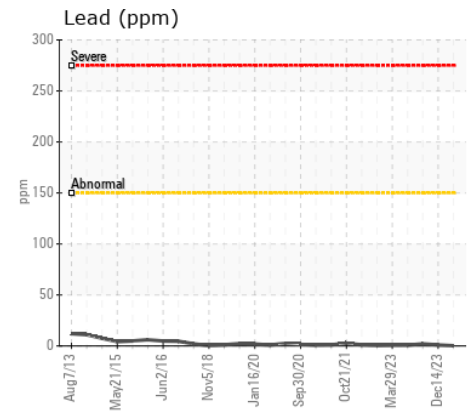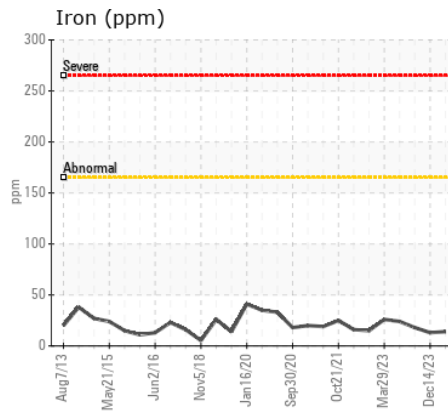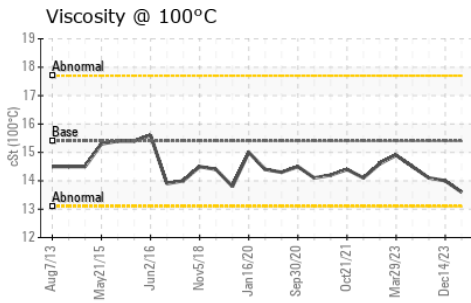

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : GFL0113171
Lab Number : 02620399
Unique Number : 5737509
Test Package : MOB 1

GFL Environmental - 225 - COT(D2)
 20 Brydon Drive
 Etobicoke, ON
 CA M9W 5R6
 Contact: Rick Philip
 rphilip@gflenv.com
 T: (416)745-8080
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.