



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
CASE TV37013 B12
 Component
Diesel Engine
 Fluid
{not provided} (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0910045	---	---
Sample Date		Client Info		08 May 2024	---	---
Machine Age	hrs	Client Info		1952	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Not Changed	---	---
Filter Changed		Client Info		Not Changed	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185(m)	>100	62	---	---
Chromium	ppm	ASTM D5185(m)	>20	2	---	---
Nickel	ppm	ASTM D5185(m)	>4	0	---	---
Titanium	ppm	ASTM D5185(m)		<1	---	---
Silver	ppm	ASTM D5185(m)	>3	0	---	---
Aluminum	ppm	ASTM D5185(m)	>20	6	---	---
Lead	ppm	ASTM D5185(m)	>40	3	---	---
Copper	ppm	ASTM D5185(m)	>330	112	---	---
Tin	ppm	ASTM D5185(m)	>15	<1	---	---
Vanadium	ppm	ASTM D5185(m)		0	---	---

CONTAMINATION












There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185(m)	>25	10	---	---
Potassium	ppm	ASTM D5185(m)	>20	<1	---	---
Fuel		WC Method	>5	<1.0	---	---
Water		WC Method	>0.2	NEG	---	---
Glycol		WC Method		NEG	---	---
Soot %	%	ASTM D7844*	>3	0.3	---	---
Nitration	Abs/cm	ASTM D7624*	>20	11.5	---	---
Sulfation	Abs/.1mm	ASTM D7415*	>30	23.6	---	---
Emulsified Water	scalar	Visual*	>0.2	NEG	---	---

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185(m)		5	---	---
Boron	ppm	ASTM D5185(m)		2	---	---
Barium	ppm	ASTM D5185(m)		0	---	---
Molybdenum	ppm	ASTM D5185(m)		309	---	---
Manganese	ppm	ASTM D5185(m)		1	---	---
Magnesium	ppm	ASTM D5185(m)		1005	---	---
Calcium	ppm	ASTM D5185(m)		1184	---	---
Phosphorus	ppm	ASTM D5185(m)		1076	---	---
Zinc	ppm	ASTM D5185(m)		1295	---	---
Sulfur	ppm	ASTM D5185(m)		2343	---	---
Oxidation	Abs/.1mm	ASTM D7414*	>25	19.4	---	---
Base Number (BN)	mg KOH/g	ASTM D2896*		8.70	---	---
Visc @ 100°C	cSt	ASTM D7279(m)		13.1	---	---

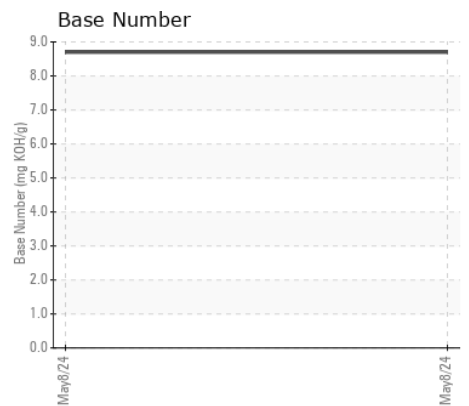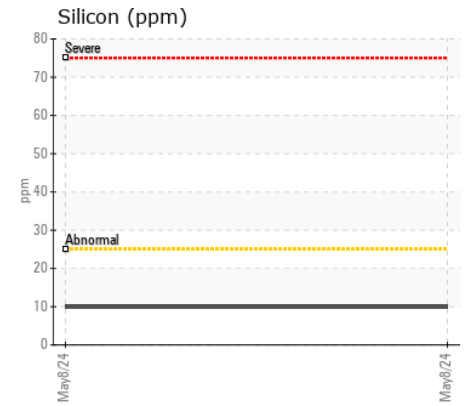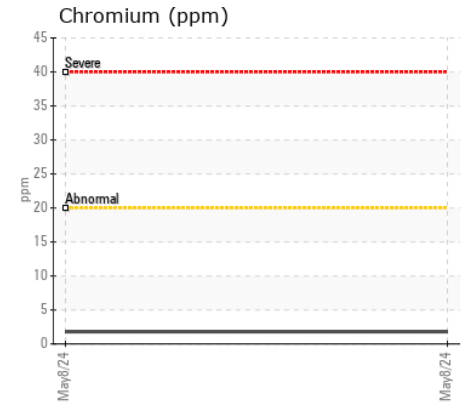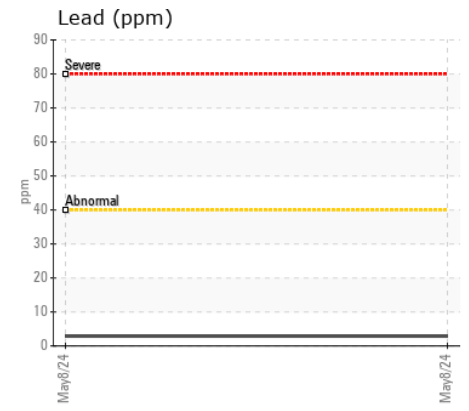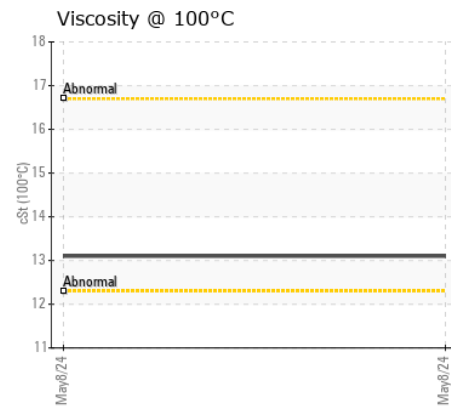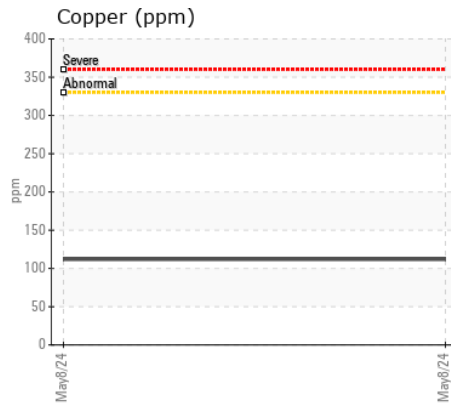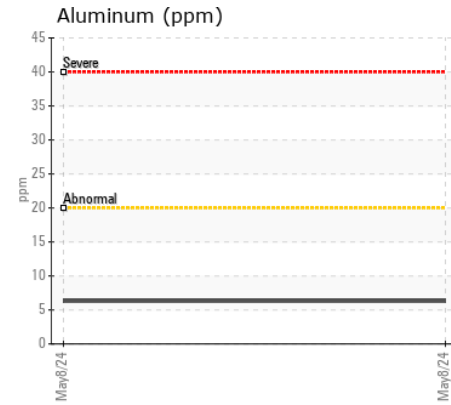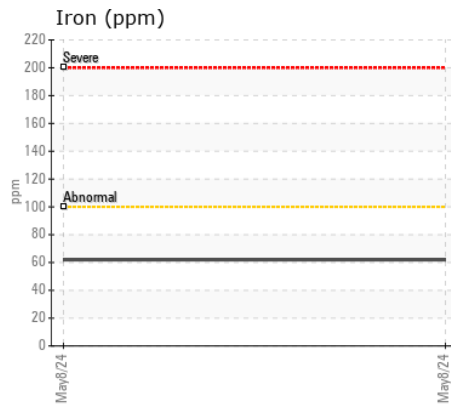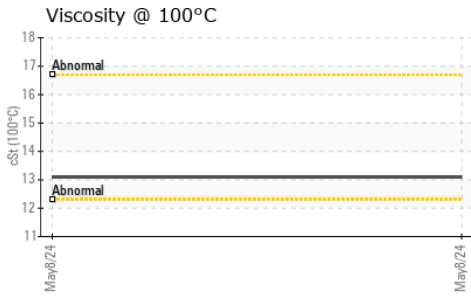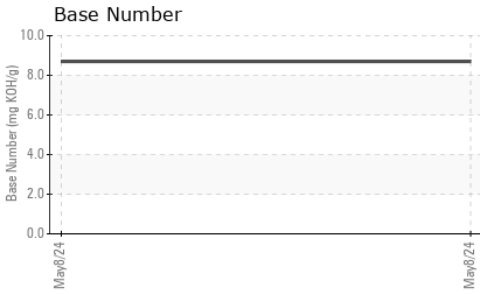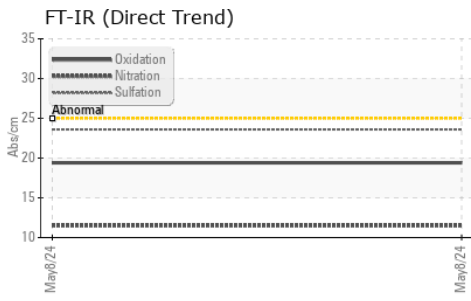

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0910045 **Received** : 16 May 2024
Lab Number : 02636002 **Tested** : 17 May 2024
Unique Number : 5785164 **Diagnosed** : 17 May 2024 - Wes Davis
Test Package : MOB 2

STRONGCO EQUIPMENT
 1075 CLARK BOULEVARD
 BRAMPTON, ON
 CA L6T 3W4
 Contact: Demitri Rjevskii
 drjevskii@strongco.com
 T: (647)218-3575
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.