



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
2102
Component
Diesel Engine
Fluid
DIESEL ENGINE OIL SAE 15W40 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0932492	WC0925672	WC0905443
Sample Date		Client Info		16 May 2024	12 Apr 2024	06 Mar 2024
Machine Age	hrs	Client Info		14364	13839	13321
Oil Age	hrs	Client Info		530	513	380
Filter Age	hrs	Client Info		530	513	380
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		N/A	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185(m)	>100	12	10	8
Chromium	ppm	ASTM D5185(m)	>20	<1	<1	0
Nickel	ppm	ASTM D5185(m)	>4	0	0	0
Titanium	ppm	ASTM D5185(m)		0	0	0
Silver	ppm	ASTM D5185(m)	>3	0	0	0
Aluminum	ppm	ASTM D5185(m)	>20	1	1	<1
Lead	ppm	ASTM D5185(m)	>40	0	0	0
Copper	ppm	ASTM D5185(m)	>330	4	3	2
Tin	ppm	ASTM D5185(m)	>15	0	0	0
Vanadium	ppm	ASTM D5185(m)		0	0	0
White Metal	scalar	Visual*	NONE	NONE	---	---
Yellow Metal	scalar	Visual*	NONE	NONE	---	---

CONTAMINATION











There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185(m)	>25	3	3	2
Potassium	ppm	ASTM D5185(m)	>20	0	0	0
Fuel		WC Method	>5	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	ASTM D7844*	>3	0.4	0.4	0.3
Nitration	Abs/cm	ASTM D7624*	>20	9.3	8.7	7.9
Sulfation	Abs/.1mm	ASTM D7415*	>30	24.0	21.0	20.1
Silt	scalar	Visual*	NONE	NONE	---	---
Debris	scalar	Visual*	NONE	NONE	---	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---	---
Appearance	scalar	Visual*	NORML	NORML	---	---
Odor	scalar	Visual*	NORML	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG	NEG

FLUID CONDITION

The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185(m)	>158	1	1	<1
Boron	ppm	ASTM D5185(m)	250	2	2	0
Barium	ppm	ASTM D5185(m)	10	0	<1	0
Molybdenum	ppm	ASTM D5185(m)	100	61	60	59
Manganese	ppm	ASTM D5185(m)		0	0	0
Magnesium	ppm	ASTM D5185(m)	450	989	986	982
Calcium	ppm	ASTM D5185(m)	3000	1061	1061	1075
Phosphorus	ppm	ASTM D5185(m)	1150	1018	1015	1010
Zinc	ppm	ASTM D5185(m)	1350	1220	1215	1206
Sulfur	ppm	ASTM D5185(m)	4250	2551	2558	2597
Oxidation	Abs/.1mm	ASTM D7414*	>25	23.8	18.4	17.1
Visc @ 100°C	cSt	ASTM D7279(m)	14.4	12.7	12.9	12.8

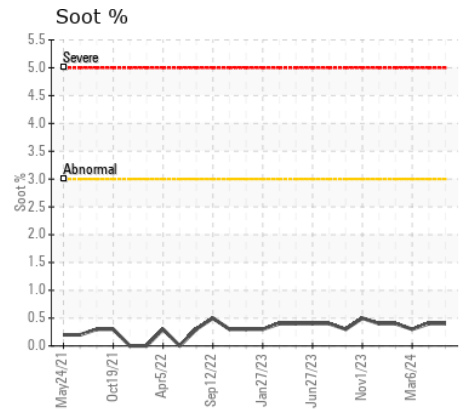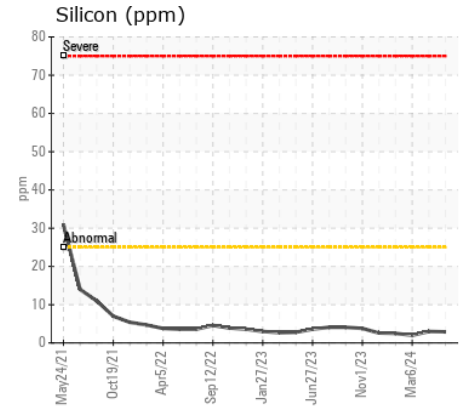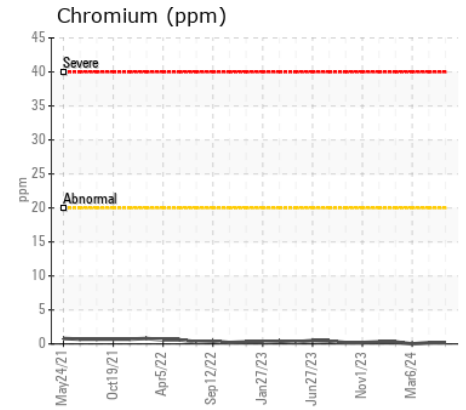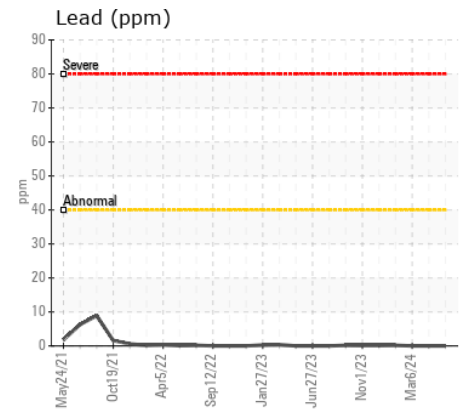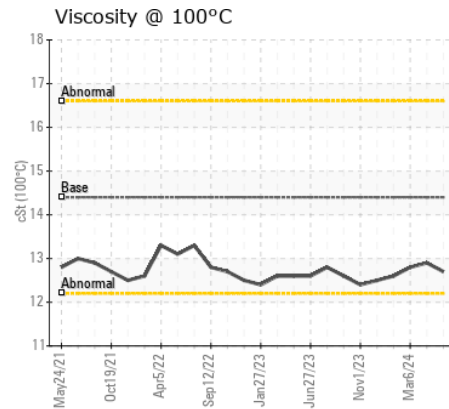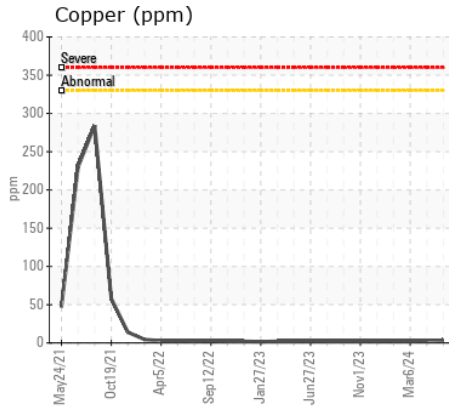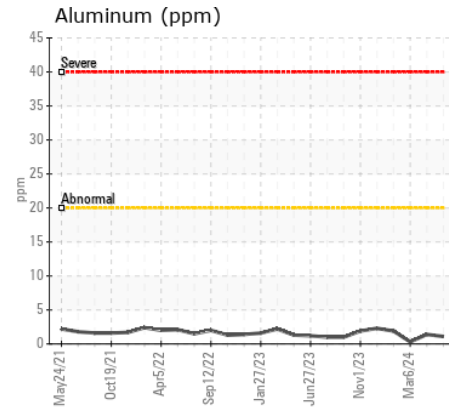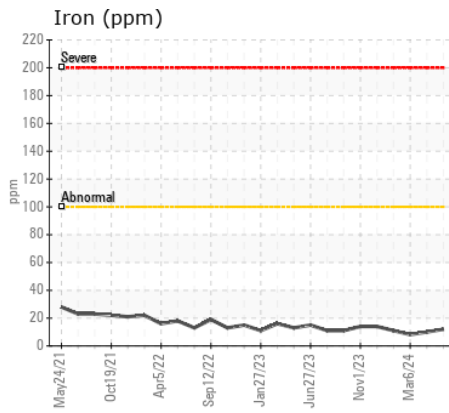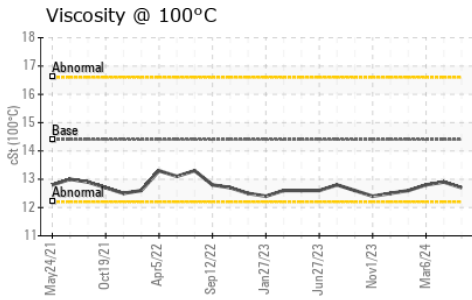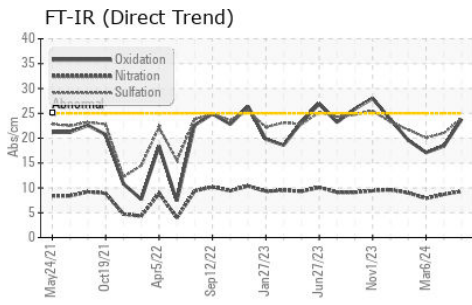

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0932492 **Received** : 27 May 2024
Lab Number : 02637645 **Tested** : 27 May 2024
Unique Number : 5786807 **Diagnosed** : 27 May 2024 - Wes Davis
Test Package : MOB 1 (Additional Tests: Visual)

KINGSTON TRANSIT
 1181 JOHN COUNTER BLVD
 KINGSTON, ON
 CA K7K 6C7
 Contact: Brent Gunter
 bgunter@cityofkingston.ca
 T: (613)546-4291
 F: (613)542-1504

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.