



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area
Scoop 6 Yard
Machine Id
LHD6102
Component
Rear Left Wheel Hub
Fluid
PETRO CANADA TRAXON 80W90 (4 LTR)

RECOMMENDATION

Confirm the source of the lubricant being utilized for top-up/fill.
Resample at the next service interval to monitor.

WEAR

All component wear rates are normal.












CONTAMINATION

There is no indication of any contamination in the oil.

FLUID CONDITION

Additive levels indicate the addition of a different brand, or type of oil.
The condition of the oil is acceptable for the time in service.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		PC0084673	PC0075101	PC0066829
Sample Date		Client Info		30 Apr 2024	02 Nov 2023	11 May 2023
Machine Age	hrs	Client Info		4879	3868	2662
Oil Age	hrs	Client Info		0	0	0
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		N/A	N/A	N/A
Filter Changed		Client Info		N/A	N/A	N/A
Sample Status				NORMAL	NORMAL	NORMAL
Iron	ppm	ASTM D5185(m)	>500	174	144	39
Chromium	ppm	ASTM D5185(m)	>8	<1	<1	<1
Nickel	ppm	ASTM D5185(m)	>5	<1	<1	0
Titanium	ppm	ASTM D5185(m)		0	0	0
Silver	ppm	ASTM D5185(m)		0	<1	0
Aluminum	ppm	ASTM D5185(m)	>5	<1	<1	<1
Lead	ppm	ASTM D5185(m)	>5	0	<1	0
Copper	ppm	ASTM D5185(m)	>50	9	8	6
Tin	ppm	ASTM D5185(m)		0	0	0
Vanadium	ppm	ASTM D5185(m)		0	0	0
White Metal	scalar	Visual*	NONE	VLITE	NONE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE	NONE
Silicon	ppm	ASTM D5185(m)	>25	1	3	2
Potassium	ppm	ASTM D5185(m)	>20	<1	<1	<1
Water		WC Method	>0.2	NEG	NEG	NEG
Silt	scalar	Visual*	NONE	VLITE	NONE	VLITE
Debris	scalar	Visual*	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG	NEG
Sodium	ppm	ASTM D5185(m)		<1	2	<1
Boron	ppm	ASTM D5185(m)	243	8	6	33
Barium	ppm	ASTM D5185(m)	1	4	4	18
Molybdenum	ppm	ASTM D5185(m)		0	0	<1
Manganese	ppm	ASTM D5185(m)		2	1	<1
Magnesium	ppm	ASTM D5185(m)	2	1	<1	3
Calcium	ppm	ASTM D5185(m)	6	24	25	13
Phosphorus	ppm	ASTM D5185(m)	987	649	634	865
Zinc	ppm	ASTM D5185(m)	1	31	22	16
Sulfur	ppm	ASTM D5185(m)	21530	21602	22389	22054
Visc @ 40°C	cSt	ASTM D7279(m)	141.0	138	138	141
Visc @ 100°C	cSt	ASTM D7279(m)	15.06	14.6	14.7	14.7
Viscosity Index (VI)	Scale	ASTM D2270*	108	105	106	103

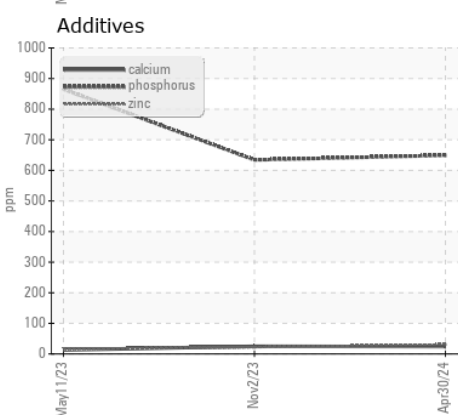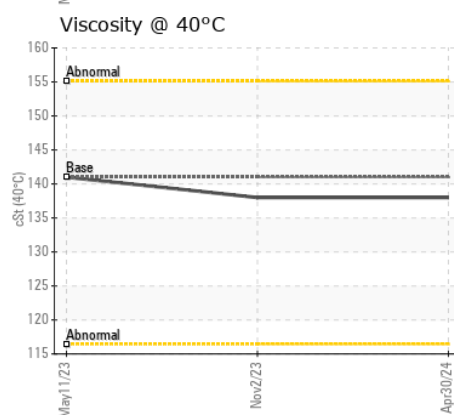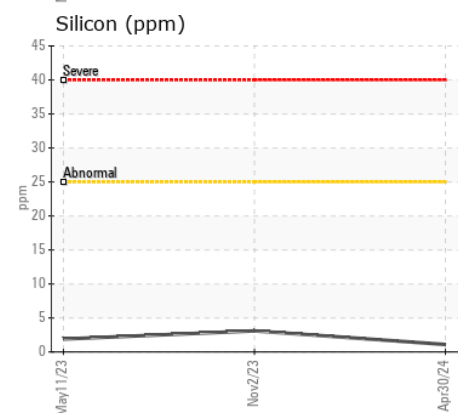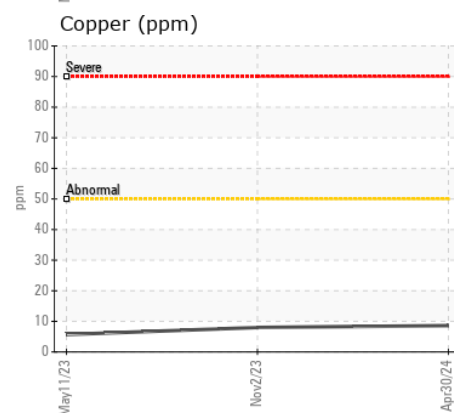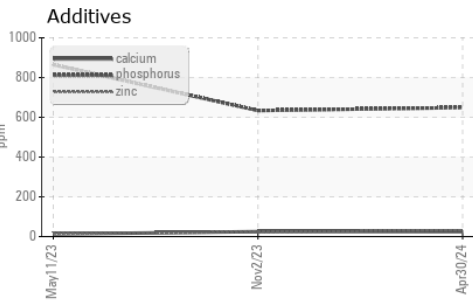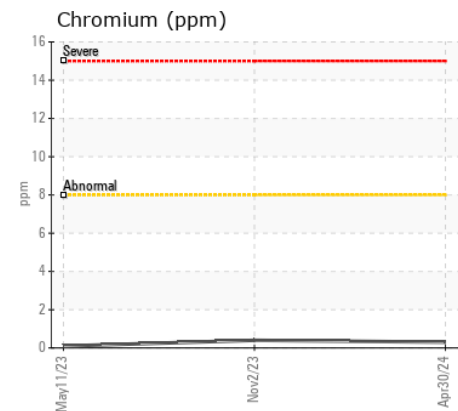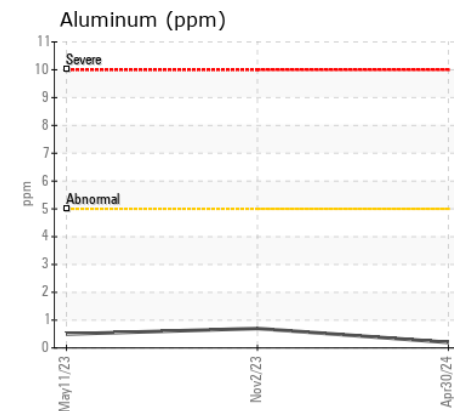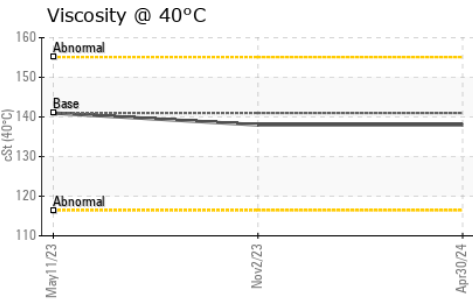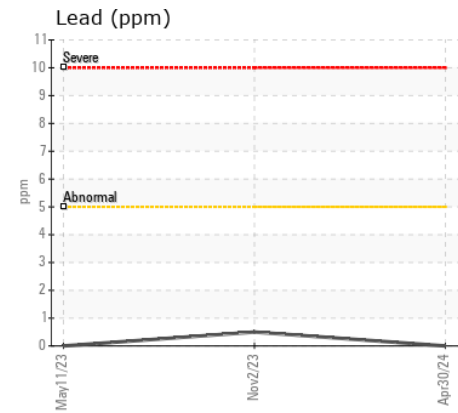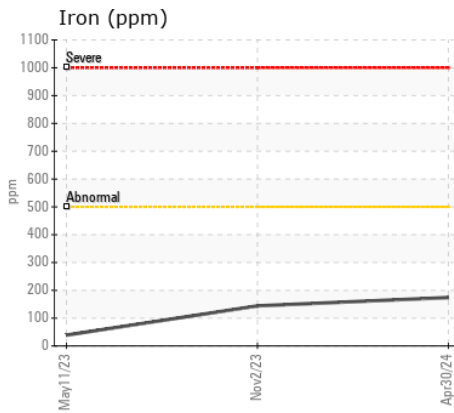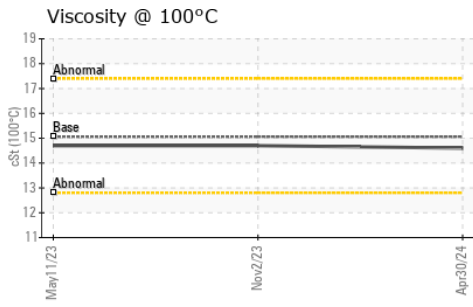

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : PC0084673 **Received** : 29 May 2024
Lab Number : 02638564 **Tested** : 29 May 2024
Unique Number : 5787726 **Diagnosed** : 29 May 2024 - Wes Davis
Test Package : MOB 1 (Additional Tests: KV100, VI)

Lakeshore Gold Timmins West

Timmins, ON
CA

Contact: Dale Arseneau
darseneau@ca.panamericansilver.com

T: (705)269-4344

F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.

Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.

Validity of results and interpretation are based on the sample and information as supplied.