



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	ABNORMAL

Machine Id
HL5913 Fwd Start Air Comp
Component
Forward Air Compressor
Fluid
SHELL CORENA S2 P 100 (6 LTR)

RECOMMENDATION

Confirm the source of the lubricant being utilized for top-up/fill.
Resample at the next service interval to monitor.

WEAR

All component wear rates are normal.











CONTAMINATION

There is no indication of any contamination in the oil.

FLUID CONDITION

Viscosity of sample indicates oil is within ISO 46 range, advise investigate. This plus the additive levels indicates that this is not the same brand, or type of oil as reported. The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0929730	WC0709126	WC
Sample Date		Client Info		30 May 2024	26 Jun 2023	25 Jun 2022
Machine Age	hrs	Client Info		4472	3900	2983
Oil Age	hrs	Client Info		0	0	983
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		Not Changd	N/A	N/A
Filter Changed		Client Info		None	N/A	N/A
Sample Status				ABNORMAL	NORMAL	NORMAL
PQ		ASTM D8184*		0	0	0
Iron	ppm	ASTM D5185(m)	>50	<1	4	14
Chromium	ppm	ASTM D5185(m)	>4	0	0	0
Nickel	ppm	ASTM D5185(m)	>4	0	0	0
Titanium	ppm	ASTM D5185(m)		0	0	0
Silver	ppm	ASTM D5185(m)		0	0	0
Aluminum	ppm	ASTM D5185(m)	>10	0	<1	<1
Lead	ppm	ASTM D5185(m)	>20	0	<1	2
Copper	ppm	ASTM D5185(m)	>40	<1	<1	<1
Tin	ppm	ASTM D5185(m)	>5	0	0	<1
Vanadium	ppm	ASTM D5185(m)		0	0	0
White Metal	scalar	Visual*	NONE	VLITE	NONE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE	NONE
Silicon	ppm	ASTM D5185(m)	>25	0	1	<1
Potassium	ppm	ASTM D5185(m)	>20	1	<1	<1
Water	%	ASTM D6304*	>0.6	0.002	0.001	0.005
ppm Water	ppm	ASTM D6304*	>6000	17	1.8	50.9
Silt	scalar	Visual*	NONE	NONE	NONE	NONE
Debris	scalar	Visual*	NONE	VLITE	NONE	NONE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.6	NEG	NEG	NEG
Sodium	ppm	ASTM D5185(m)		3	<1	<1
Boron	ppm	ASTM D5185(m)	0	0	0	0
Barium	ppm	ASTM D5185(m)	0	<1	0	0
Molybdenum	ppm	ASTM D5185(m)	0	0	0	0
Manganese	ppm	ASTM D5185(m)		0	0	<1
Magnesium	ppm	ASTM D5185(m)	0	<1	<1	<1
Calcium	ppm	ASTM D5185(m)	60	77	65	69
Phosphorus	ppm	ASTM D5185(m)	160	229	191	177
Zinc	ppm	ASTM D5185(m)	190	50	203	201
Sulfur	ppm	ASTM D5185(m)	1300	767	881	905
Acid Number (AN)	mg KOH/g	ASTM D974*	0.3	0.11	0.49	0.19
Visc @ 40°C	cSt	ASTM D7279(m)	100	50.0	113	115

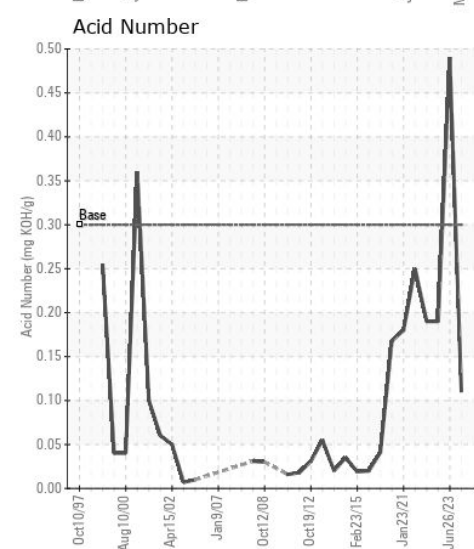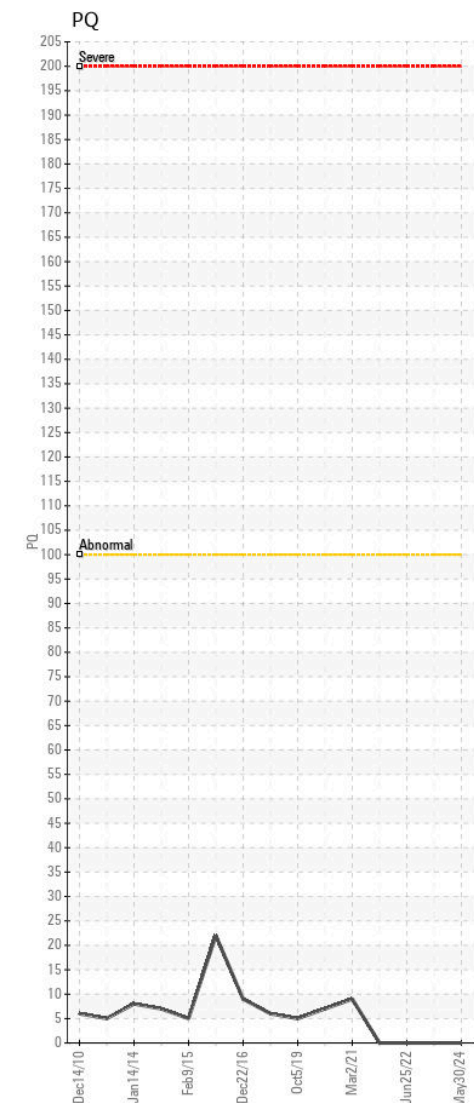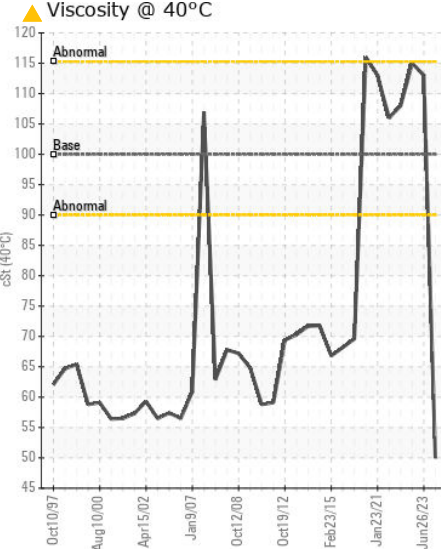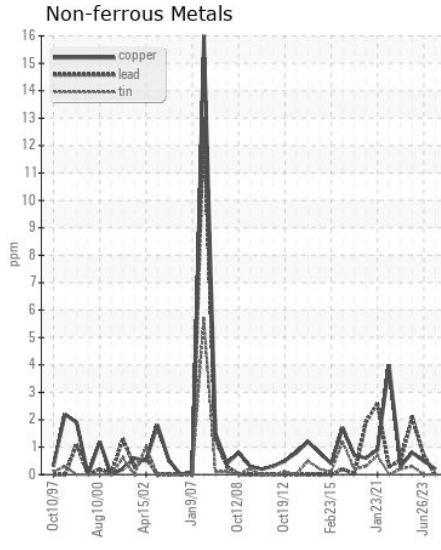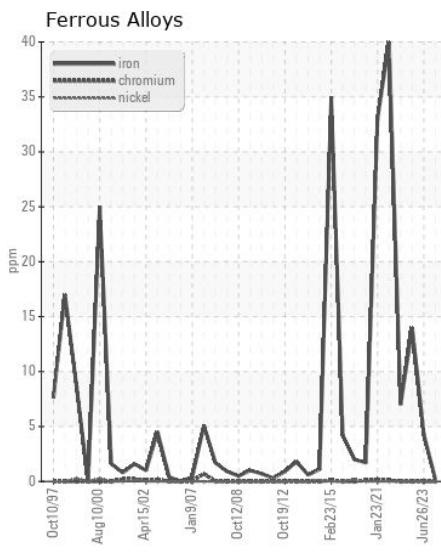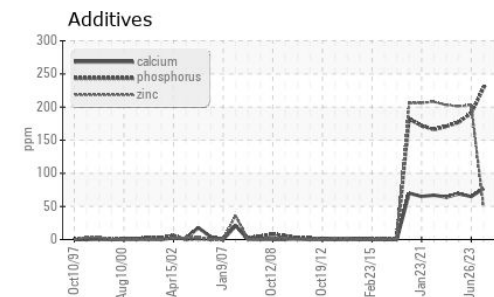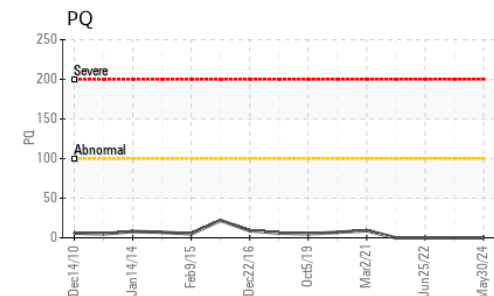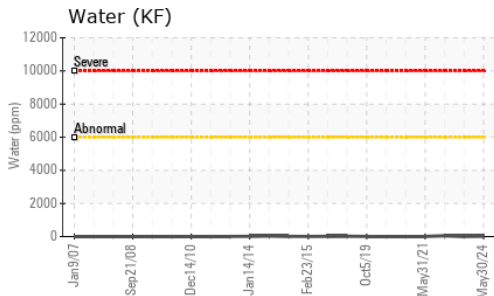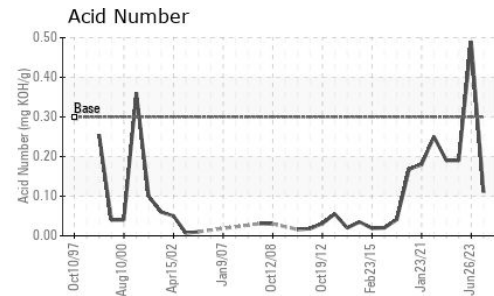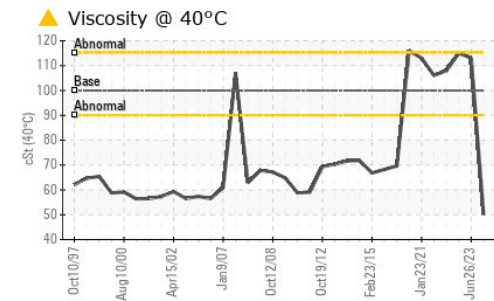

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0929730 **Received** : 05 Jun 2024
Lab Number : 02639895 **Tested** : 06 Jun 2024
Unique Number : 5789057 **Diagnosed** : 06 Jun 2024 - Kevin Marson
Test Package : MAR 2 (Additional Tests: KF)

CANADIAN COAST GUARD
 CCGS HENRY LARSEN, P.O. BOX 5667, 280 SOUTHSIDE RD.
 ST. JOHN'S, NL
 CA A1C 5X1
 Contact: Chief Engineer
 henrylarsence@ccgs-ngcc.gc.ca
 T: (709)687-5198
 F: (709)685-3187

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.