



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
INTERNATIONAL 51928
Component
Diesel Engine
Fluid
PETRO CANADA DURON SAE 10W30 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0935045	WC0915476	WC0904902
Sample Date		Client Info		21 May 2024	14 Apr 2024	15 Feb 2024
Machine Age	kms	Client Info		509542	784778	734944
Oil Age	kms	Client Info		21905	0	0
Filter Age	kms	Client Info		21905	0	0
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185(m)	>100	10	14	17
Chromium	ppm	ASTM D5185(m)	>20	<1	1	1
Nickel	ppm	ASTM D5185(m)	>4	0	<1	<1
Titanium	ppm	ASTM D5185(m)		0	0	0
Silver	ppm	ASTM D5185(m)	>3	0	0	0
Aluminum	ppm	ASTM D5185(m)	>20	1	2	2
Lead	ppm	ASTM D5185(m)	>40	<1	<1	2
Copper	ppm	ASTM D5185(m)	>330	<1	<1	<1
Tin	ppm	ASTM D5185(m)	>15	0	0	<1
Vanadium	ppm	ASTM D5185(m)		0	0	0

CONTAMINATION











There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185(m)	>25	2	3	5
Potassium	ppm	ASTM D5185(m)	>20	<1	<1	2
Fuel		WC Method	>2.0	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	ASTM D7844*	>3	0.2	0.2	0.3
Nitration	Abs/cm	ASTM D7624*	>20	7.9	8.7	9.3
Sulfation	Abs/.1mm	ASTM D7415*	>30	19.8	20.3	21.1
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG	NEG

FLUID CONDITION

The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185(m)		2	2	2
Boron	ppm	ASTM D5185(m)	1	5	5	4
Barium	ppm	ASTM D5185(m)	1	0	0	0
Molybdenum	ppm	ASTM D5185(m)	1	61	62	61
Manganese	ppm	ASTM D5185(m)	1	0	<1	0
Magnesium	ppm	ASTM D5185(m)	10	982	1013	1002
Calcium	ppm	ASTM D5185(m)	2942	1089	1119	1092
Phosphorus	ppm	ASTM D5185(m)	1102	995	1030	1026
Zinc	ppm	ASTM D5185(m)	1351	1214	1262	1235
Sulfur	ppm	ASTM D5185(m)	3903	2475	2377	2483
Oxidation	Abs/.1mm	ASTM D7414*	>25	15.8	17.2	18.5
Visc @ 100°C	cSt	ASTM D7279(m)	11.4	11.4	11.2	11.4

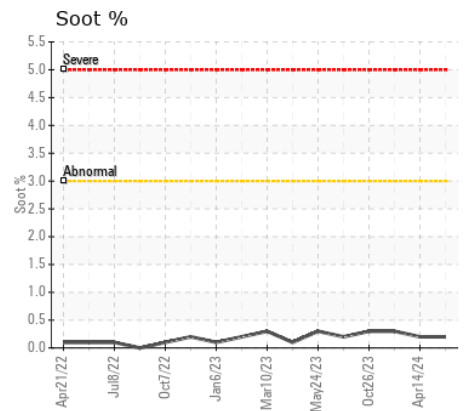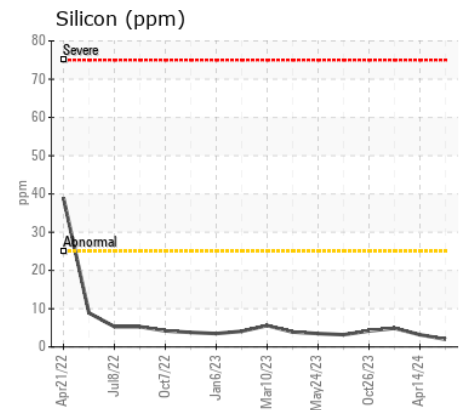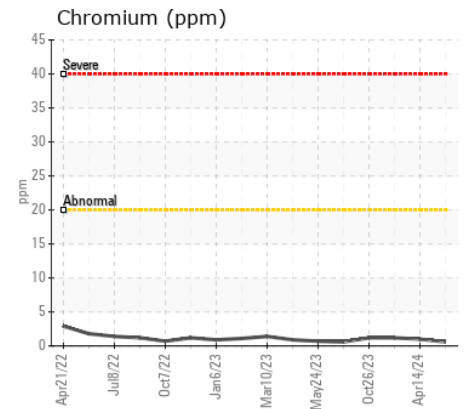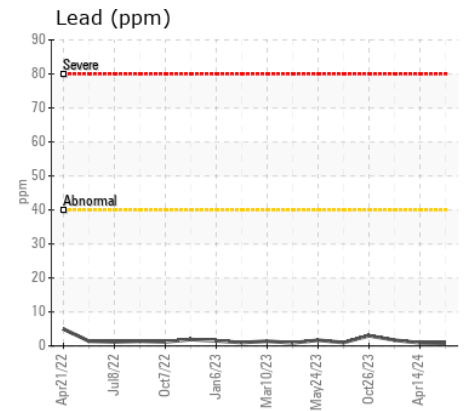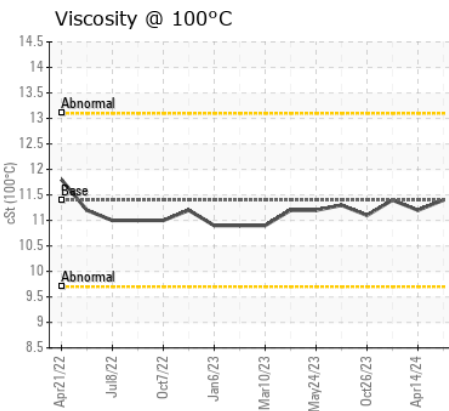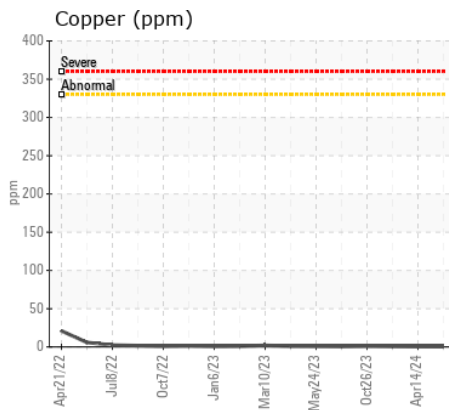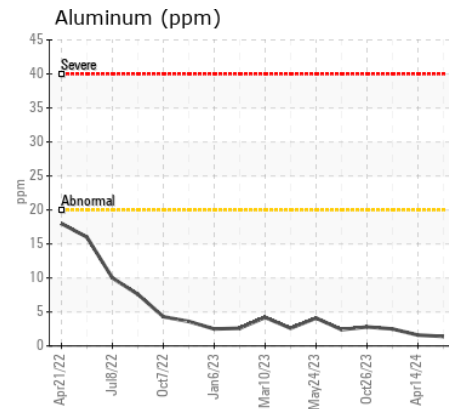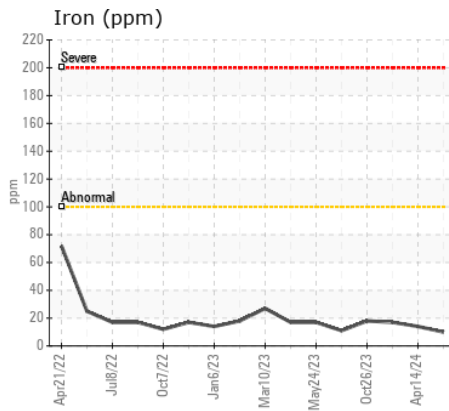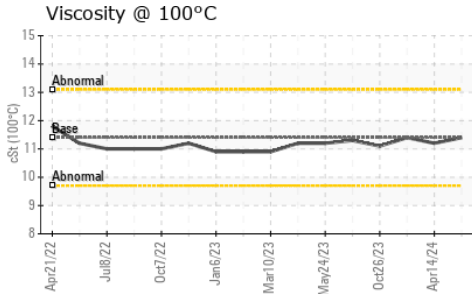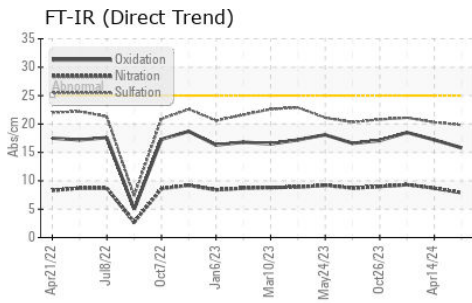

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : WC0935045
Lab Number : 02640149
Unique Number : 5789311
Test Package : MOB 1

Received : 06 Jun 2024
Tested : 06 Jun 2024
Diagnosed : 06 Jun 2024 - Wes Davis

MANITOU LIN TRANSPORT
 75 MUMFORD ROAD
 LIVELY, ON
 CA P3Y 1L1
 Contact: Todd Smith
 tosmith@manitoulintransport.com
 T: (705)562-3302
 F: x:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.