



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
3940014310
 Component
Port IPS
 Fluid
{not provided} (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		VPA062121	---	---
Sample Date		Client Info		09 Jun 2024	---	---
Machine Age	hrs	Client Info		653	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		N/A	---	---
Filter Changed		Client Info		N/A	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

PQ		ASTM D8184*		11	---	---
Iron	ppm	ASTM D5185(m)	>275	240	---	---
Chromium	ppm	ASTM D5185(m)	>4	2	---	---
Nickel	ppm	ASTM D5185(m)	>4	3	---	---
Titanium	ppm	ASTM D5185(m)	>3	0	---	---
Silver	ppm	ASTM D5185(m)		0	---	---
Aluminum	ppm	ASTM D5185(m)	>10	2	---	---
Lead	ppm	ASTM D5185(m)	>4	0	---	---
Copper	ppm	ASTM D5185(m)	>30	14	---	---
Tin	ppm	ASTM D5185(m)	>3	0	---	---
Vanadium	ppm	ASTM D5185(m)		0	---	---
White Metal	scalar	Visual*	NONE	NONE	---	---
Yellow Metal	scalar	Visual*	NONE	NONE	---	---

CONTAMINATION











There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185(m)	>35	18	---	---
Potassium	ppm	ASTM D5185(m)	>20	<1	---	---
Water		WC Method	>0.2	NEG	---	---
Silt	scalar	Visual*	NONE	NONE	---	---
Debris	scalar	Visual*	NONE	NONE	---	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---	---
Appearance	scalar	Visual*	NORML	NORML	---	---
Odor	scalar	Visual*	NORML	NORML	---	---
Emulsified Water	scalar	Visual*	>0.2	NEG	---	---

FLUID CONDITION

Viscosity of sample indicates oil is within SAE 75W90 range, advise investigate. The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185(m)		10	---	---
Boron	ppm	ASTM D5185(m)		265	---	---
Barium	ppm	ASTM D5185(m)		0	---	---
Molybdenum	ppm	ASTM D5185(m)		0	---	---
Manganese	ppm	ASTM D5185(m)		3	---	---
Magnesium	ppm	ASTM D5185(m)		3	---	---
Calcium	ppm	ASTM D5185(m)		4	---	---
Phosphorus	ppm	ASTM D5185(m)		1351	---	---
Zinc	ppm	ASTM D5185(m)		17	---	---
Sulfur	ppm	ASTM D5185(m)		22061	---	---
Visc @ 40°C	cSt	ASTM D7279(m)		105	---	---

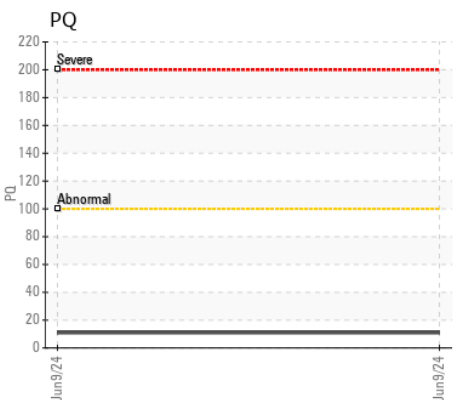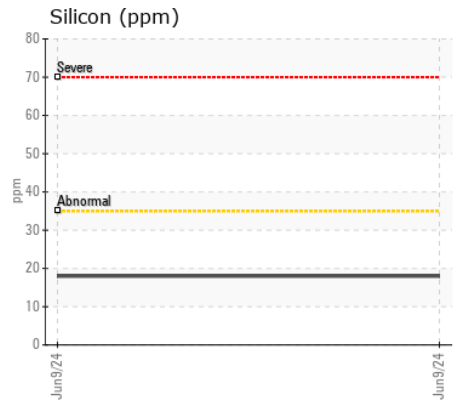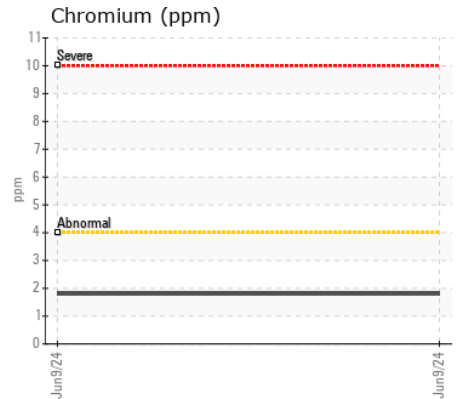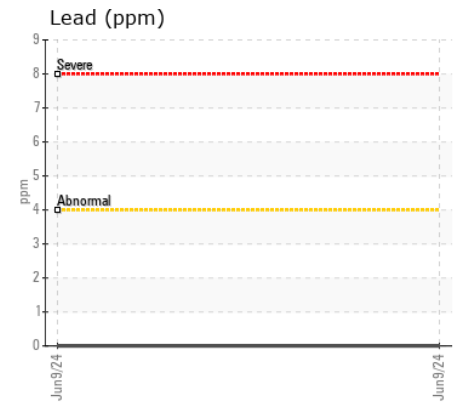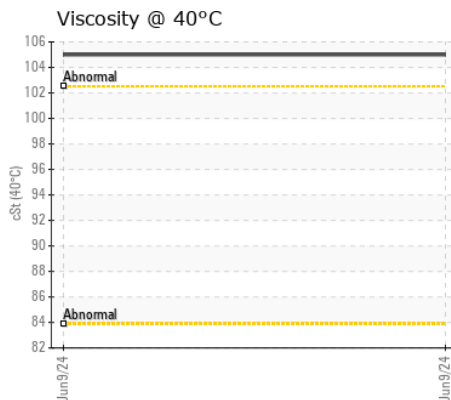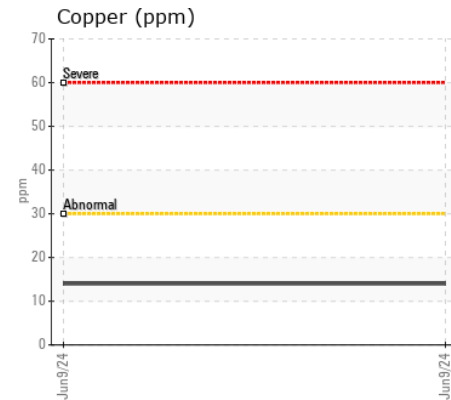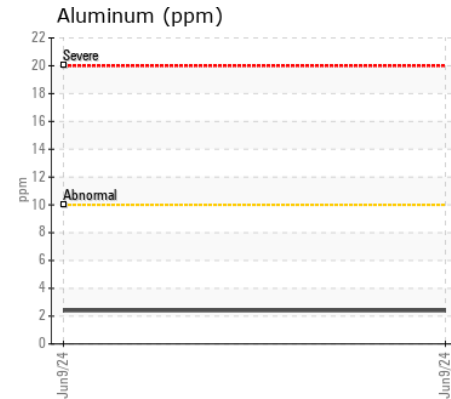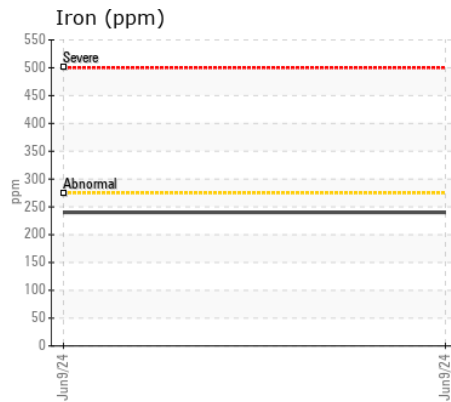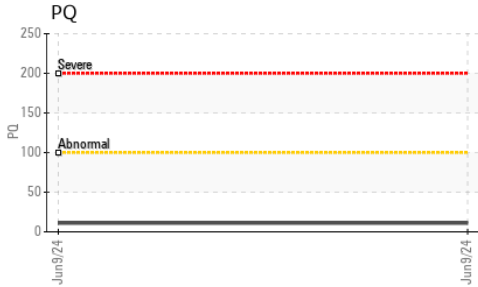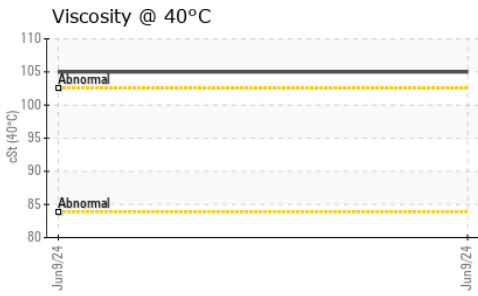

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : VPA062121 **Received** : 10 Jun 2024
Lab Number : 02640876 **Tested** : 11 Jun 2024
Unique Number : 5798415 **Diagnosed** : 11 Jun 2024 - Kevin Marson
Test Package : MOB 1 (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.

Sea Power Ltd
 2077 Amelia Ave
 SIDNEY, BC
 CA V8L 3Z8
 Contact: Kayla Sousa
 service@seapower.ca
 T: (250)656-4341
 F: