

WEAR NORMAL CONTAMINATION NORMAL FLUID CONDITION NORMAL



RECOMMENDATION

Area Store 4 - Fairmont Machine Id JOHN DEERE 850K 1T0850KXCDE246953

Right Inner Final Drive

JÕHN DEERE HY-GARD HYD/TRANS (4 GAL)

Resample at the next service interval to monitor. Please note that this is a corrected copy for data entry updates.

WEAR

All component wear rates are normal.

CONTAMINATION


There is no indication of any contamination in the oil.


FLUID CONDITION


The condition of the oil is acceptable for the time in service.

RANS (4 GA	<u> </u>					
Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LEC0014002	LECP153557	
Sample Date		Client Info		06 Aug 2020	17 Sep 2014	
Machine Age	hrs	Client Info		5933	532	
Oil Age	hrs	Client Info		1000	532	
Filter Age	hrs	Client Info		0	0	
Oil Changed		Client Info		Not Changd	Not Changd	
Filter Changed		Client Info		N/A	N/A	
Sample Status				NORMAL	NORMAL	
PQ		ASTM D8184	>1250	356	35.0	
Iron	ppm	ASTM D5185m	>750	687	112	
Chromium	ppm	ASTM D5185m	>9	6	2	
Nickel	ppm	ASTM D5185m		3	0	
Titanium	ppm	ASTM D5185m		0	0	
Silver	ppm	ASTM D5185m		0	0	
Aluminum	ppm	ASTM D5185m	>40	9	2	
Lead	ppm	ASTM D5185m	>15	<1	2	
Copper	ppm	ASTM D5185m	>40	2	<1	
Tin	ppm	ASTM D5185m		<1	0	
Vanadium	ppm	ASTM D5185m		0	<1	
White Metal	scalar	*Visual	NONE	NONE	LIGHT	
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	
Silicon	ppm	ASTM D5185m	>75	39	5	
Potassium	ppm	ASTM D5185m	>20	5	2	
Water	ppm	WC Method	>0.075	NEG	NEG	
Silt	scalar	*Visual	NONE	NONE	NONE	
Debris	scalar	*Visual	NONE	NONE	NONE	
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	
Appearance	scalar	*Visual	NORML	NORML	NORML	
Odor	scalar	*Visual	NORML	NORML	NORML	
Emulsified Water	scalar	*Visual	>0.075	NEG	NEG	
Sodium	ppm	ASTM D5185m	>51	3	1	
Boron	ppm	ASTM D5185m	6	4	1	
Barium	ppm	ASTM D5185m	0	0	0	
Molybdenum	ppm	ASTM D5185m	0	0	1	
Manganese	ppm	ASTM D5185m		6	<1	
Magnesium	ppm	ASTM D5185m	145	92	112	
Calcium	ppm	ASTM D5185m	3570	3524	3798	
Phosphorus	ppm	ASTM D5185m	1290	1034	1096	
Zinc	ppm	ASTM D5185m	1640	1124	1414	
Sulfur	ppm	ASTM D5185m		4257	0	
Visc @ 40°C	cSt	ASTM D445	57.0	49.8	52.87	

Submitted By: STORE 9 - MARIETTA - LEANNE KENDALL

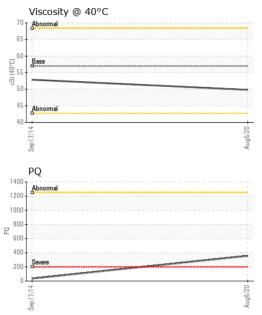

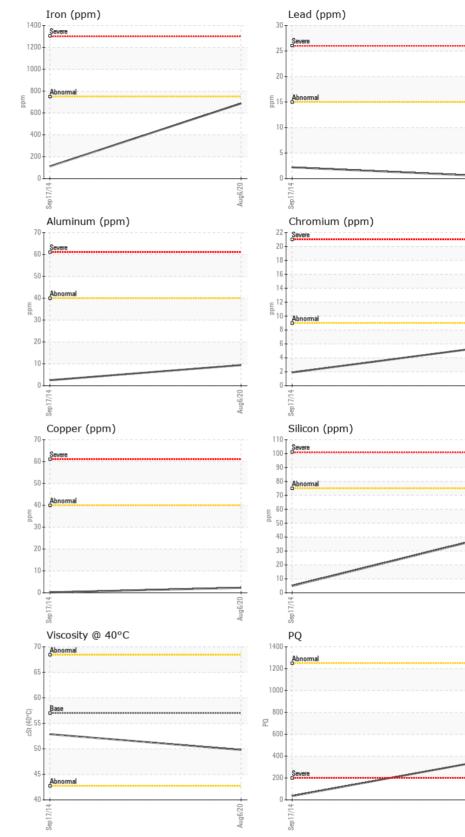

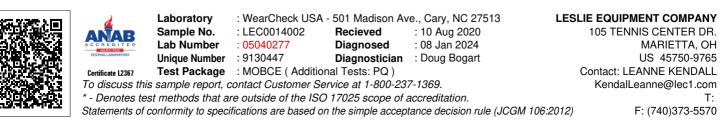

Submitted By: STORE 9 - MARIETTA - LEANNE KENDALL