



OIL ANALYSIS REPORT

WEAR	ABNORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area
Store 9 - Marietta
Machine Id
1DW310EXVKF695527
Component
Diesel Engine
Fluid
JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (9 GAL)

RECOMMENDATION

Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LEC0016659	LEC0006968	---
Sample Date		Client Info		29 Jan 2021	04 Oct 2019	---
Machine Age	hrs	Client Info		1100	515	---
Oil Age	hrs	Client Info		585	515	---
Filter Age	hrs	Client Info		0	515	---
Oil Changed		Client Info		Changed	Changed	---
Filter Changed		Client Info		Changed	Changed	---
Sample Status				ABNORMAL	ABNORMAL	---

WEAR

The copper level is abnormal. In the absence of other significant wear metals, suspect copper due to sources other than wear (i.e. cooling core). All other component wear rates are normal.

Iron	ppm	ASTM D5185m	>51	48	30	---
Chromium	ppm	ASTM D5185m	>11	<1	<1	---
Nickel	ppm	ASTM D5185m	>5	2	3	---
Titanium	ppm	ASTM D5185m		<1	<1	---
Silver	ppm	ASTM D5185m		<1	0	---
Aluminum	ppm	ASTM D5185m	>31	8	8	---
Lead	ppm	ASTM D5185m	>26	1	2	---
Copper	ppm	ASTM D5185m	>26	▲ 238	▲ 258	---
Tin	ppm	ASTM D5185m	>4	0	0	---
Vanadium	ppm	ASTM D5185m		0	0	---
White Metal	scalar	*Visual	NONE	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	---

CONTAMINATION

There is no indication of any contamination in the oil.


Silicon	ppm	ASTM D5185m	>22	7	9	---
Potassium	ppm	ASTM D5185m	>20	0	0	---
Fuel	%	ASTM D3524	>2.1	<1.0	<1.0	---
Water		WC Method	>0.21	NEG	NEG	---
Glycol	%	*ASTM D2982		NEG	NEG	---
Soot %	%	*ASTM D7844	>3	0.3	0.2	---
Nitration	Abs/cm	*ASTM D7624	>20	9	7.8	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	22.8	21	---
Silt	scalar	*Visual	NONE	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.21	NEG	NEG	---

FLUID CONDITION


The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>31	3	10	---
Boron	ppm	ASTM D5185m		198	242	---
Barium	ppm	ASTM D5185m		1	<1	---
Molybdenum	ppm	ASTM D5185m		248	248	---
Manganese	ppm	ASTM D5185m		<1	1	---
Magnesium	ppm	ASTM D5185m		820	895	---
Calcium	ppm	ASTM D5185m		1366	1512	---
Phosphorus	ppm	ASTM D5185m		826	878	---
Zinc	ppm	ASTM D5185m		967	1107	---
Sulfur	ppm	ASTM D5185m		2242	2707	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	16.8	16	---
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	8.7	9	---
Visc @ 100°C	cSt	ASTM D445	15.4	12.7	10.1	---


▲ Non-ferrous Metals

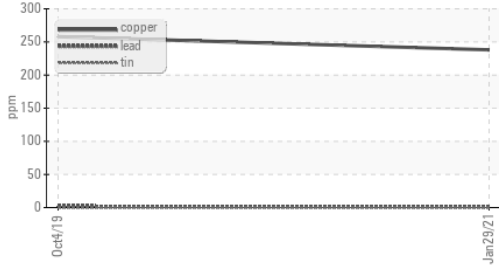


Base Number

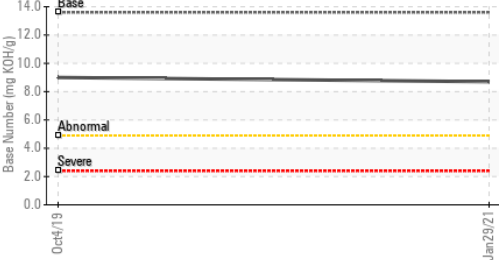


Glycol Contamination

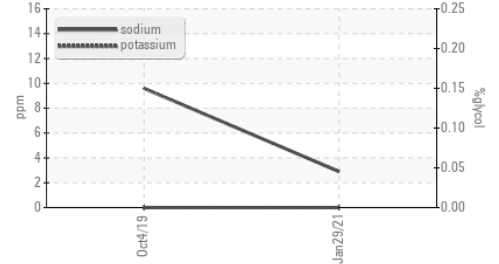


Iron (ppm)

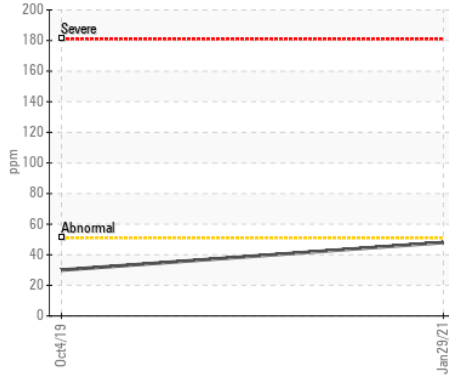


Aluminum (ppm)

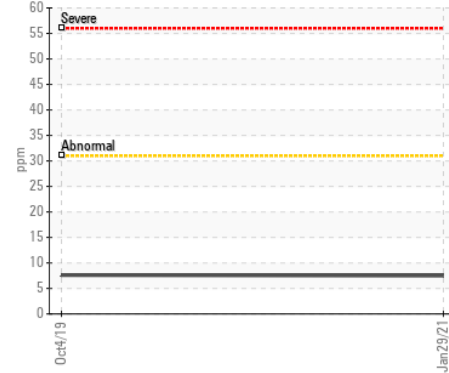


Lead (ppm)

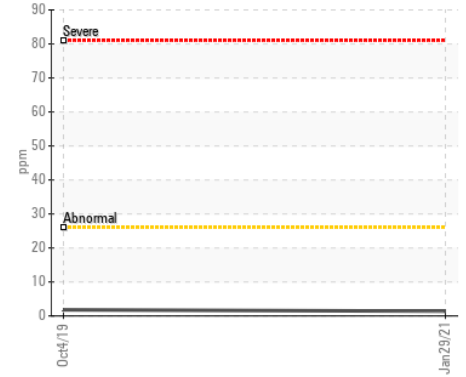


Chromium (ppm)

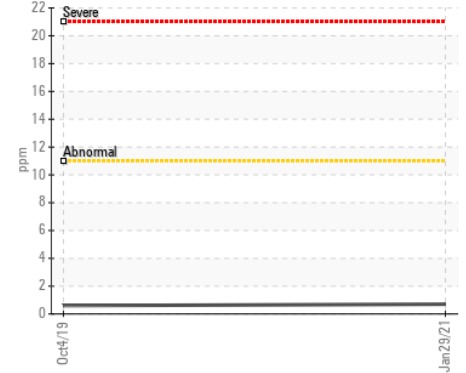


▲ Copper (ppm)

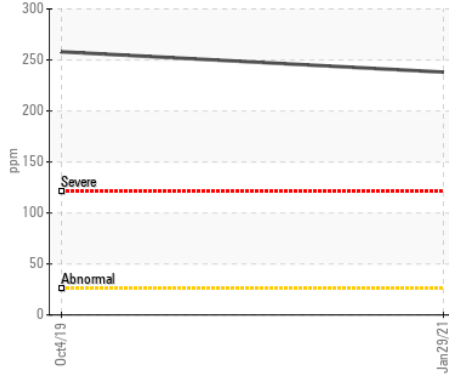


Silicon (ppm)

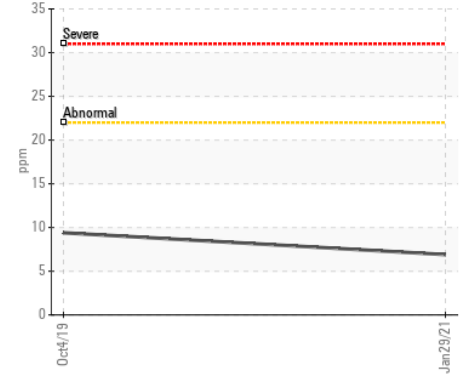


Viscosity @ 100°C

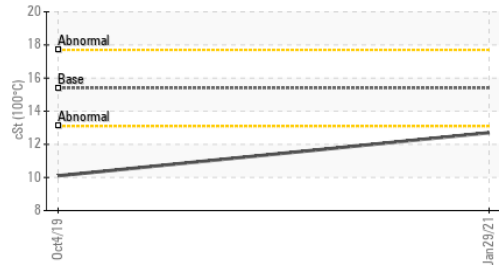

Viscosity @ 100°C

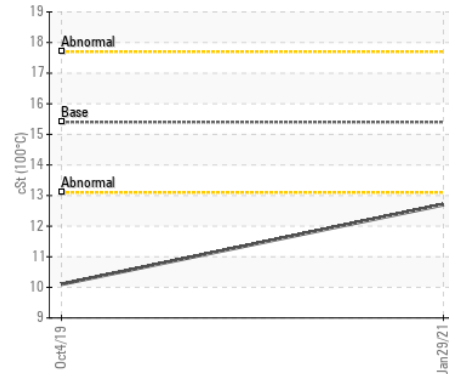

Base Number

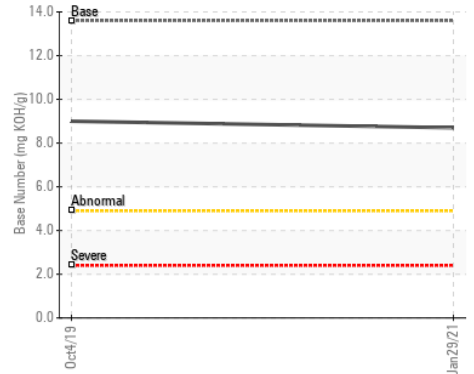

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : LEC0016659 **Received** : 02 Feb 2021
Lab Number : 05173202 **Diagnosed** : 03 Feb 2021
Unique Number : 9348485 **Diagnostician** : Don Baldrige
Test Package : MOBCE (Additional Tests: FuelDilution, Glycol, TBN)

LESLIE EQUIPMENT COMPANY
 105 TENNIS CENTER DR.
 MARIETTA, OH
 US 45750-9765
 Contact: LEANNE KENDALL
 KendalLeanne@lec1.com
 T:
 F: (740)373-5570

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)