



WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Area

[W34635]

Machine Id

JOHN DEERE 325G 1T0325GKCKJ366194

Component

Hydraulic System

Fluid

JOHN DEERE HYDRAU (--- GAL)

### RECOMMENDATION

No corrective action is recommended at this time. Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0106549	---	---
Sample Date		Client Info		07 Mar 2022	---	---
Machine Age	hrs	Client Info		1015	---	---
Oil Age	hrs	Client Info		1015	---	---
Filter Age	hrs	Client Info		1015	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				ABNORMAL	---	---

### WEAR

Metal levels are typical for a new component breaking in.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	35	---	---
Chromium	ppm	ASTM D5185m	>10	1	---	---
Nickel	ppm	ASTM D5185m		0	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	4	---	---
Lead	ppm	ASTM D5185m	>10	2	---	---
Copper	ppm	ASTM D5185m	>75	15	---	---
Tin	ppm	ASTM D5185m	>10	0	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

### CONTAMINATION











There is a high amount of silt (particulates < 14 microns in size) present in the oil.

Silicon	ppm	ASTM D5185m	>20	9	---	---
Potassium	ppm	ASTM D5185m	>20	<1	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	▲ 19853	---	---
Particles >6µm		ASTM D7647	>1300	165	---	---
Particles >14µm		ASTM D7647	>160	11	---	---
Particles >21µm		ASTM D7647	>40	3	---	---
Particles >38µm		ASTM D7647	>10	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ 21/15/11	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

### FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		2	---	---
Boron	ppm	ASTM D5185m		4	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		1	---	---
Manganese	ppm	ASTM D5185m		<1	---	---
Magnesium	ppm	ASTM D5185m		22	---	---
Calcium	ppm	ASTM D5185m	87	267	---	---
Phosphorus	ppm	ASTM D5185m	727	619	---	---
Zinc	ppm	ASTM D5185m	900	792	---	---
Sulfur	ppm	ASTM D5185m	1500	1713	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.75	---	---
Visc @ 40°C	cSt	ASTM D445	65	48.1	---	---

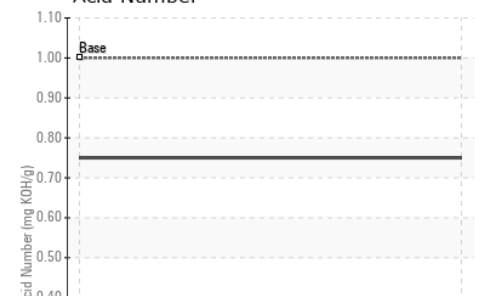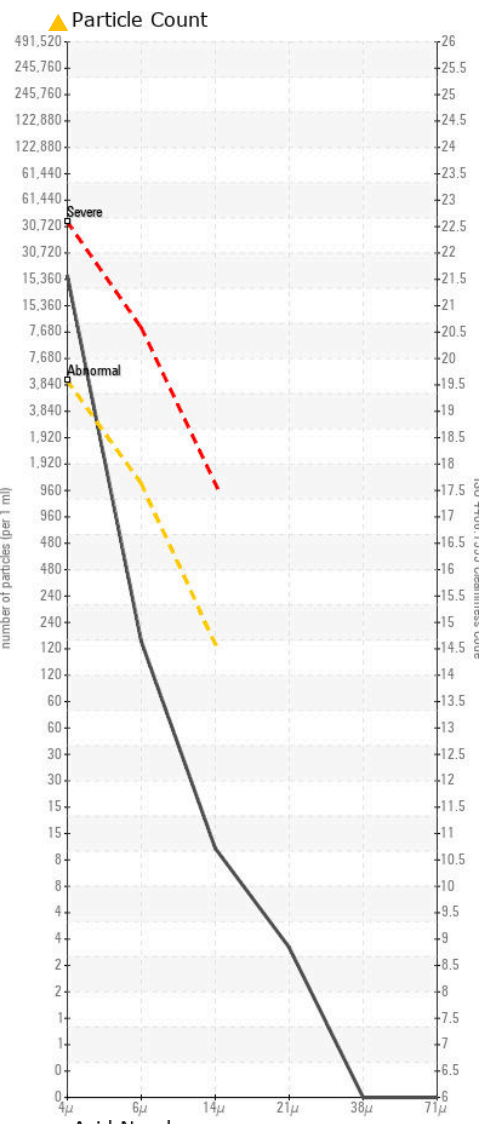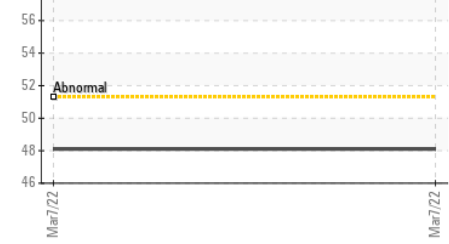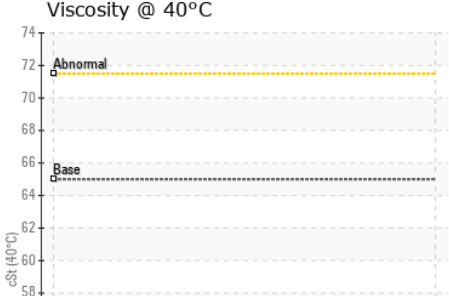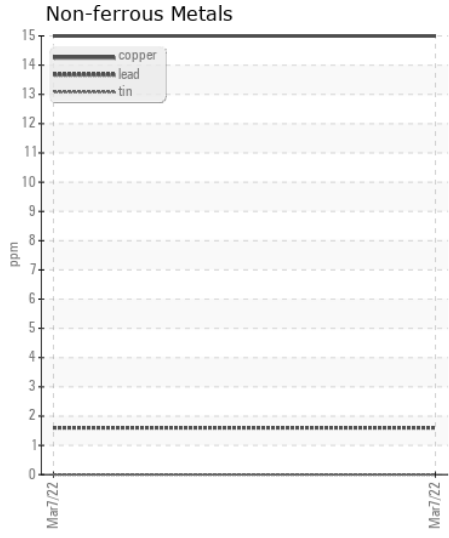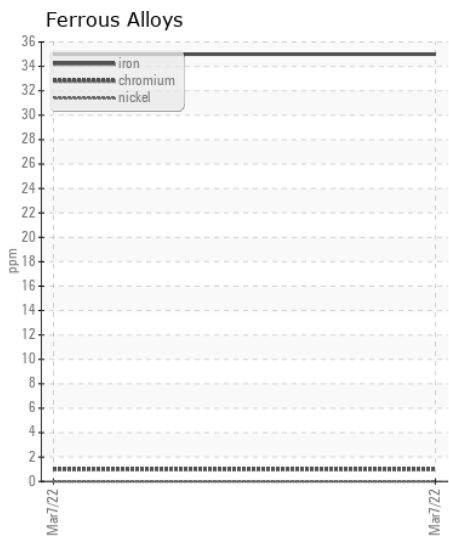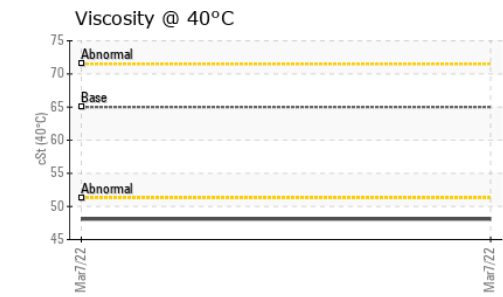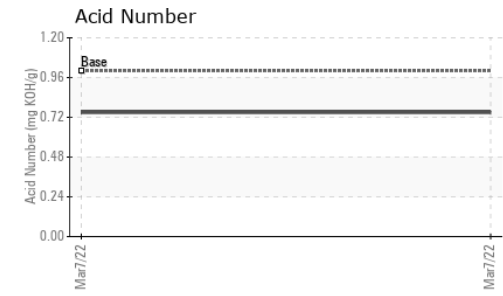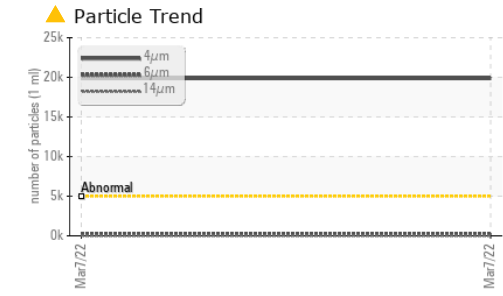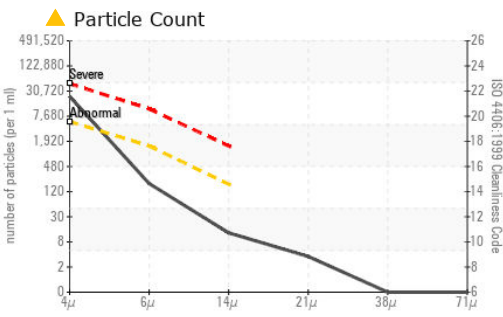

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : JR0106549 **Received** : 08 Mar 2022  
**Lab Number** : 05486509 **Tested** : 10 Mar 2022  
**Unique Number** : 9880728 **Diagnosed** : 10 Mar 2022 - Don Baldrige  
**Test Package** : MOBCE ( Additional Tests: PQ )

**JRE - ASHLAND**  
 11047 LEADBETTER RD  
 ASHLAND, VA  
 US 23005  
 Contact: DAVID ZIEG  
 dzieg@jamesriverequipment.com  
 T: (804)798-6001  
 F: (804)798-0292

To discuss this sample report, contact Customer Service at 1-800-237-1369.  
 \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.  
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)