



WEAR	ABNORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 180G 1FF180GXAJF020850
 Component
Left Inner Final Drive
 Fluid
JOHN DEERE GL-5 80W90 (--- GAL)

RECOMMENDATION

We advise that you check all areas where dirt can enter the system. We recommend that you drain the oil from the component if this has not already been done. We recommend an early resample to monitor this condition.

WEAR

PQ levels are abnormal. Aluminum and chromium and iron ppm levels are abnormal. Titanium ppm levels are marginal. Gear wear is indicated. The high ferrous density (PQ) index indicates that abnormal wear is occurring.










CONTAMINATION

There is a moderate concentration of dirt present in the oil.

FLUID CONDITION

The oil is no longer serviceable as a result of the abnormal and/or severe wear.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0118087	---	---
Sample Date		Client Info		13 Jun 2022	---	---
Machine Age	hrs	Client Info		3568	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Not Changd	---	---
Filter Changed		Client Info		Not Changd	---	---
Sample Status				ABNORMAL	---	---
PQ		ASTM D8184	>1250	▲ 2939	---	---
Iron	ppm	ASTM D5185m	>750	▲ 2321	---	---
Chromium	ppm	ASTM D5185m	>9	▲ 22	---	---
Nickel	ppm	ASTM D5185m		6	---	---
Titanium	ppm	ASTM D5185m		▲ 14	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>40	▲ 75	---	---
Lead	ppm	ASTM D5185m	>15	<1	---	---
Copper	ppm	ASTM D5185m	>40	4	---	---
Tin	ppm	ASTM D5185m		<1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	LIGHT	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---
Silicon	ppm	ASTM D5185m	>75	▲ 801	---	---
Potassium	ppm	ASTM D5185m	>20	11	---	---
Water		WC Method	>0.075	NEG	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.075	NEG	---	---
Sodium	ppm	ASTM D5185m	>51	1	---	---
Boron	ppm	ASTM D5185m		23	---	---
Barium	ppm	ASTM D5185m		<1	---	---
Molybdenum	ppm	ASTM D5185m		2	---	---
Manganese	ppm	ASTM D5185m		18	---	---
Magnesium	ppm	ASTM D5185m		4	---	---
Calcium	ppm	ASTM D5185m		41	---	---
Phosphorus	ppm	ASTM D5185m		179	---	---
Zinc	ppm	ASTM D5185m		13	---	---
Sulfur	ppm	ASTM D5185m		9175	---	---
Visc @ 40°C	cSt	ASTM D445		243	---	---

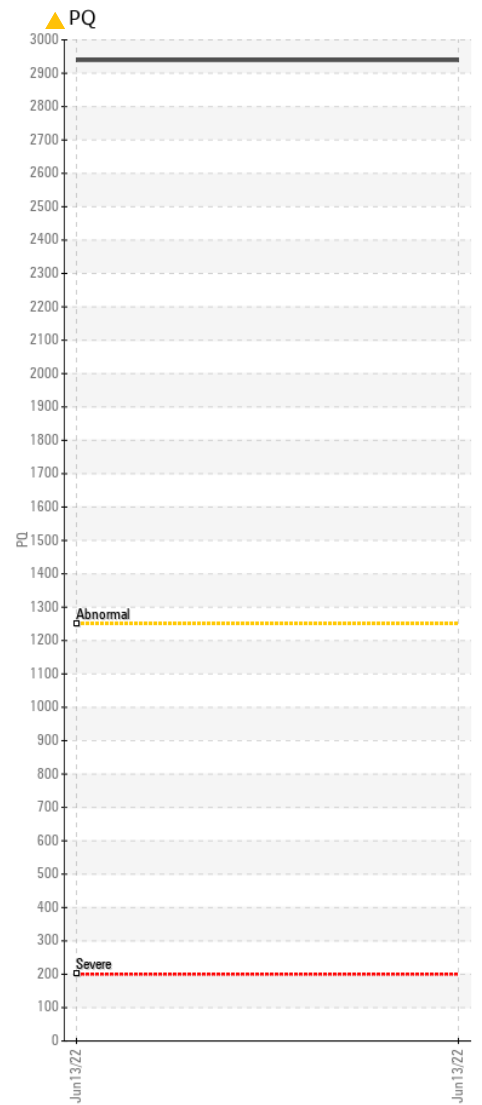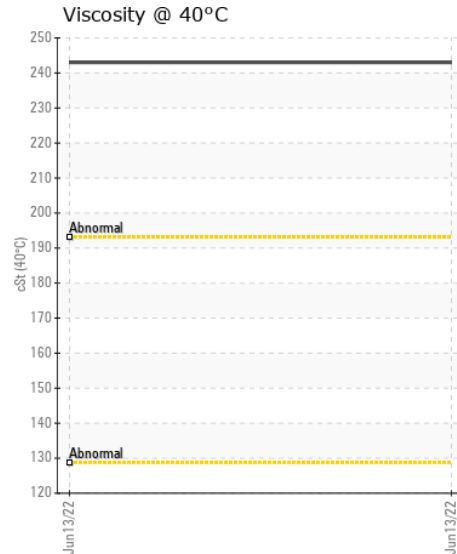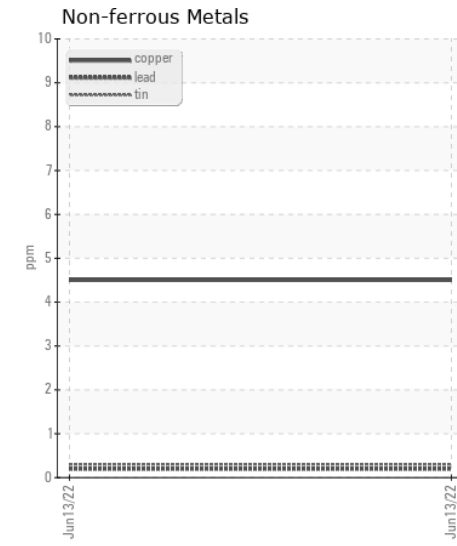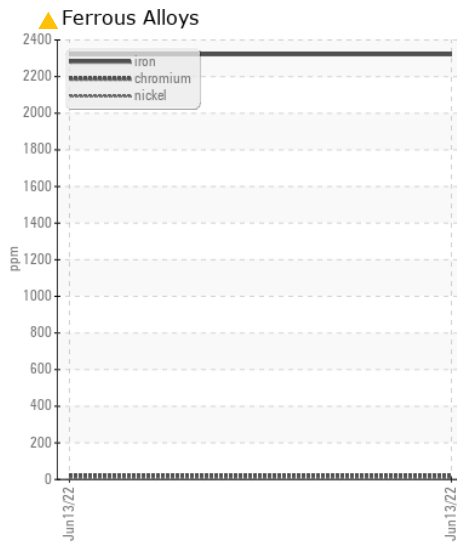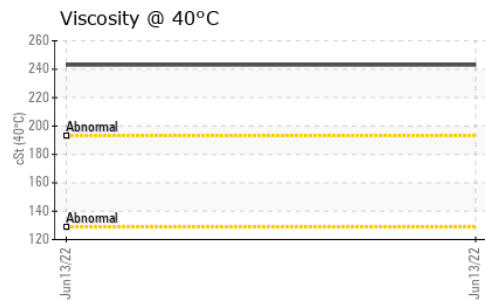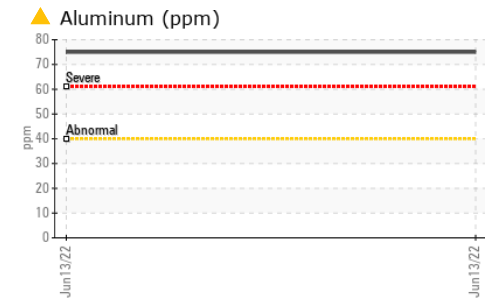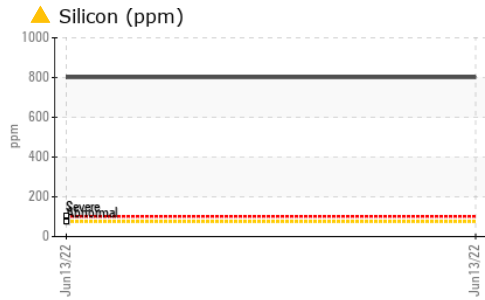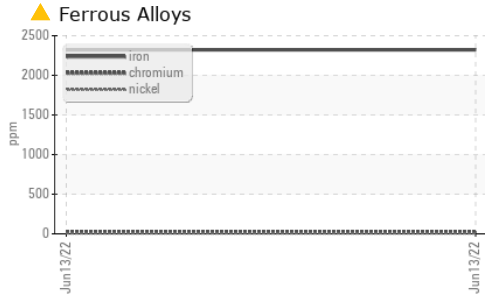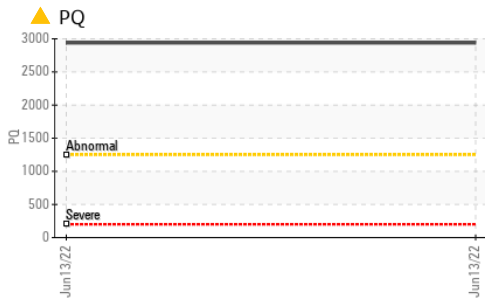

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : JR0118087

Lab Number : 05569266

Unique Number : 10013666

Test Package : CONST (Additional Tests: PQ)

Received : 15 Jun 2022

Tested : 16 Jun 2022

Diagnosed : 16 Jun 2022 - Angela Borella

JRE - NEW BERN
3816 MARTIN LUTHER KING BLVD
NEW BERN, NC
US 28562

Contact: JEFF BROWN
jeff.brown@jamesriverequipment.com

T: (252)638-5838

F: (252)638-2949

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)