



WEAR	<b>NORMAL</b>
CONTAMINATION	<b>NORMAL</b>
FLUID CONDITION	<b>NORMAL</b>

Machine Id  
**CWR**  
Component  
**Starboard Main Engine**  
Fluid  
**CHEVRON DELO 400 XLE 15W40 (39 GAL)**

**RECOMMENDATION**

Resample at the next service interval to monitor. Note that there appears to be a discrepancy in the total time on this component, when compared to the historical data.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		<b>MW05981757</b>	MW05877881	MW05749255
Sample Date		Client Info		<b>16 Oct 2023</b>	19 Jun 2023	24 Jan 2023
Machine Age	hrs	Client Info		<b>49279</b>	49704	49053
Oil Age	hrs	Client Info		<b>1</b>	651	483
Filter Age	hrs	Client Info		<b>0</b>	0	0
Oil Changed		Client Info		<b>N/A</b>	N/A	N/A
Filter Changed		Client Info		<b>N/A</b>	N/A	N/A
Sample Status				<b>NORMAL</b>	NORMAL	NORMAL

**WEAR**

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>75	<b>3</b>	12	22
Chromium	ppm	ASTM D5185m	>8	<b>&lt;1</b>	<1	<1
Nickel	ppm	ASTM D5185m	>2	<b>&lt;1</b>	<1	<1
Titanium	ppm	ASTM D5185m	>3	<b>&lt;1</b>	<1	<1
Silver	ppm	ASTM D5185m	>2	<b>0</b>	0	0
Aluminum	ppm	ASTM D5185m	>15	<b>2</b>	2	4
Lead	ppm	ASTM D5185m	>18	<b>0</b>	1	7
Copper	ppm	ASTM D5185m	>80	<b>&lt;1</b>	2	3
Tin	ppm	ASTM D5185m	>14	<b>&lt;1</b>	<1	1
Vanadium	ppm	ASTM D5185m		<b>&lt;1</b>	0	<1
White Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE

**CONTAMINATION**







There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>20	<b>4</b>	5	6
Potassium	ppm	ASTM D5185m	>20	<b>3</b>	4	3
Fuel		WC Method	>4.0	<b>&lt;1.0</b>	<1.0	<1.0
Water		WC Method	>0.1	<b>NEG</b>	NEG	NEG
Glycol		WC Method		<b>NEG</b>	NEG	NEG
Soot %	%	*ASTM D7844		<b>0.1</b>	0.3	0.4
Nitration	Abs/cm	*ASTM D7624	>20	<b>5.0</b>	9.9	9.9
Sulfation	Abs/.1mm	*ASTM D7415	>30	<b>19.4</b>	24.1	24.8
Silt	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Debris	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Appearance	scalar	*Visual	NORML	<b>NORML</b>	NORML	NORML
Odor	scalar	*Visual	NORML	<b>NORML</b>	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	<b>NEG</b>	NEG	NEG

**FLUID CONDITION**

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>75	<b>&lt;1</b>	<1	0
Boron	ppm	ASTM D5185m		<b>429</b>	295	272
Barium	ppm	ASTM D5185m		<b>10</b>	2	<1
Molybdenum	ppm	ASTM D5185m		<b>87</b>	103	101
Manganese	ppm	ASTM D5185m		<b>0</b>	<1	<1
Magnesium	ppm	ASTM D5185m		<b>385</b>	515	570
Calcium	ppm	ASTM D5185m		<b>1315</b>	1545	1624
Phosphorus	ppm	ASTM D5185m	760	<b>846</b>	734	746
Zinc	ppm	ASTM D5185m	830	<b>997</b>	890	928
Sulfur	ppm	ASTM D5185m	2770	<b>3052</b>	2814	2965
Oxidation	Abs/.1mm	*ASTM D7414	>25	<b>13.7</b>	20.9	22.6
Base Number (BN)	mg KOH/g	ASTM D2896	10.7	<b>8.3</b>	8.4	7.8
Visc @ 100°C	cSt	ASTM D445	14.9	<b>14.1</b>	13.8	14.1

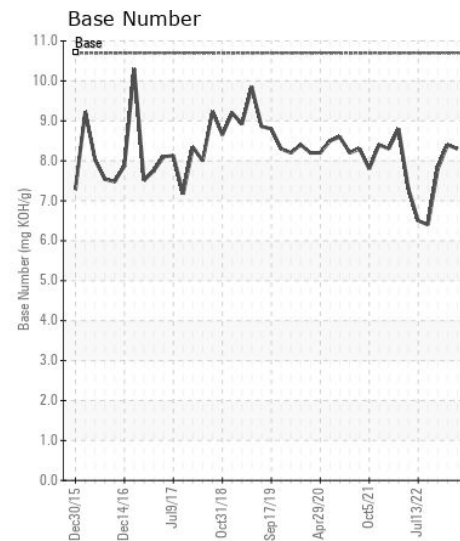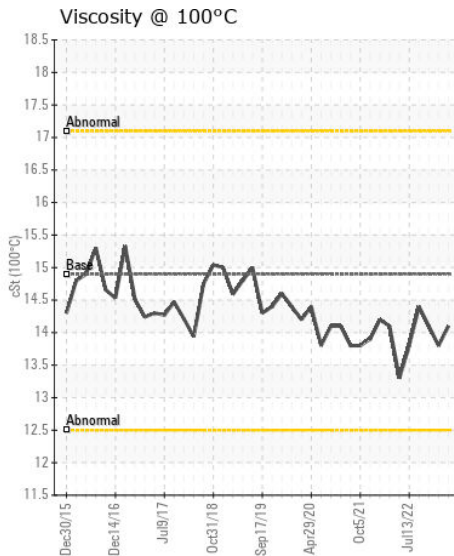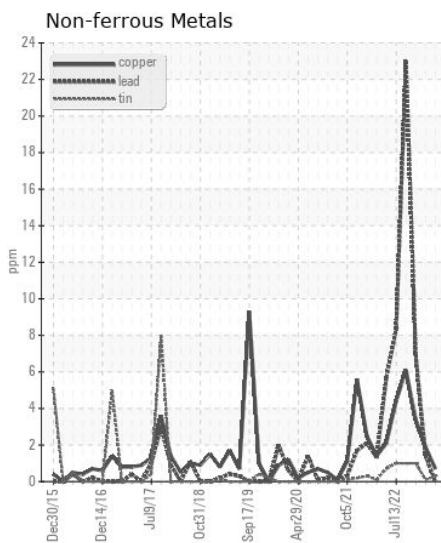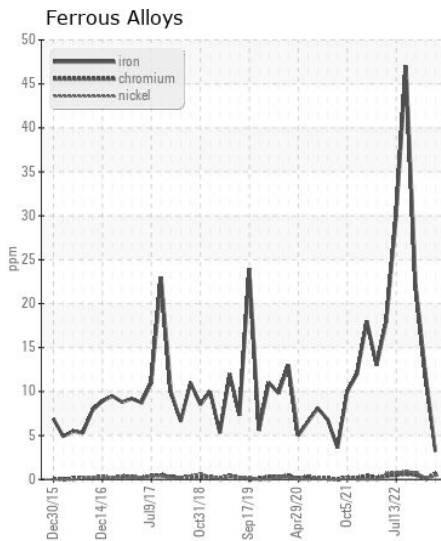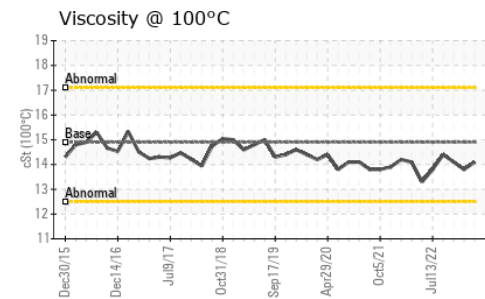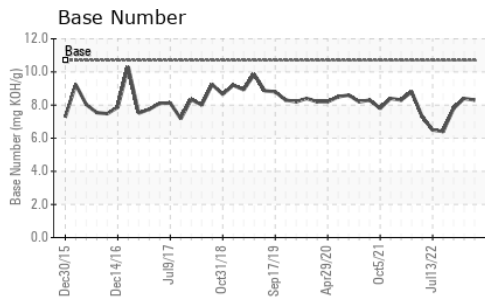

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : MW05981757  
**Lab Number** : 05981757  
**Unique Number** : 10699052  
**Test Package** : MAR 2

**Received** : 17 Oct 2023  
**Tested** : 18 Oct 2023  
**Diagnosed** : 19 Oct 2023 - Don Baldrige

**ILLINOIS MARINE TOWING**  
 PO BOX 391  
 LEMONT, IL  
 US 60439  
 Contact: RHETT DANIEL  
 rdaniel@imtowing.com  
 T: (630)280-4926  
 F: (630)739-2041

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)