



Machine Id
EIC
Component
Port Genset
Fluid
CHEVRON URSA SUPER PLUS 40 (--- GAL)

RECOMMENDATION

No corrective action is recommended at this time. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		MW06028300	MW05981752	MW05981748
Sample Date		Client Info		06 Dec 2023	16 Oct 2023	16 Oct 2023
Machine Age	hrs	Client Info		36865	36352	35672
Oil Age	hrs	Client Info		513	680	662
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		N/A	N/A	N/A
Filter Changed		Client Info		N/A	N/A	N/A
Sample Status				ATTENTION	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>50	2	3	3
Chromium	ppm	ASTM D5185m	>4	<1	<1	<1
Nickel	ppm	ASTM D5185m	>2	0	<1	<1
Titanium	ppm	ASTM D5185m		<1	7	6
Silver	ppm	ASTM D5185m	>5	0	0	0
Aluminum	ppm	ASTM D5185m	>12	2	2	2
Lead	ppm	ASTM D5185m	>17	0	2	0
Copper	ppm	ASTM D5185m	>70	0	<1	<1
Tin	ppm	ASTM D5185m	>15	0	<1	<1
Vanadium	ppm	ASTM D5185m		0	<1	<1
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION








Fuel content negligible. There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>25	4	2	2
Potassium	ppm	ASTM D5185m	>20	2	2	2
Fuel	%	ASTM D3524	>4.0	1.5	<1.0	<1.0
Water		WC Method	>0.1	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844		0.1	0.1	0.1
Nitration	Abs/cm	*ASTM D7624	>20	7.5	7.8	7.5
Sulfation	Abs/.1mm	*ASTM D7415	>30	17.4	19.1	19.0
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG	NEG

FLUID CONDITION

The oil viscosity is lower than normal. The BN result indicates that there is suitable alkalinity remaining in the oil. Confirm oil type.

Sodium	ppm	ASTM D5185m		1	0	0
Boron	ppm	ASTM D5185m		92	123	144
Barium	ppm	ASTM D5185m		5	10	10
Molybdenum	ppm	ASTM D5185m		34	60	62
Manganese	ppm	ASTM D5185m		0	0	0
Magnesium	ppm	ASTM D5185m		185	693	673
Calcium	ppm	ASTM D5185m		2110	1351	1336
Phosphorus	ppm	ASTM D5185m	1000	880	776	824
Zinc	ppm	ASTM D5185m	1090	1034	964	962
Sulfur	ppm	ASTM D5185m		3936	3196	3053
Oxidation	Abs/.1mm	*ASTM D7414	>25	11.8	15.4	14.7
Base Number (BN)	mg KOH/g	ASTM D2896	7.4	7.4	7.5	7.5
Visc @ 100°C	cSt	ASTM D445	14.7	11.1	12.7	12.8

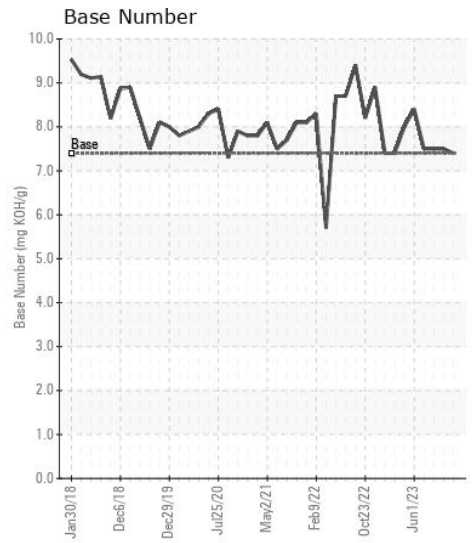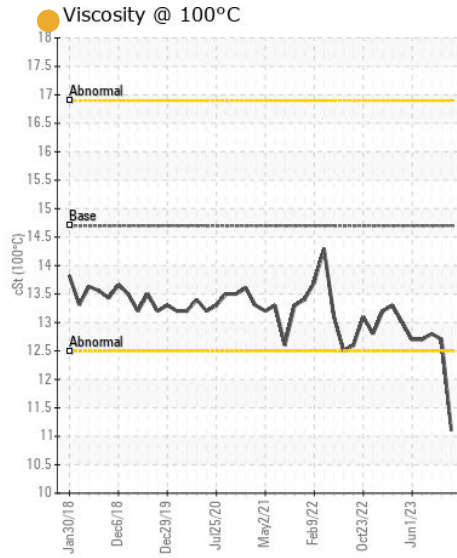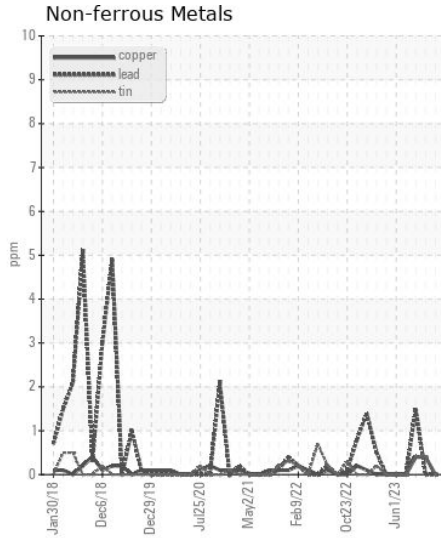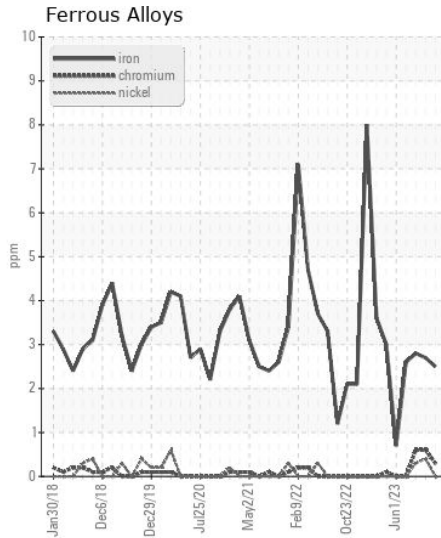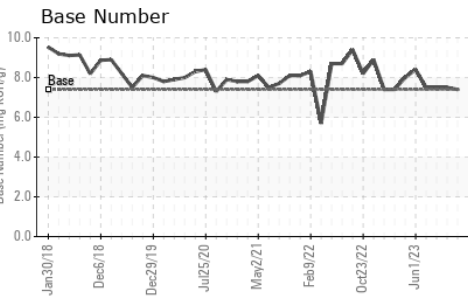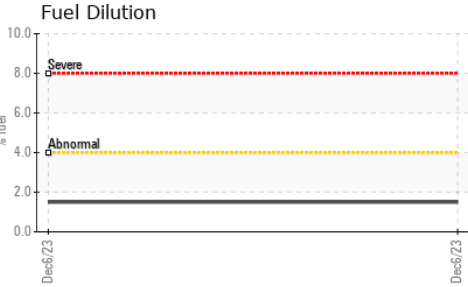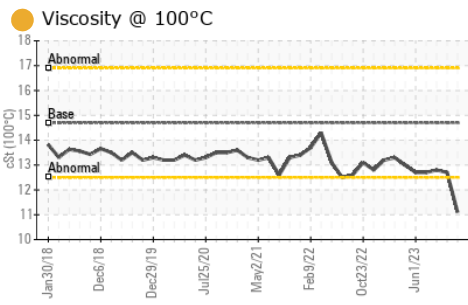

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : MW06028300 **Received** : 07 Dec 2023
Lab Number : 06028300 **Tested** : 14 Dec 2023
Unique Number : 10778091 **Diagnosed** : 14 Dec 2023 - Jonathan Hester
Test Package : MAR 2 (Additional Tests: FuelDilution, PercentFuel)

ILLINOIS MARINE TOWING
 PO BOX 391
 LEMONT, IL
 US 60439
 Contact: RHETT DANIEL
 rdaniel@imtowing.com
 T: (630)280-4926
 F: (630)739-2041

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)