WEAR CONTAMINATION FLUID CONDITION

NORMAL NORMAL NORMAL


[W8326]

JOHN DEERE 350P 1FF350PATPF000479

Component Left Final Drive

Fluid
IOUN DEEDE GL 5 90W00 (0 OTS)

JOHN DEERE GL-5 80W90 (9 QTS)							
RECOMMENDATION	Test	UOM	Method	Limit/Abn	Current	History1	History2
Resample at the next service interval to monitor. (Customer Sample Comment: W8326)	Sample Number		Client Info		JR0183238	JR0185570	
	Sample Date		Client Info		03 Jan 2024	31 Aug 2023	
	Machine Age	hrs	Client Info		1027	517	
	Oil Age	hrs	Client Info		1027	517	
	Filter Age	hrs	Client Info		0	0	
	Oil Changed		Client Info		Not Changd	Not Changd	
	Filter Changed		Client Info		N/A	N/A	
	Sample Status				NORMAL	NORMAL	
WEAR	PQ		ASTM D8184	>1250	252	119	
All component wear rates are normal.	Iron	ppm	ASTM D5185m	>750	323	209	
	Chromium	ppm	ASTM D5185m		4	4	
	Nickel	ppm	ASTM D5185m		0	0	
	Titanium	ppm	ASTM D5185m		0	<1	
	Silver	ppm	ASTM D5185m		0	0	
	Aluminum	ppm	ASTM D5185m	>40	<1	<1	
	Lead	ppm	ASTM D5185m	>15	0	0	
	Copper	ppm	ASTM D5185m	>40	0	<1	
	Tin	ppm	ASTM D5185m	>10	0	0	
	Vanadium	ppm	ASTM D5185m		0	<1	
	White Metal	scalar	*Visual	NONE	MODER	NONE	
	Yellow Metal	scalar	*Visual	NONE	NONE	NONE	
CONTAMINATION	Silicon	ppm	ASTM D5185m		21	14	
There is no indication of any contamination in the oil.	Potassium	ppm	ASTM D5185m		<1	0	
	Water			>0.075	NEG	NEG	
	Silt	scalar	*Visual	NONE	NONE	MODER	
	Debris	scalar	*Visual	NONE	NONE	NONE	
	Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	
	Appearance	scalar	*Visual	NORML	NORML	NORML	
	Odor	scalar	*Visual	NORML	NORML	NORML	
	Emulsified Water	scalar	*Visual	>0.075	NEG	NEG	
FLUID CONDITION	Sodium	ppm	ASTM D5185m	>51	<1	<1	
The condition of the oil is acceptable for the time in service.	Boron	ppm	ASTM D5185m		72	94	
	Barium	ppm	ASTM D5185m		2	0	
	Molybdenum	ppm	ASTM D5185m		0	<1	
	Manganese	ppm	ASTM D5185m		5	5	
	Magnesium	ppm	ASTM D5185m		0	0	
	Calcium	ppm	ASTM D5185m		18	46	
	Phosphorus	ppm	ASTM D5185m		522	536	
	Zinc	ppm	ASTM D5185m		7	11	
	Sulfur	ppm	ASTM D5185m		15428	17635	
	Visc @ 40°C	cSt	ASTM D445		187	185	

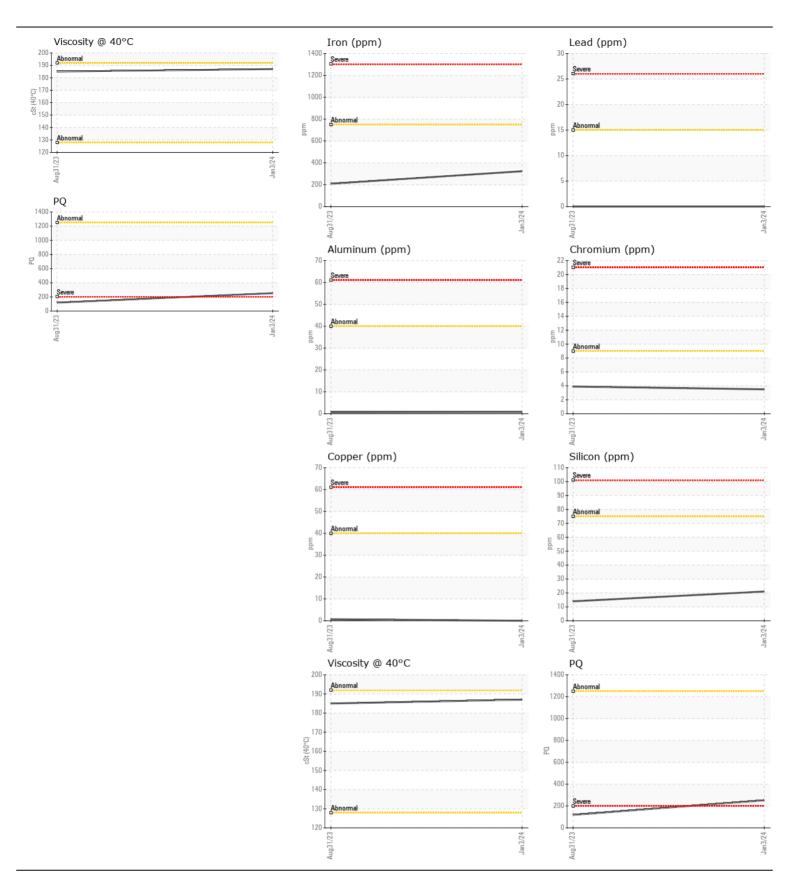



Laboratory Sample No. Lab Number **Unique Number**

: JR0183238 : 06054238 : 10820187 Test Package : MOBCE (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 Recieved : 08 Jan 2024 : 09 Jan 2024 Diagnosed

Diagnostician : Sean Felton

Contact: RALEIGH SHOP

sean.betts@jamesriverequipment.com;catherine.anastasio@wearcheck.com T: (919)614-2260

4161 AUBURN CHURCH RD

JRE - GARNER

GARNER, NC

US 27529

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation. Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

F: (919)779-5432

Submitted By: Fayetteville - JUSTIN JACKSON