



| | |
|-----------------|---------------|
| WEAR | NORMAL |
| CONTAMINATION | NORMAL |
| FLUID CONDITION | NORMAL |

Machine Id
JOHN DEERE 245G 1FF245GXAMF802160

Component
Diesel Engine

Fluid
JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

| Test | UOM | Method | Limit/Abn | Current | History1 | History2 |
|----------------|-----|-------------|-----------|--------------------|-------------|-------------|
| Sample Number | | Client Info | | JR0195296 | JR0166346 | JR0138086 |
| Sample Date | | Client Info | | 05 Jan 2024 | 17 Mar 2023 | 19 Aug 2022 |
| Machine Age | hrs | Client Info | | 1450 | 899 | 433 |
| Oil Age | hrs | Client Info | | 0 | 0 | 433 |
| Filter Age | hrs | Client Info | | 0 | 0 | 433 |
| Oil Changed | | Client Info | | Changed | Changed | Changed |
| Filter Changed | | Client Info | | Changed | Changed | Changed |
| Sample Status | | | | NORMAL | NORMAL | NORMAL |

WEAR

All component wear rates are normal.

| | | | | | | |
|--------------|--------|-------------|------|--------------|------|------|
| Iron | ppm | ASTM D5185m | >51 | 8 | 8 | 20 |
| Chromium | ppm | ASTM D5185m | >11 | <1 | <1 | <1 |
| Nickel | ppm | ASTM D5185m | >5 | 0 | 0 | 0 |
| Titanium | ppm | ASTM D5185m | | <1 | 0 | 0 |
| Silver | ppm | ASTM D5185m | >3 | 0 | 0 | <1 |
| Aluminum | ppm | ASTM D5185m | >31 | 5 | 4 | 4 |
| Lead | ppm | ASTM D5185m | >26 | <1 | 0 | 1 |
| Copper | ppm | ASTM D5185m | >26 | 3 | 6 | 14 |
| Tin | ppm | ASTM D5185m | >4 | 1 | 2 | 4 |
| Vanadium | ppm | ASTM D5185m | | 0 | 0 | 0 |
| White Metal | scalar | *Visual | NONE | NONE | NONE | NONE |
| Yellow Metal | scalar | *Visual | NONE | NONE | NONE | NONE |

CONTAMINATION







There is no indication of any contamination in the oil.

| | | | | | | |
|------------------|----------|-------------|-------|----------------|-------|-------|
| Silicon | ppm | ASTM D5185m | >22 | 8 | 10 | 28 |
| Potassium | ppm | ASTM D5185m | >20 | 3 | 0 | 3 |
| Fuel | | WC Method | >2.1 | <1.0 | <1.0 | <1.0 |
| Water | | WC Method | >0.21 | NEG | NEG | NEG |
| Glycol | | WC Method | | NEG | NEG | NEG |
| Soot % | % | *ASTM D7844 | >3 | 0.1 | 0.2 | 0.1 |
| Nitration | Abs/cm | *ASTM D7624 | >20 | 7.6 | 7.5 | 7.5 |
| Sulfation | Abs/.1mm | *ASTM D7415 | >30 | 20.6 | 21.1 | 17.1 |
| Silt | scalar | *Visual | NONE | NONE | NONE | NONE |
| Debris | scalar | *Visual | NONE | NONE | NONE | NONE |
| Sand/Dirt | scalar | *Visual | NONE | NONE | NONE | NONE |
| Appearance | scalar | *Visual | NORML | NORML | NORML | NORML |
| Odor | scalar | *Visual | NORML | NORML | NORML | NORML |
| Emulsified Water | scalar | *Visual | >0.21 | NEG | NEG | NEG |

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

| | | | | | | |
|------------------|----------|-------------|------|--------------|------|------|
| Sodium | ppm | ASTM D5185m | >31 | 0 | 2 | <1 |
| Boron | ppm | ASTM D5185m | | 299 | 219 | 175 |
| Barium | ppm | ASTM D5185m | | 0 | 0 | <1 |
| Molybdenum | ppm | ASTM D5185m | | 207 | 205 | 2 |
| Manganese | ppm | ASTM D5185m | | <1 | 1 | 4 |
| Magnesium | ppm | ASTM D5185m | | 702 | 667 | 30 |
| Calcium | ppm | ASTM D5185m | | 1241 | 1382 | 2145 |
| Phosphorus | ppm | ASTM D5185m | | 1033 | 798 | 989 |
| Zinc | ppm | ASTM D5185m | | 941 | 916 | 1173 |
| Sulfur | ppm | ASTM D5185m | | 5145 | 3262 | 2987 |
| Oxidation | Abs/.1mm | *ASTM D7414 | >25 | 14.9 | 15.0 | 9.7 |
| Base Number (BN) | mg KOH/g | ASTM D2896 | 13.6 | 9.1 | 9.0 | 10.2 |
| Visc @ 100°C | cSt | ASTM D445 | 15.4 | 13.2 | 13.2 | 13.3 |

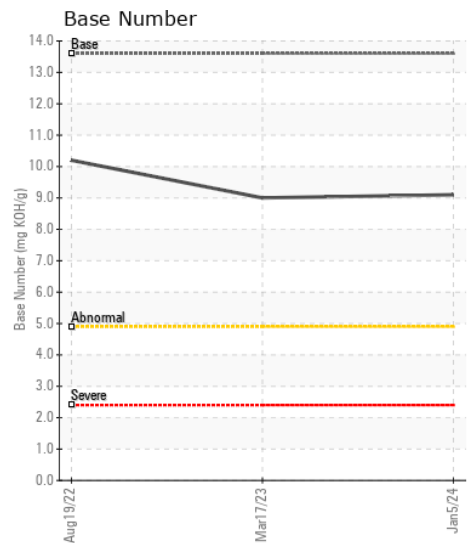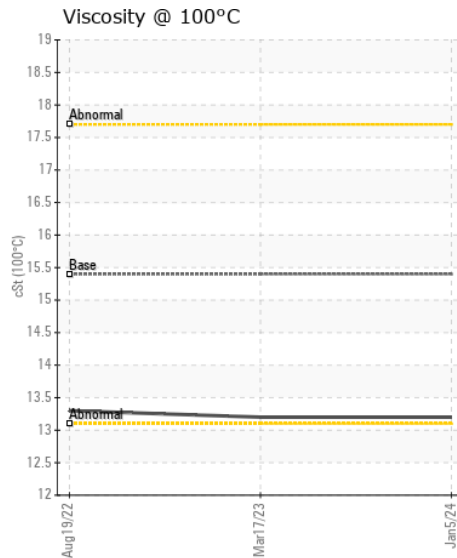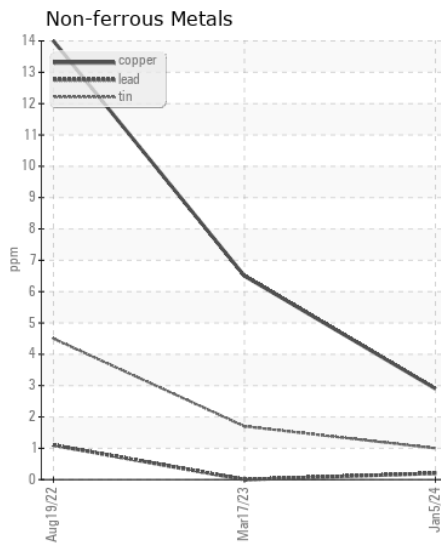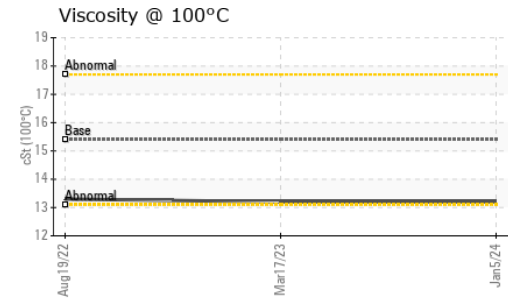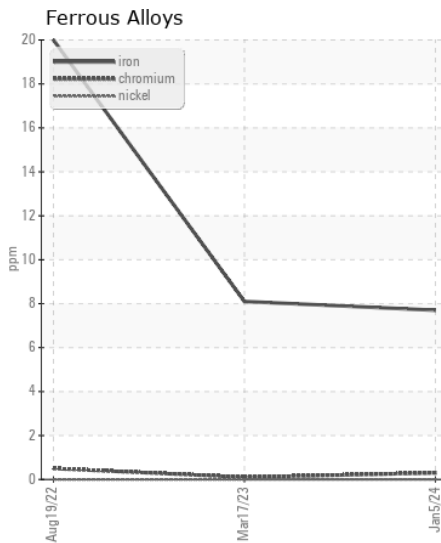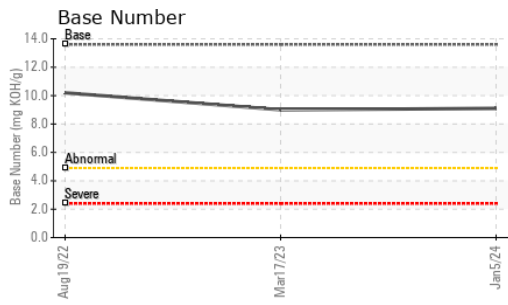

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0195296 **Received** : 09 Jan 2024
Lab Number : 06055713 **Diagnosed** : 10 Jan 2024
Unique Number : 10821662 **Diagnostician** : Wes Davis
Test Package : CONST (Additional Tests: TBN)

JRE - STEPHENSON
 245 YARDMASTER COURT
 STEPHENSON, VA
 US 22656-1761
 Contact: PHIL DAUGHERTY
 pdaugherty@jamesriverequipment.com
 T: x:
 F: (540)693-2588

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)