



# OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id  
**857-5176**  
 Component  
**Diesel Engine**  
 Fluid  
**CHEVRON DELO 400 SAE 10W30 (--- GAL)**

## RECOMMENDATION

Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		RPL0014675	---	---
Sample Date		Client Info		31 Oct 2023	---	---
Machine Age	hrs	Client Info		87	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		N/A	---	---
Filter Changed		Client Info		N/A	---	---
Sample Status				NORMAL	---	---

## WEAR

Metal levels are typical for a new component breaking in.

Iron	ppm	ASTM D5185m	>100	13	---	---
Chromium	ppm	ASTM D5185m	>20	<1	---	---
Nickel	ppm	ASTM D5185m	>4	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m	>3	0	---	---
Aluminum	ppm	ASTM D5185m	>20	14	---	---
Lead	ppm	ASTM D5185m	>40	0	---	---
Copper	ppm	ASTM D5185m	>330	6	---	---
Tin	ppm	ASTM D5185m	>15	0	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

## CONTAMINATION







Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>25	8	---	---
Potassium	ppm	ASTM D5185m	>20	56	---	---
Fuel		WC Method	>5	<1.0	---	---
Water		WC Method	>0.2	NEG	---	---
Glycol		WC Method		NEG	---	---
Soot %	%	*ASTM D7844	>3	0.1	---	---
Nitration	Abs/cm	*ASTM D7624	>20	7.0	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	17.5	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---	---

## FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		2	---	---
Boron	ppm	ASTM D5185m		109	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		0	---	---
Manganese	ppm	ASTM D5185m		0	---	---
Magnesium	ppm	ASTM D5185m		716	---	---
Calcium	ppm	ASTM D5185m		1272	---	---
Phosphorus	ppm	ASTM D5185m	1260	748	---	---
Zinc	ppm	ASTM D5185m	1400	797	---	---
Sulfur	ppm	ASTM D5185m		3160	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	12.1	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	10.1	8.6	---	---
Visc @ 100°C	cSt	ASTM D445	11.1	11.2	---	---

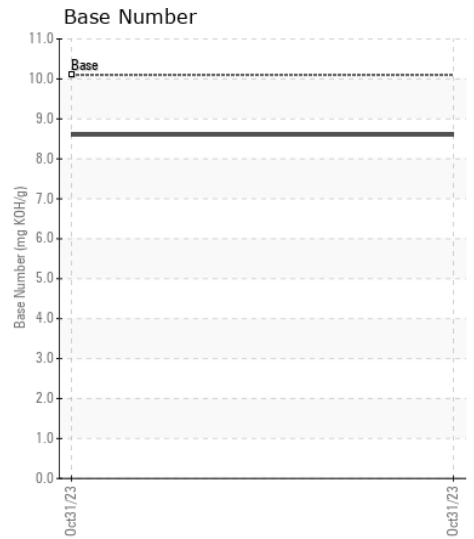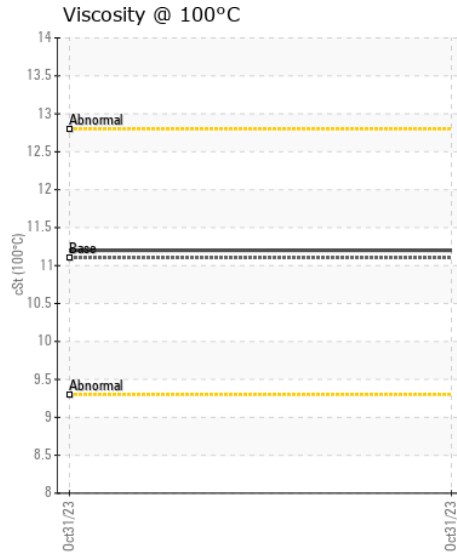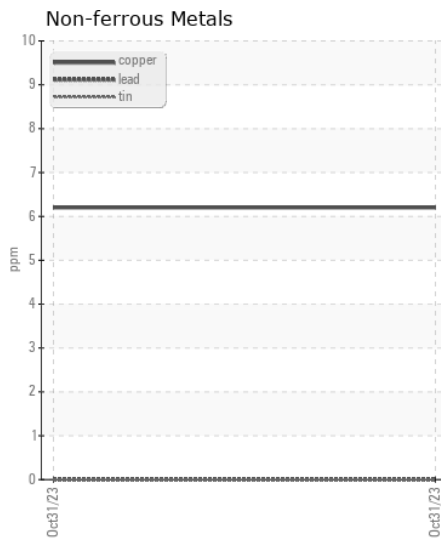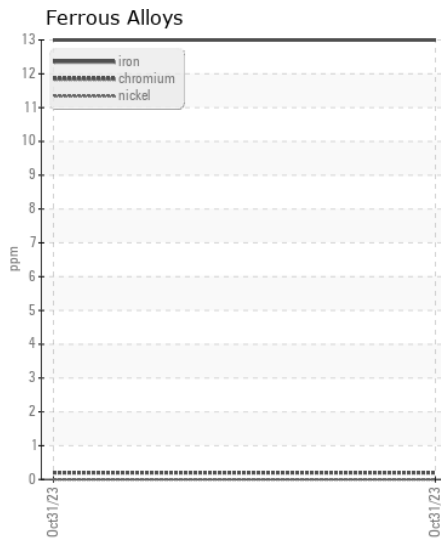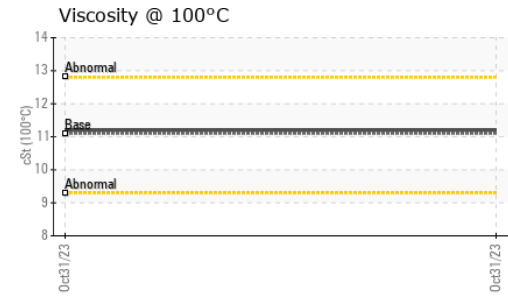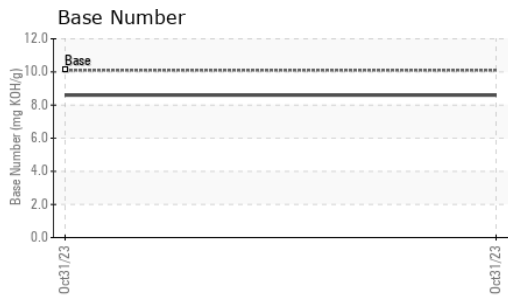

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : RPL0014675 **Received** : 10 Jan 2024  
**Lab Number** : 06056126 **Diagnosed** : 11 Jan 2024  
**Unique Number** : 10822075 **Diagnostician** : Wes Davis  
**Test Package** : FLEET

**RTL PACLEASE - 7001 - Houston**  
 6300 N. Loop East  
 Houston, TX  
 US 77026  
 Contact: RODNEY BRIGGS  
 briggsr@rushenterprises.com  
 T:  
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.  
 \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.  
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)