



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	ABNORMAL

Machine Id
JOHN DEERE 350G 1FF350GXLMF815176

Component
Hydraulic System

Fluid
HITACHI HYDRAULIC SUPER EX 46HN (--- QTS)

RECOMMENDATION

Recommend drain oil if not already done. Reduce drain interval to 2000 hours or drain and flush and use recommended zinc free oil.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0192809	JR0173157	JR0162868
Sample Date		Client Info		22 Dec 2023	03 May 2023	16 Feb 2023
Machine Age	hrs	Client Info		4146	3731	3435
Oil Age	hrs	Client Info		4146	0	3435
Filter Age	hrs	Client Info		0	0	3435
Oil Changed		Client Info		Not Changed	Not Changed	Not Changed
Filter Changed		Client Info		Changed	Not Changed	Not Changed
Sample Status				ABNORMAL	ABNORMAL	ABNORMAL

WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
PQ		ASTM D8184	>50	16	15	20
Iron	ppm	ASTM D5185m	>32	6	10	9
Chromium	ppm	ASTM D5185m	>9	0	<1	0
Nickel	ppm	ASTM D5185m	>5	0	0	0
Titanium	ppm	ASTM D5185m		0	0	0
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m	>9	<1	0	<1
Lead	ppm	ASTM D5185m	>28	0	<1	<1
Copper	ppm	ASTM D5185m	>50	6	8	8
Tin	ppm	ASTM D5185m	>5	<1	<1	<1
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION















The amount and size of particulates present in the system are acceptable.

Silicon	ppm	ASTM D5185m	>11	3	4	3
Potassium	ppm	ASTM D5185m	>20	<1	1	2
Water		WC Method	>0.075	NEG	NEG	NEG
Particles >4µm		ASTM D7647	>80000	25815	14392	20790
Particles >6µm		ASTM D7647	>20000	2541	974	1195
Particles >14µm		ASTM D7647	>640	93	21	30
Particles >21µm		ASTM D7647	>160	24	5	11
Particles >38µm		ASTM D7647	>40	2	1	0
Particles >71µm		ASTM D7647	>10	0	1	0
Oil Cleanliness		ISO 4406 (c)	>23/21/16	22/19/14	21/17/12	22/17/12
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.075	NEG	NEG	NEG

FLUID CONDITION

Zinc level above manufacturer's recommendations. The AN level is acceptable for this fluid.

Sodium	ppm	ASTM D5185m	>21	<1	<1	0
Boron	ppm	ASTM D5185m		0	0	0
Barium	ppm	ASTM D5185m		0	<1	0
Molybdenum	ppm	ASTM D5185m		0	<1	<1
Manganese	ppm	ASTM D5185m		<1	<1	0
Magnesium	ppm	ASTM D5185m		2	4	3
Calcium	ppm	ASTM D5185m		251	337	352
Phosphorus	ppm	ASTM D5185m	827	567	548	552
Zinc	ppm	ASTM D5185m	0	▲ 158	▲ 196	▲ 190
Sulfur	ppm	ASTM D5185m	13	456	575	528
Acid Number (AN)	mg KOH/g	ASTM D8045	0.06	0.53	0.71	0.51
Visc @ 40°C	cSt	ASTM D445	47	47.1	47.4	47.5

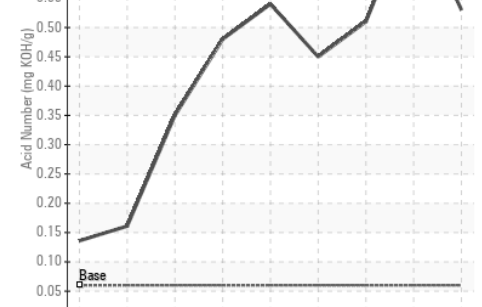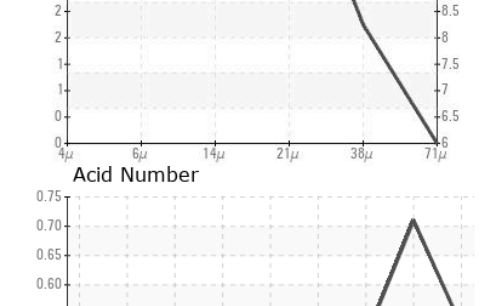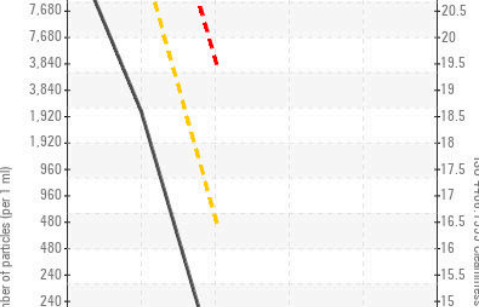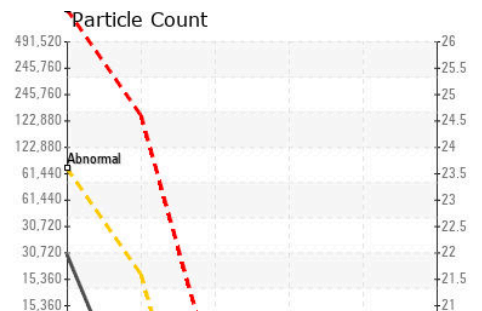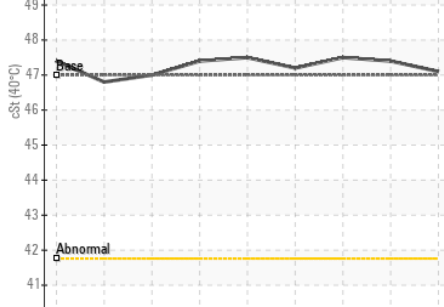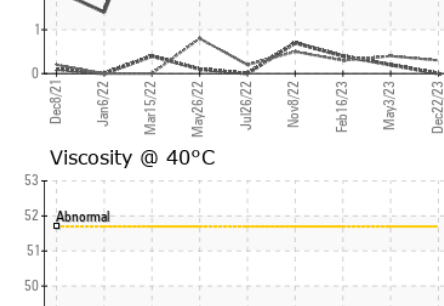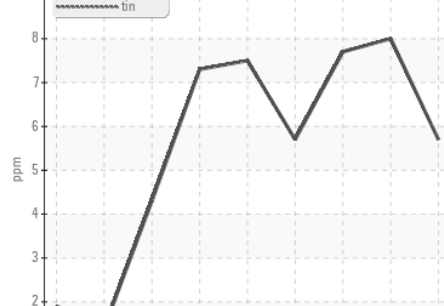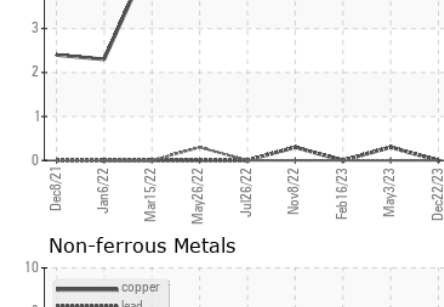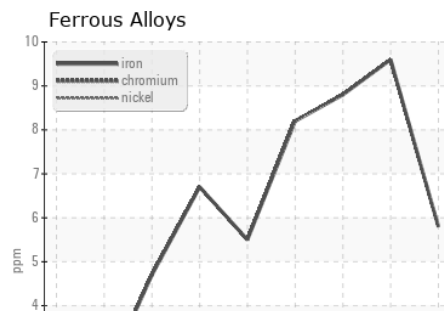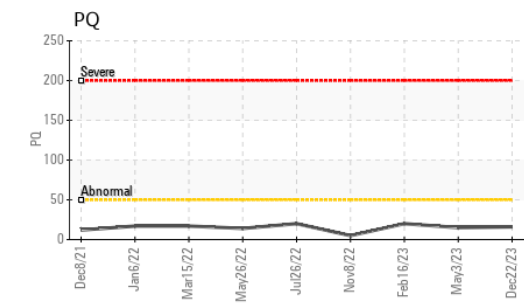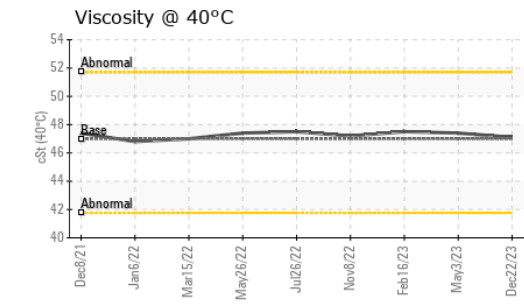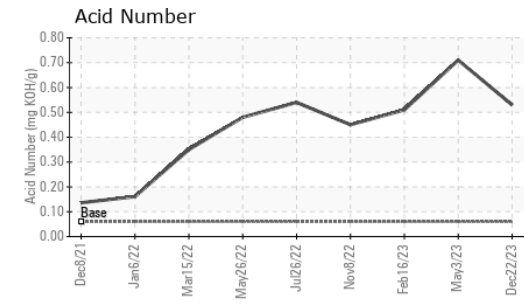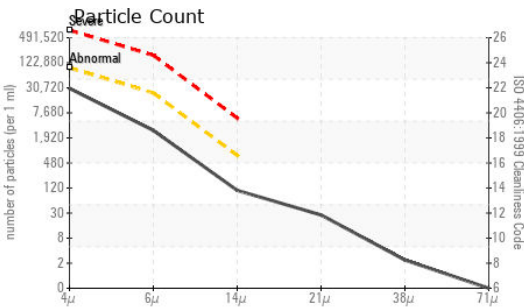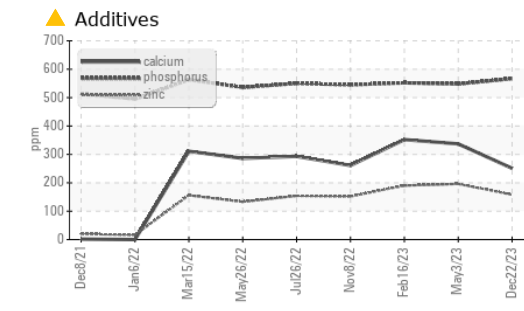

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0192809 **Received** : 10 Jan 2024
Lab Number : 06056587 **Diagnosed** : 11 Jan 2024
Unique Number : 10822536 **Diagnostician** : Don Baldrige
Test Package : CONST (Additional Tests: PQ)

B & S SITE DEVELOPMENT
 7800 PINEY BRANCH LANE
 BRISTOW, VA
 US 20136
 Contact: DANNY HUFF
 dhuff@bandssite.com
 T: (540)270-3203
 F: (703)753-0605

Certificate L2367
 To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)