



OIL ANALYSIS REPORT

WEAR
CONTAMINATION
FLUID CONDITION

ATTENTION
ABNORMAL
NORMAL



Area
Store 4 - Fairmont
Machine Id
JOHN DEERE 850K 1T0850KXCDE246953
Component
Left Outer Final Drive
Fluid
JOHN DEERE HY-GARD HYD/TRANS (4 GAL)

RECOMMENDATION

We advise that you check all areas where dirt can enter the system.
We recommend an early resample to monitor this condition.

WEAR

All component wear rates are normal.

CONTAMINATION

Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress.

FLUID CONDITION









The condition of the oil is acceptable for the time in service.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LEC0046078	LEC0014537	LECP141559
Sample Date		Client Info		05 Jan 2024	06 Aug 2020	17 Sep 2014
Machine Age	hrs	Client Info		7289	5933	532
Oil Age	hrs	Client Info		6789	1000	532
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		Not Chngd	Changed	Changed
Filter Changed		Client Info		None	N/A	N/A
Sample Status				ABNORMAL	SEVERE	NORMAL

PQ		ASTM D8184	>1250	542	254	69.0
Iron	ppm	ASTM D5185m	>750	1054	▲ 2516	83
Chromium	ppm	ASTM D5185m	>9	8	▲ 26	4
Nickel	ppm	ASTM D5185m	>10	10	12	0
Titanium	ppm	ASTM D5185m		5	17	0
Silver	ppm	ASTM D5185m		0	0	<1
Aluminum	ppm	ASTM D5185m	>40	▲ 64	▲ 232	5
Lead	ppm	ASTM D5185m	>15	<1	4	4
Copper	ppm	ASTM D5185m	>40	2	5	<1
Tin	ppm	ASTM D5185m	>10	0	0	0
Vanadium	ppm	ASTM D5185m		0	0	<1
White Metal	scalar	*Visual	NONE	NONE	NONE	MODER
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

Silicon	ppm	ASTM D5185m	>75	▲ 283	● 1057	15
Potassium	ppm	ASTM D5185m	>20	17	63	2
Water		WC Method	>0.075	NEG	NEG	NEG
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.075	NEG	NEG	NEG

Sodium	ppm	ASTM D5185m	>51	4	15	1
Boron	ppm	ASTM D5185m	6	12	10	1
Barium	ppm	ASTM D5185m	0	0	1	0
Molybdenum	ppm	ASTM D5185m	0	9	0	1
Manganese	ppm	ASTM D5185m		8	25	1
Magnesium	ppm	ASTM D5185m	145	121	101	114
Calcium	ppm	ASTM D5185m	3570	3002	3370	3758
Phosphorus	ppm	ASTM D5185m	1290	918	1002	1059
Zinc	ppm	ASTM D5185m	1640	1102	1041	1372
Sulfur	ppm	ASTM D5185m		3054	5015	0
Visc @ 40°C	cSt	ASTM D445	57.0	56.4	56.2	56.93

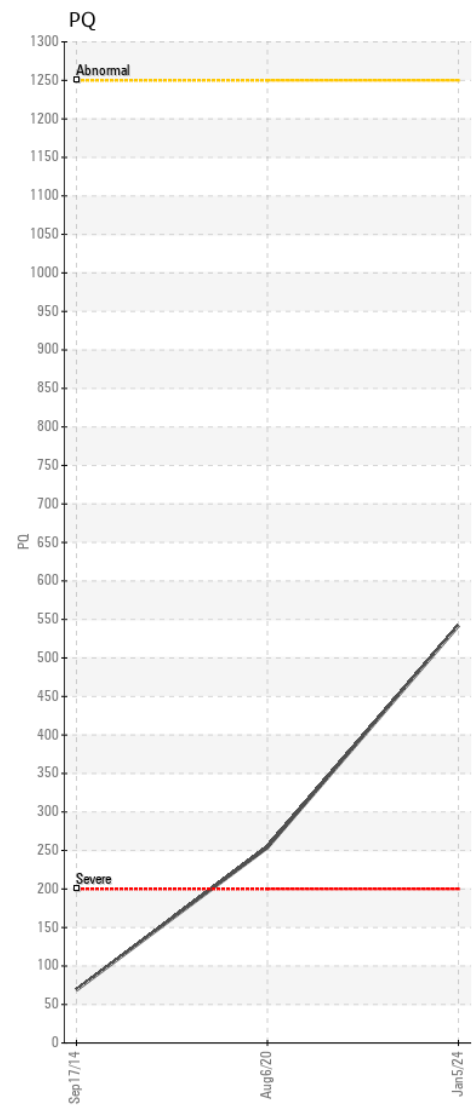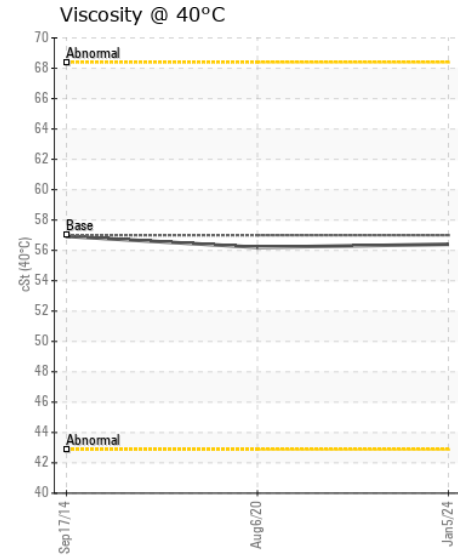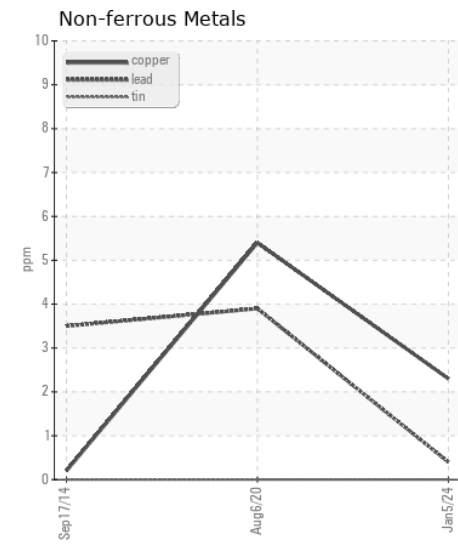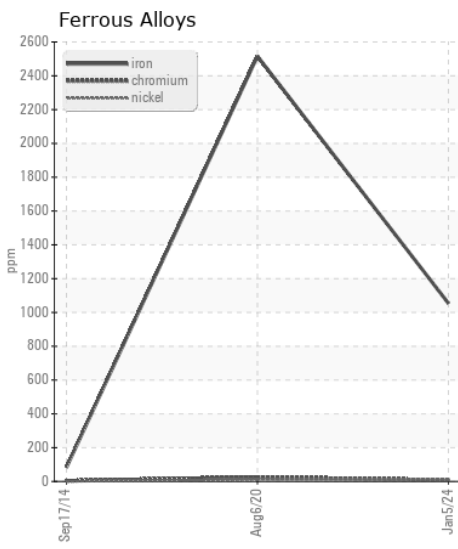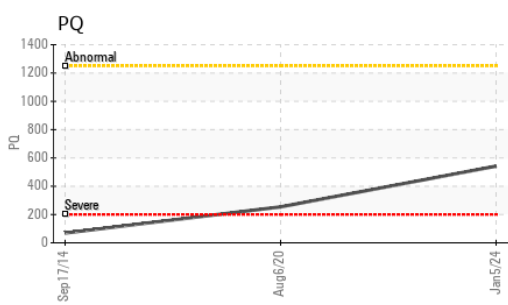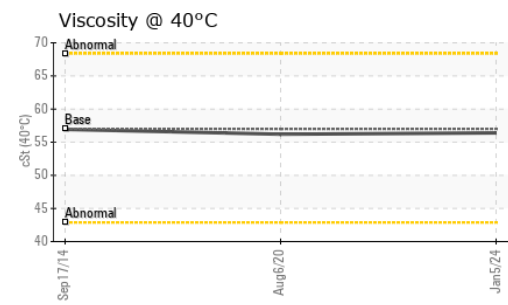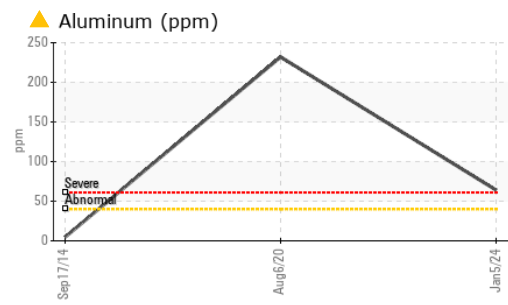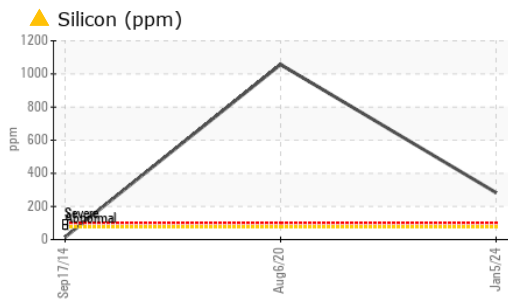

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : LEC0046078 **Received** : 10 Jan 2024
Lab Number : 06056900 **Diagnosed** : 11 Jan 2024
Unique Number : 10822849 **Diagnostician** : Sean Felton
Test Package : CONST (Additional Tests: PQ)

LESLIE EQUIPMENT COMPANY
 105 TENNIS CENTER DR.
 MARIETTA, OH
 US 45750-9765
 Contact: LEANNE KENDALL
 KendalLeanne@lec1.com
 T:
 F: (740)373-5570

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)