



# OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	ABNORMAL

Machine Id  
**272-436**  
 Component  
**Diesel Engine**  
 Fluid  
**MOBIL DELVAC 1300 SUPER15W40 (--- QTS)**

## RECOMMENDATION

We advise that you check the fuel injection system. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		RPL0016918	---	---
Sample Date		Client Info		27 Dec 2023	---	---
Machine Age	mls	Client Info		55149	---	---
Oil Age	mls	Client Info		0	---	---
Filter Age	mls	Client Info		0	---	---
Oil Changed		Client Info		Not Changd	---	---
Filter Changed		Client Info		Not Changd	---	---
Sample Status				ABNORMAL	---	---

## WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	15	---	---
Chromium	ppm	ASTM D5185m	>20	0	---	---
Nickel	ppm	ASTM D5185m	>4	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m	>3	0	---	---
Aluminum	ppm	ASTM D5185m	>20	11	---	---
Lead	ppm	ASTM D5185m	>40	<1	---	---
Copper	ppm	ASTM D5185m	>330	13	---	---
Tin	ppm	ASTM D5185m	>15	0	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

## CONTAMINATION








There is a moderate amount of fuel present in the oil.

Silicon	ppm	ASTM D5185m	>25	4	---	---
Potassium	ppm	ASTM D5185m	>20	23	---	---
Fuel	%	ASTM D3524	>5	▲ 5.1	---	---
Water		WC Method	>0.2	NEG	---	---
Glycol		WC Method		NEG	---	---
Soot %	%	*ASTM D7844	>3	0.2	---	---
Nitration	Abs/cm	*ASTM D7624	>20	7.9	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	24.6	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---	---

## FLUID CONDITION

Fuel is present in the oil and is lowering the viscosity. The BN result indicates that there is suitable alkalinity remaining in the oil.

Sodium	ppm	ASTM D5185m		<1	---	---
Boron	ppm	ASTM D5185m	0	2	---	---
Barium	ppm	ASTM D5185m	0	0	---	---
Molybdenum	ppm	ASTM D5185m	0	53	---	---
Manganese	ppm	ASTM D5185m		0	---	---
Magnesium	ppm	ASTM D5185m	0	856	---	---
Calcium	ppm	ASTM D5185m		976	---	---
Phosphorus	ppm	ASTM D5185m		875	---	---
Zinc	ppm	ASTM D5185m		1186	---	---
Sulfur	ppm	ASTM D5185m		2829	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	25.7	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	9.4	6.4	---	---
Visc @ 100°C	cSt	ASTM D445	14	▲ 11.0	---	---

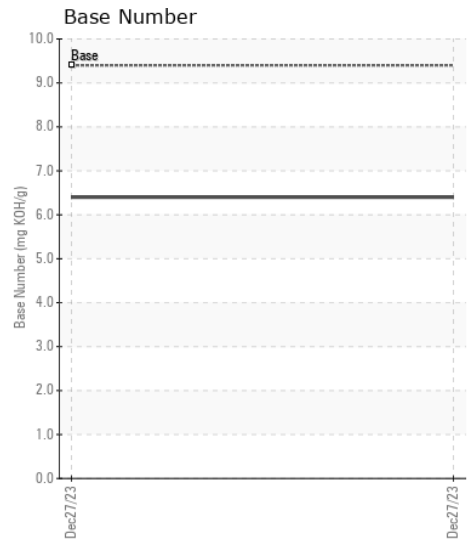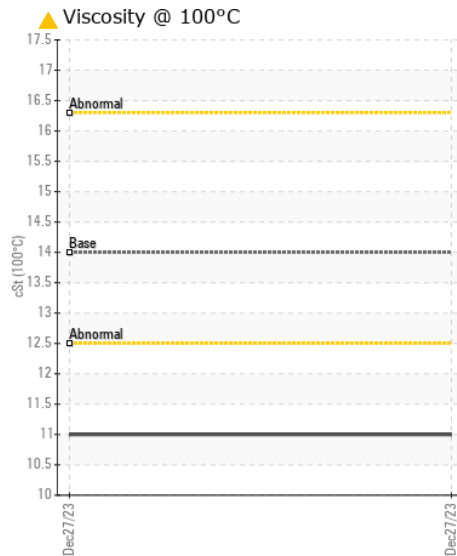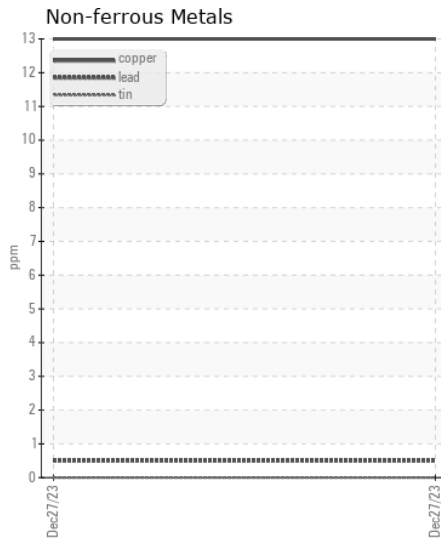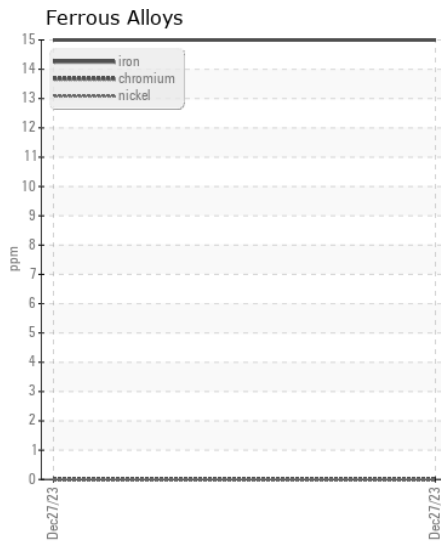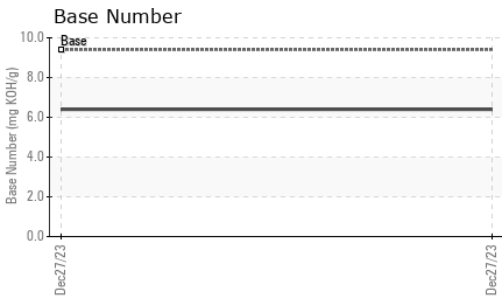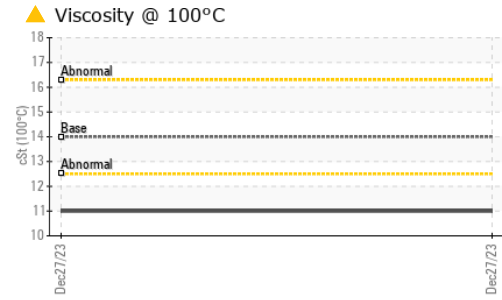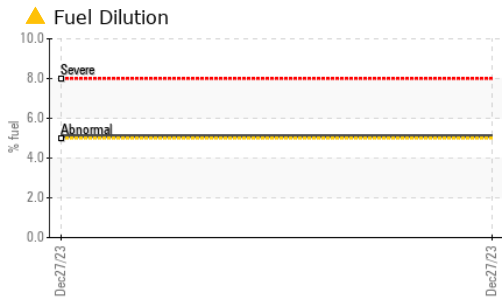

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : RPL0016918 **Received** : 11 Jan 2024  
**Lab Number** : 06057819 **Diagnosed** : 15 Jan 2024  
**Unique Number** : 10829201 **Diagnostician** : Jonathan Hester  
**Test Package** : FLEET ( Additional Tests: FuelDilution, PercentFuel )

**RTL PACLEASE - 7007 - Fontana**  
 3121 South Riverside  
 Bloomington, CA  
 US 92316  
 Contact: Rudy Trevizo  
 TrevizoR@RushEnterprises.Com  
 T: (909)829-1044  
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)