



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
HITACHI 470LC HCMJAG60J00061713

Component
Diesel Engine

Fluid
DIESEL ENGINE OIL SAE 40 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0192896	JR0179076	JR0161939
Sample Date		Client Info		04 Jan 2024	28 Jul 2023	02 May 2023
Machine Age	hrs	Client Info		6892	1474	6892
Oil Age	hrs	Client Info		0	1474	500
Filter Age	hrs	Client Info		0	1474	500
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	0	18	17
Chromium	ppm	ASTM D5185m	>20	0	<1	<1
Nickel	ppm	ASTM D5185m	>4	2	0	0
Titanium	ppm	ASTM D5185m		0	0	0
Silver	ppm	ASTM D5185m	>3	<1	0	0
Aluminum	ppm	ASTM D5185m	>20	2	3	3
Lead	ppm	ASTM D5185m	>40	<1	0	0
Copper	ppm	ASTM D5185m	>330	2	2	6
Tin	ppm	ASTM D5185m	>15	0	<1	<1
Vanadium	ppm	ASTM D5185m		<1	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION







There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>25	3	9	8
Potassium	ppm	ASTM D5185m	>20	0	0	2
Fuel		WC Method	>5	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.1	0.3	0.2
Nitration	Abs/cm	*ASTM D7624	>20	5.5	8.4	7.5
Sulfation	Abs/.1mm	*ASTM D7415	>30	18.7	21.4	18.8
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>216	0	2	9
Boron	ppm	ASTM D5185m	250	8	204	199
Barium	ppm	ASTM D5185m	10	0	0	0
Molybdenum	ppm	ASTM D5185m	100	69	228	186
Manganese	ppm	ASTM D5185m		<1	1	3
Magnesium	ppm	ASTM D5185m	450	1030	845	693
Calcium	ppm	ASTM D5185m	3000	1071	1699	1594
Phosphorus	ppm	ASTM D5185m	1150	1052	1003	951
Zinc	ppm	ASTM D5185m	1350	1354	1197	1189
Sulfur	ppm	ASTM D5185m	4250	3376	3856	3753
Oxidation	Abs/.1mm	*ASTM D7414	>25	14.1	15.7	14.2
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	10.0	8.5	7.4
Visc @ 100°C	cSt	ASTM D445	14.4	13.0	13.2	13.1

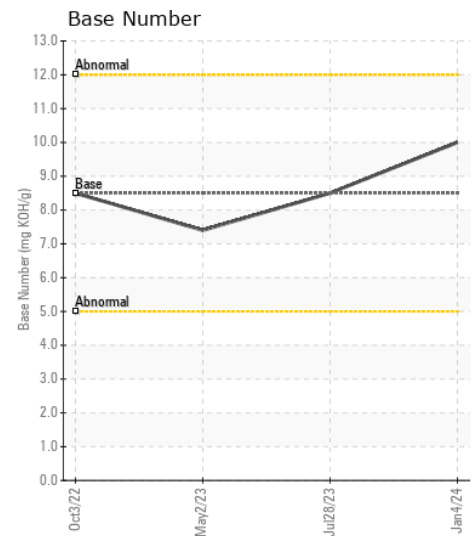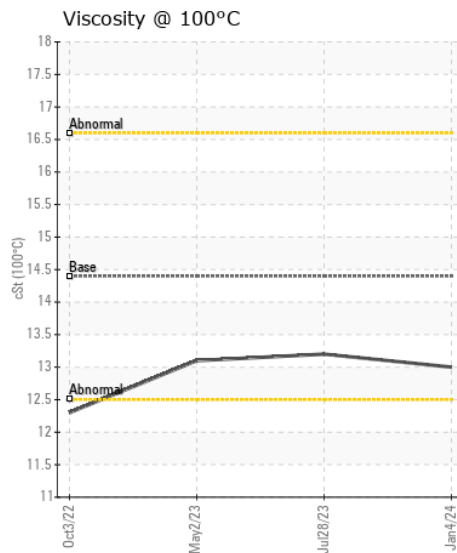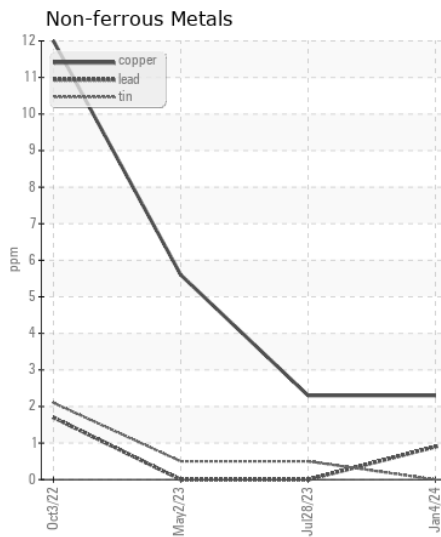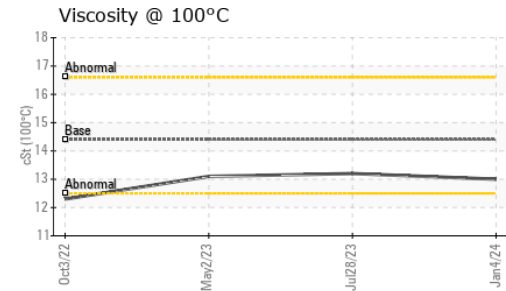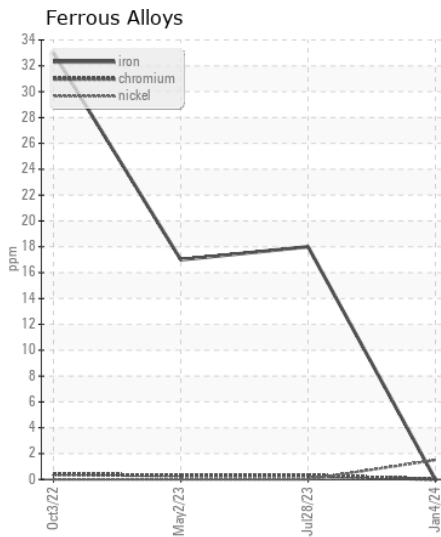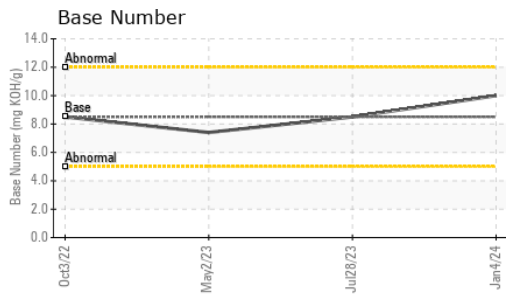

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0192896 **Received** : 12 Jan 2024
Lab Number : 06059114 **Diagnosed** : 12 Jan 2024
Unique Number : 10830496 **Diagnostician** : Wes Davis
Test Package : CONST (Additional Tests: TBN)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - CHARLOTTE
 9550 STATESVILLE ROAD
 CHARLOTTE, NC
 US 28269
 Contact: CHARLOTTE SHOP
 myoung@jamesriverequipment.com
 T: (704)597-0211
 F: (704)596-6198