



WEAR	<b>NORMAL</b>
CONTAMINATION	<b>ABNORMAL</b>
FLUID CONDITION	<b>NORMAL</b>

Area

**[W10828]**

Machine Id

**JOHN DEERE 333G 1T0333GMVNF427183**

Component

**Hydraulic System**

Fluid

**{not provided} (--- GAL)**

### RECOMMENDATION

The filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		<b>JR0125897</b>	JR0125866	---
Sample Date		Client Info		<b>09 Jan 2024</b>	02 Feb 2023	---
Machine Age	hrs	Client Info		<b>1307</b>	438	---
Oil Age	hrs	Client Info		<b>1307</b>	0	---
Filter Age	hrs	Client Info		<b>1307</b>	0	---
Oil Changed		Client Info		<b>Changed</b>	N/A	---
Filter Changed		Client Info		<b>Changed</b>	N/A	---
Sample Status				<b>ABNORMAL</b>	ATTENTION	---

### WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	<b>18</b>	10	---
Chromium	ppm	ASTM D5185m	>10	<b>&lt;1</b>	<1	---
Nickel	ppm	ASTM D5185m	>10	<b>0</b>	0	---
Titanium	ppm	ASTM D5185m		<b>0</b>	0	---
Silver	ppm	ASTM D5185m		<b>0</b>	<1	---
Aluminum	ppm	ASTM D5185m	>10	<b>2</b>	<1	---
Lead	ppm	ASTM D5185m	>10	<b>&lt;1</b>	1	---
Copper	ppm	ASTM D5185m	>75	<b>11</b>	8	---
Tin	ppm	ASTM D5185m	>10	<b>0</b>	<1	---
Vanadium	ppm	ASTM D5185m		<b>0</b>	0	---
White Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	---
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	---

### CONTAMINATION











There is a moderate amount of silt (particulates < 14 microns in size) present in the oil.

Silicon	ppm	ASTM D5185m	>20	<b>2</b>	1	---
Potassium	ppm	ASTM D5185m	>20	<b>1</b>	1	---
Water		WC Method	>0.1	<b>NEG</b>	NEG	---
Particles >4µm		ASTM D7647	>5000	<b>▲ 15174</b>	▲ 7089	---
Particles >6µm		ASTM D7647	>1300	<b>864</b>	821	---
Particles >14µm		ASTM D7647	>160	<b>57</b>	121	---
Particles >21µm		ASTM D7647	>40	<b>13</b>	36	---
Particles >38µm		ASTM D7647	>10	<b>0</b>	1	---
Particles >71µm		ASTM D7647	>3	<b>0</b>	0	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	<b>▲ 21/17/13</b>	▲ 20/17/14	---
Silt	scalar	*Visual	NONE	<b>NONE</b>	NONE	---
Debris	scalar	*Visual	NONE	<b>NONE</b>	NONE	---
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	NONE	---
Appearance	scalar	*Visual	NORML	<b>NORML</b>	NORML	---
Odor	scalar	*Visual	NORML	<b>NORML</b>	NORML	---
Emulsified Water	scalar	*Visual	>0.1	<b>NEG</b>	NEG	---

### FLUID CONDITION

The AN level is acceptable for this fluid. The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

Sodium	ppm	ASTM D5185m		<b>0</b>	2	---
Boron	ppm	ASTM D5185m		<b>2</b>	2	---
Barium	ppm	ASTM D5185m		<b>3</b>	0	---
Molybdenum	ppm	ASTM D5185m		<b>3</b>	4	---
Manganese	ppm	ASTM D5185m		<b>&lt;1</b>	<1	---
Magnesium	ppm	ASTM D5185m		<b>4</b>	5	---
Calcium	ppm	ASTM D5185m		<b>225</b>	249	---
Phosphorus	ppm	ASTM D5185m		<b>714</b>	598	---
Zinc	ppm	ASTM D5185m		<b>859</b>	789	---
Sulfur	ppm	ASTM D5185m		<b>2235</b>	2282	---
Acid Number (AN)	mg KOH/g	ASTM D8045		<b>0.71</b>	0.71	---
Visc @ 40°C	cSt	ASTM D445		<b>51.5</b>	52.9	---

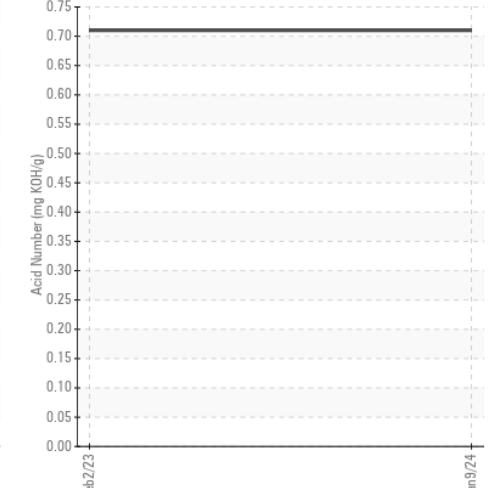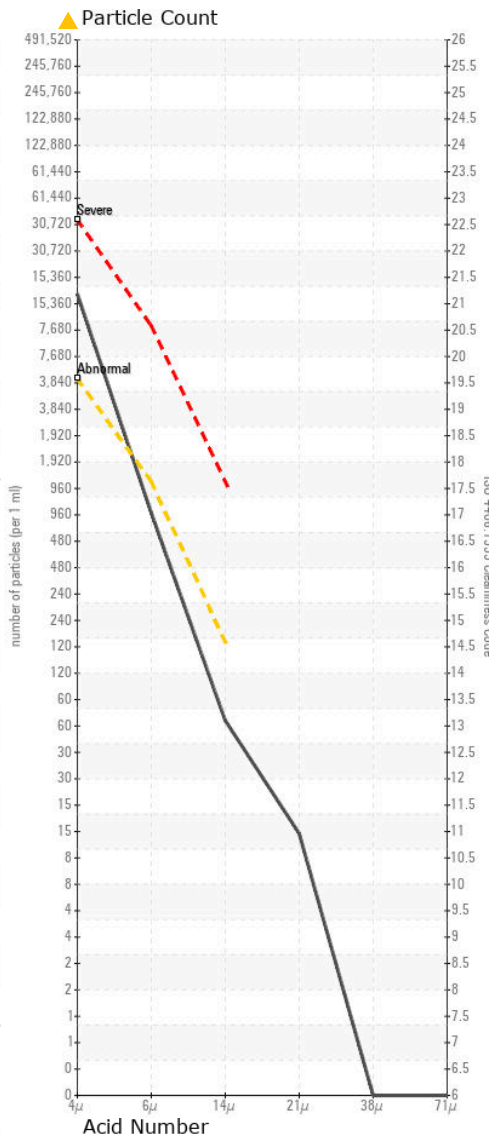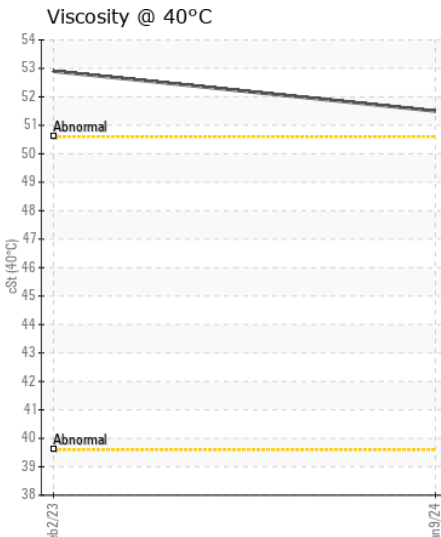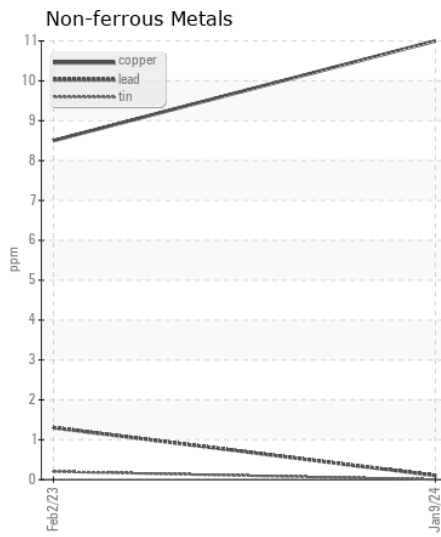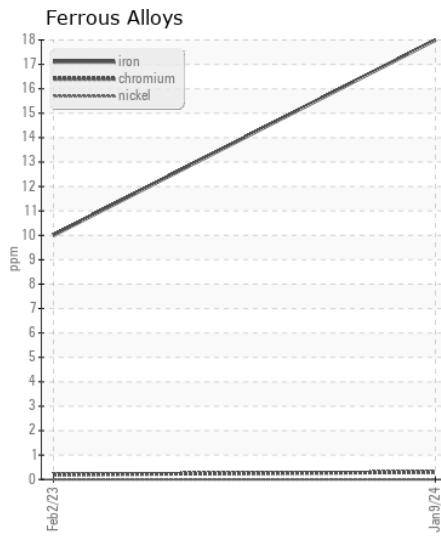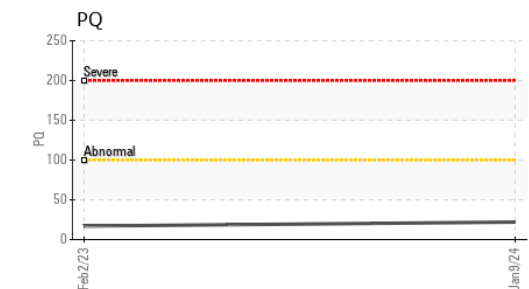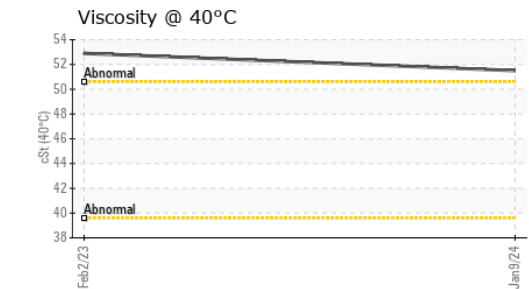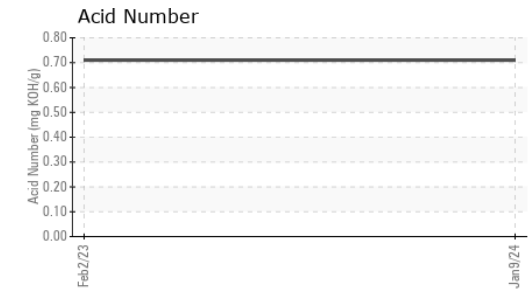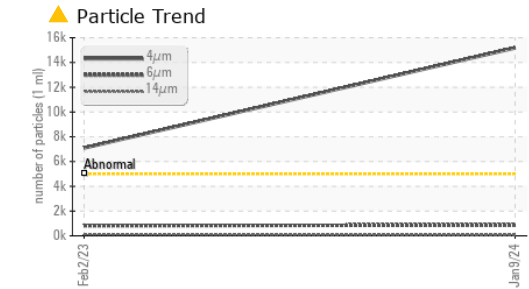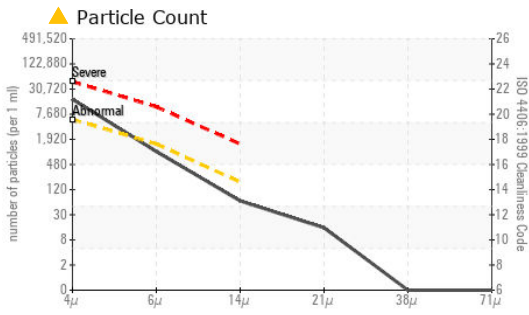

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : JR0125897 **Received** : 17 Jan 2024  
**Lab Number** : 06063490 **Diagnosed** : 19 Jan 2024  
**Unique Number** : 10834872 **Diagnostician** : Wes Davis  
**Test Package** : MOBCE ( Additional Tests: PQ )

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

**JRE - SALEM**  
 3902 W. MAIN STREET  
 SALEM, VA  
 US 24153  
 Contact: BUTCH GOAD  
 bgoad@jrenet.com  
 T:  
 F: (540)380-5547