



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Area
[W32420-1]
 Machine Id
NOT GIVEN JR0194292 (S/N NO INFO ON SIF/BOTTLE)

Component
Hydraulic System
 Fluid
JOHN DEERE HYDRAU (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0194292	---	---
Sample Date		Client Info		12 Jan 2024	---	---
Machine Age	hrs	Client Info		74	---	---
Oil Age	hrs	Client Info		74	---	---
Filter Age	hrs	Client Info		74	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
		ASTM D8184		14	---	---
Iron	ppm	ASTM D5185m	>20	2	---	---
Chromium	ppm	ASTM D5185m	>10	0	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	0	---	---
Lead	ppm	ASTM D5185m	>10	3	---	---
Copper	ppm	ASTM D5185m	>75	27	---	---
Tin	ppm	ASTM D5185m	>10	<1	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION










The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>20	1	---	---
Potassium	ppm	ASTM D5185m	>20	2	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	2395	---	---
Particles >6µm		ASTM D7647	>1300	268	---	---
Particles >14µm		ASTM D7647	>160	12	---	---
Particles >21µm		ASTM D7647	>40	2	---	---
Particles >38µm		ASTM D7647	>10	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	18/15/11	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		<1	---	---
Boron	ppm	ASTM D5185m		0	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		0	---	---
Manganese	ppm	ASTM D5185m		<1	---	---
Magnesium	ppm	ASTM D5185m		1	---	---
Calcium	ppm	ASTM D5185m	87	80	---	---
Phosphorus	ppm	ASTM D5185m	727	653	---	---
Zinc	ppm	ASTM D5185m	900	826	---	---
Sulfur	ppm	ASTM D5185m	1500	1766	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.69	---	---
Visc @ 40°C	cSt	ASTM D445	65	57.5	---	---

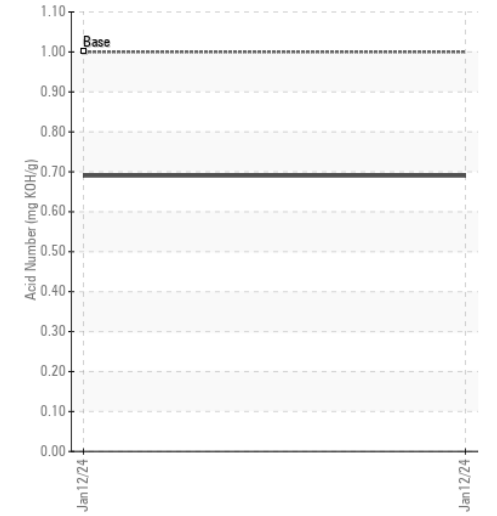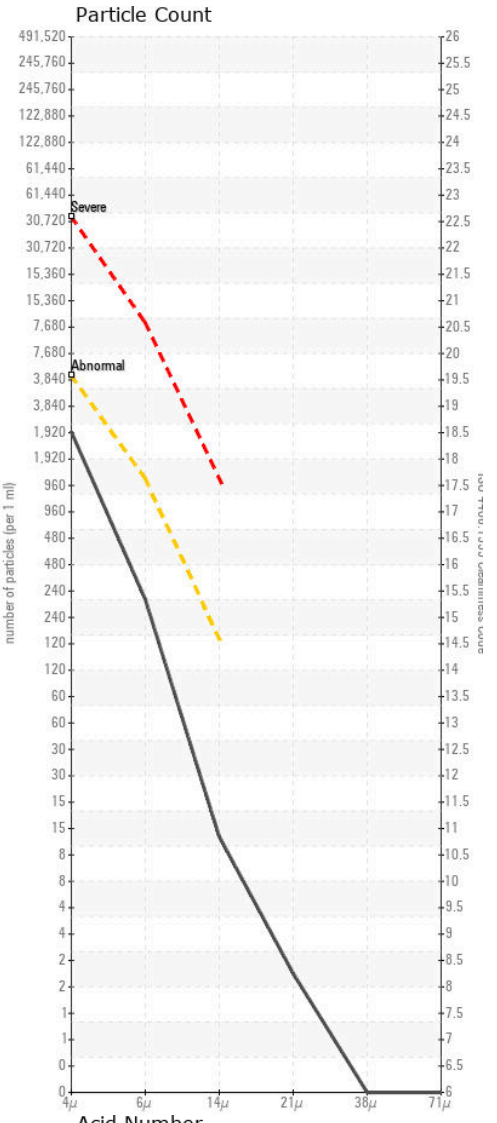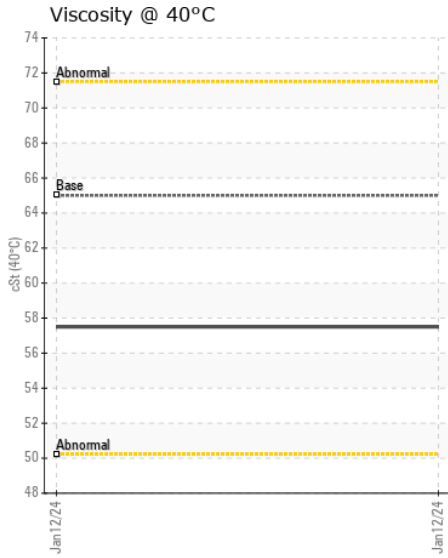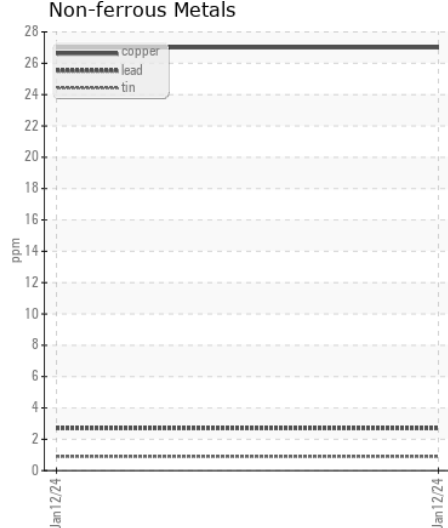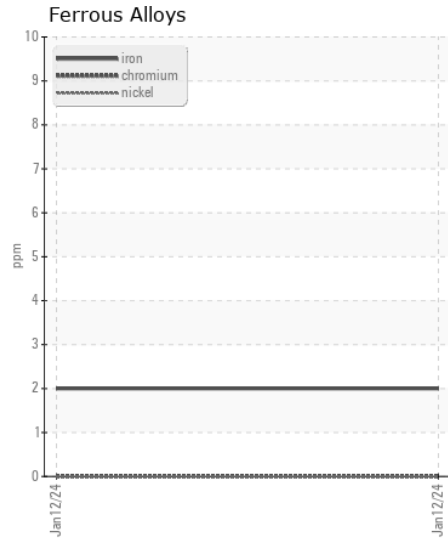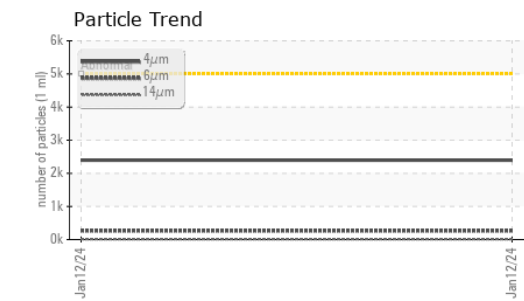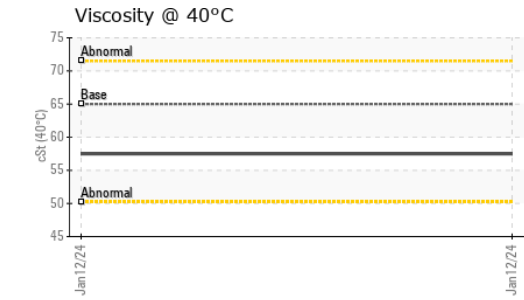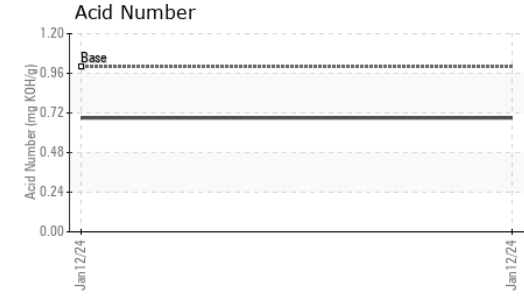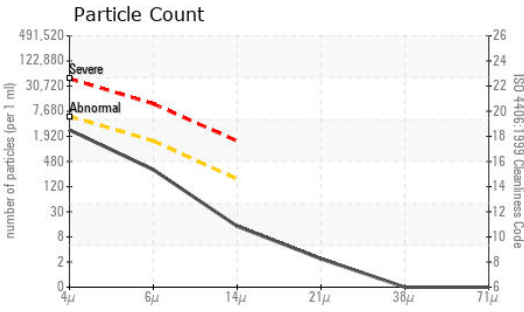

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0194292 **Received** : 18 Jan 2024
Lab Number : 06064195 **Diagnosed** : 19 Jan 2024
Unique Number : 10835577 **Diagnostician** : Wes Davis
Test Package : CONST (Additional Tests: PQ)

JRE - GREENSBORO
 411 SOUTH REGIONAL ROAD
 GREENSBORO, NC
 US 27409
 Contact: NICK GALLAHER
 NGALLAHER@JRENET.COM
 T: (336)668-2762
 F: (336)665-9556

Certificate L2367
 To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)