



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
GREENERD 1530
Component
Hydraulic System
Fluid
MOBIL DTE 25 (250 GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		ST44431	ST42701	ST40909
Sample Date		Client Info		19 Jan 2024	20 Jan 2022	12 Jan 2021
Machine Age	hrs	Client Info		0	0	0
Oil Age	hrs	Client Info		0	0	0
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		N/A	N/A	N/A
Filter Changed		Client Info		N/A	N/A	N/A
Sample Status				NORMAL	NORMAL	MARGINAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>20	2	4	4
Chromium	ppm	ASTM D5185m	>20	<1	0	0
Nickel	ppm	ASTM D5185m	>20	0	0	0
Titanium	ppm	ASTM D5185m		<1	0	0
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m	>20	<1	<1	<1
Lead	ppm	ASTM D5185m	>20	3	2	2
Copper	ppm	ASTM D5185m	>20	40	44	▲ 44
Tin	ppm	ASTM D5185m	>20	1	<1	<1
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION











There is no indication of any contamination in the oil. The amount and size of particulates present in the system are acceptable.

Silicon	ppm	ASTM D5185m	>15	3	4	3
Potassium	ppm	ASTM D5185m	>20	1	0	<1
Water	%	ASTM D6304	>0.05	0.007	0.007	0.011
ppm Water	ppm	ASTM D6304	>500	75	72.2	111.6
Particles >4µm		ASTM D7647	>2500	1174	1499	607
Particles >6µm		ASTM D7647	>640	295	187	66
Particles >14µm		ASTM D7647	>80	30	19	11
Particles >21µm		ASTM D7647	>20	8	6	4
Particles >38µm		ASTM D7647	>4	0	0	0
Particles >71µm		ASTM D7647	>3	0	0	0
Oil Cleanliness		ISO 4406 (c)	>18/16/13	17/15/12	18/15/11	16/13/11
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.05	NEG	NEG	NEG

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		4	4	4
Boron	ppm	ASTM D5185m		0	2	4
Barium	ppm	ASTM D5185m		<1	0	0
Molybdenum	ppm	ASTM D5185m		0	<1	<1
Manganese	ppm	ASTM D5185m		<1	<1	<1
Magnesium	ppm	ASTM D5185m		32	35	35
Calcium	ppm	ASTM D5185m		103	152	154
Phosphorus	ppm	ASTM D5185m		520	520	522
Zinc	ppm	ASTM D5185m		662	697	686
Sulfur	ppm	ASTM D5185m		4626	4236	4412
Acid Number (AN)	mg KOH/g	ASTM D8045		0.70	0.64	0.642
Visc @ 40°C	cSt	ASTM D445	44.2	44.6	44.1	44.0

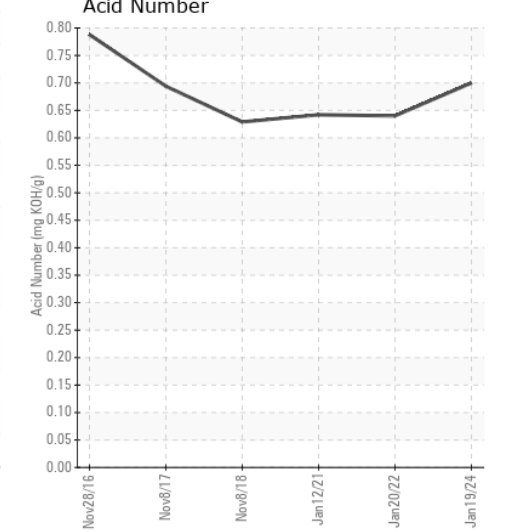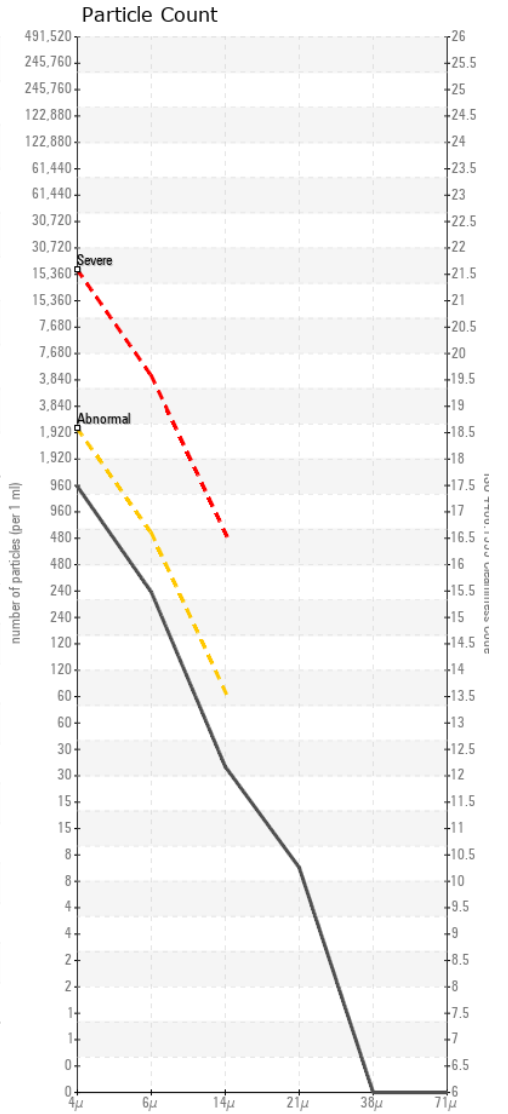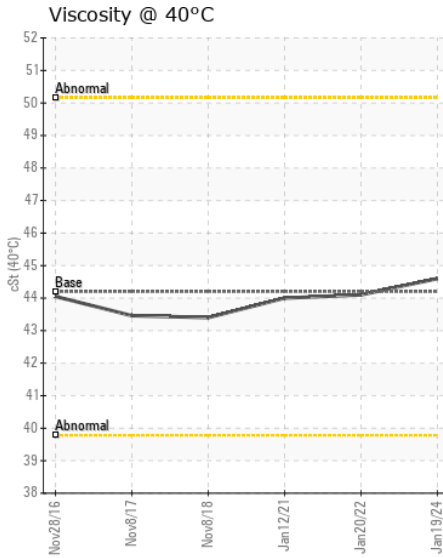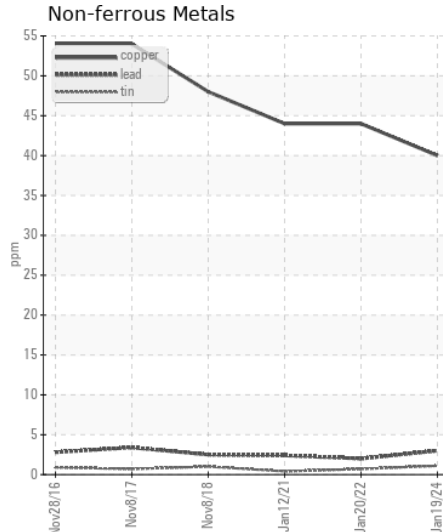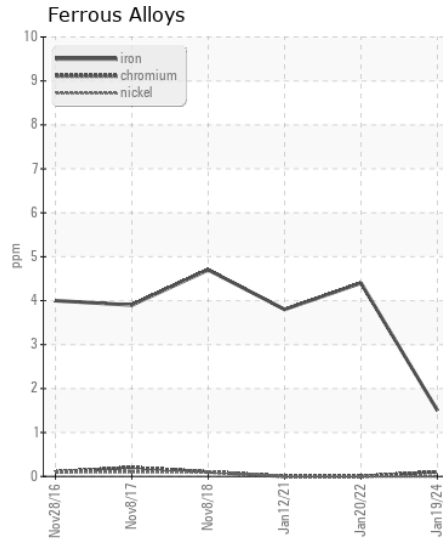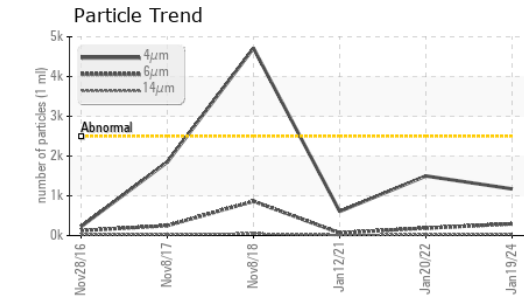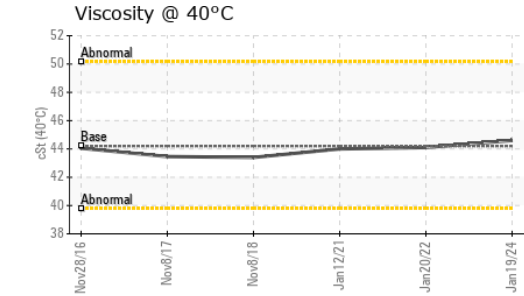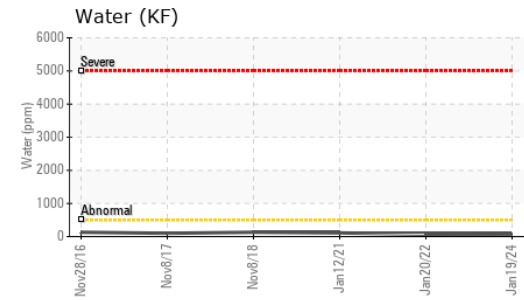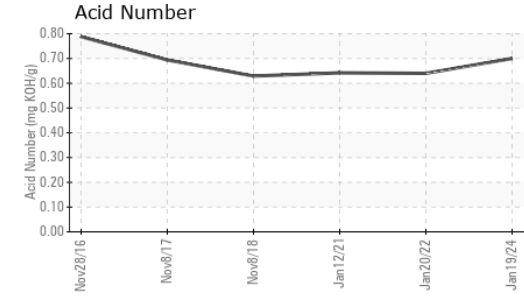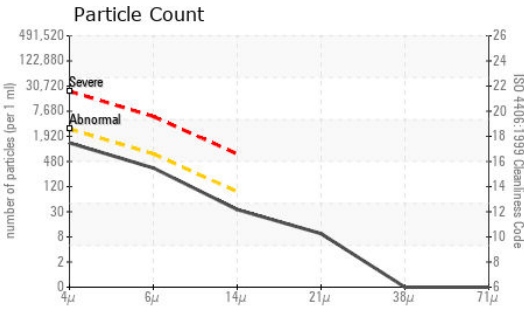

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : ST44431 **Received** : 30 Jan 2024
Lab Number : 06074783 **Diagnosed** : 01 Feb 2024
Unique Number : 10856874 **Diagnostician** : Jonathan Hester
Test Package : IND 2 (Additional Tests: KF)

LARSON TOOL & STAMPING CO
 90 OLIVE ST
 ATTLEBORO, MA
 US 02703
 Contact: GARY BRUNE
 gbrune@larsonstool.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)