



WEAR	ABNORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 1025R 58001356 (S/N 1LV1025RELM813345)

Component
Hydraulic System

Fluid
JOHN DEERE HY-GARD HYD/TRANS LOW VIS (--- GAL)

RECOMMENDATION

No corrective action is recommended at this time. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0183568	---	---
Sample Date		Client Info		19 Jan 2024	---	---
Machine Age	hrs	Client Info		100	---	---
Oil Age	hrs	Client Info		100	---	---
Filter Age	hrs	Client Info		100	---	---
Oil Changed		Client Info		Not Chngd	---	---
Filter Changed		Client Info		Not Chngd	---	---
Sample Status				ABNORMAL	---	---

WEAR

The iron level is abnormal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	▲ 24	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	4	---	---
Lead	ppm	ASTM D5185m	>10	2	---	---
Copper	ppm	ASTM D5185m	>75	35	---	---
Tin	ppm	ASTM D5185m	>10	1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	LIGHT	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION











There is a high amount of silt (particulates < 14 microns in size) present in the oil. Elemental level of silicon (Si) above normal indicating ingress of seal material.

Silicon	ppm	ASTM D5185m	>20	▲ 22	---	---
Potassium	ppm	ASTM D5185m	>20	3	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	▲ 69620	---	---
Particles >6µm		ASTM D7647	>1300	▲ 3013	---	---
Particles >14µm		ASTM D7647	>160	19	---	---
Particles >21µm		ASTM D7647	>40	3	---	---
Particles >38µm		ASTM D7647	>10	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ 23/19/11	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oils additive package is suitable for further service.

Sodium	ppm	ASTM D5185m		4	---	---
Boron	ppm	ASTM D5185m		4	---	---
Barium	ppm	ASTM D5185m		3	---	---
Molybdenum	ppm	ASTM D5185m		<1	---	---
Manganese	ppm	ASTM D5185m		2	---	---
Magnesium	ppm	ASTM D5185m		101	---	---
Calcium	ppm	ASTM D5185m		3299	---	---
Phosphorus	ppm	ASTM D5185m		972	---	---
Zinc	ppm	ASTM D5185m		1154	---	---
Sulfur	ppm	ASTM D5185m		3244	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045		1.24	---	---
Visc @ 40°C	cSt	ASTM D445	32	30.8	---	---

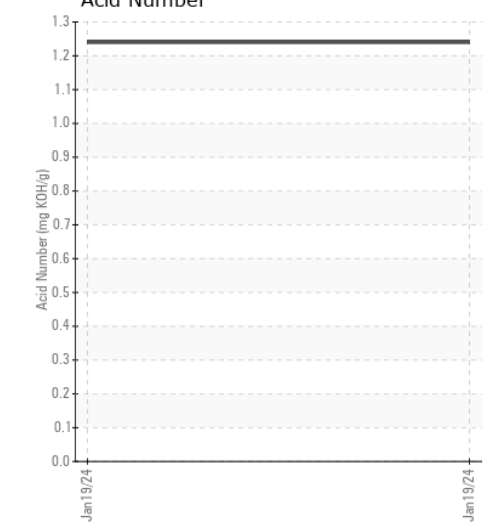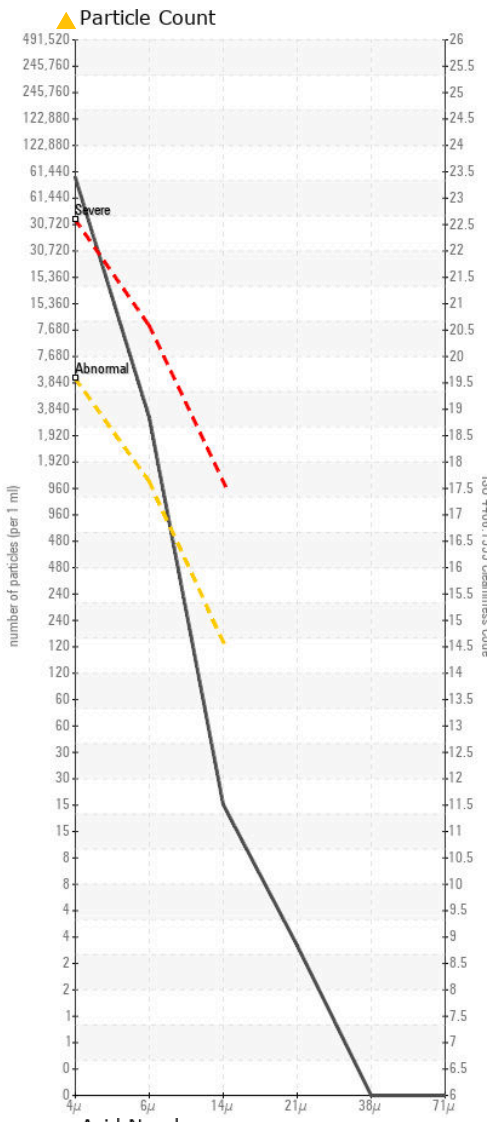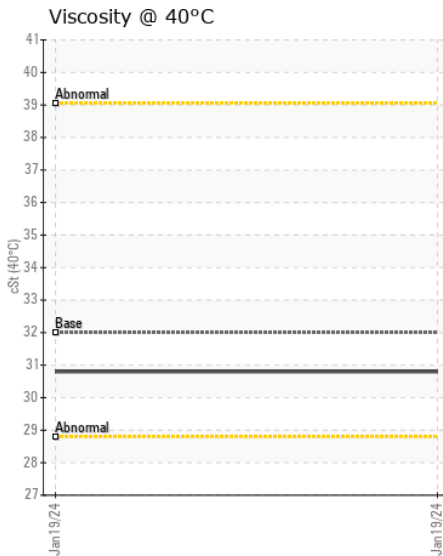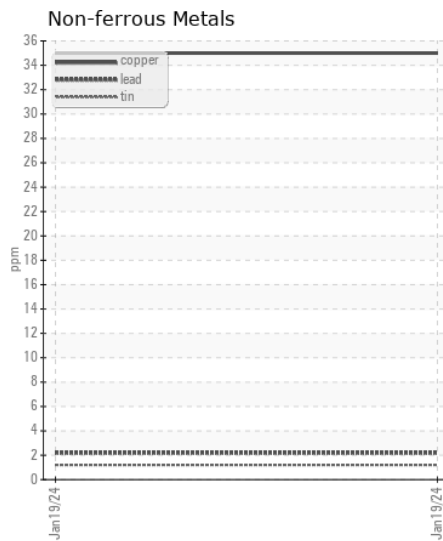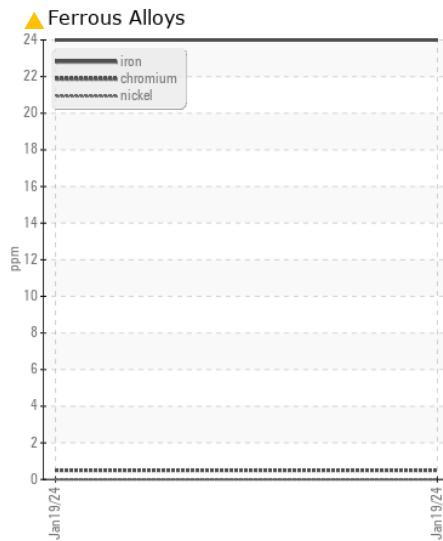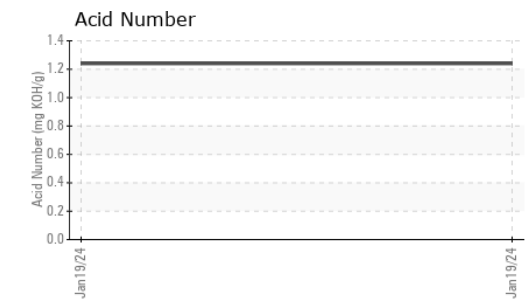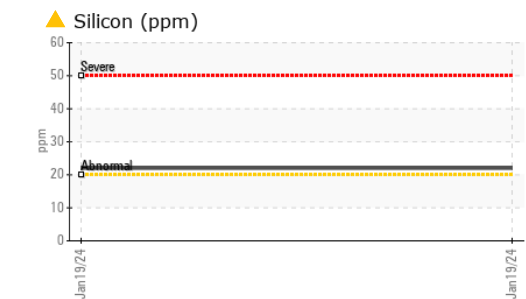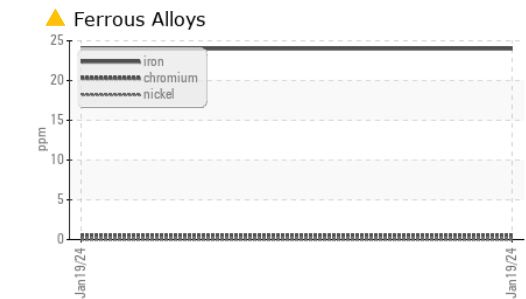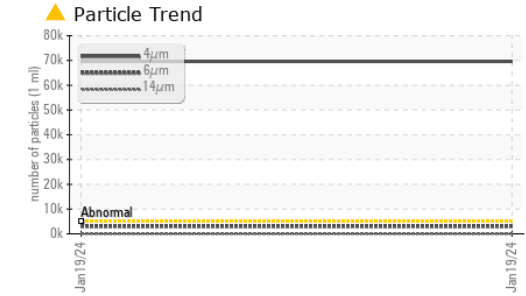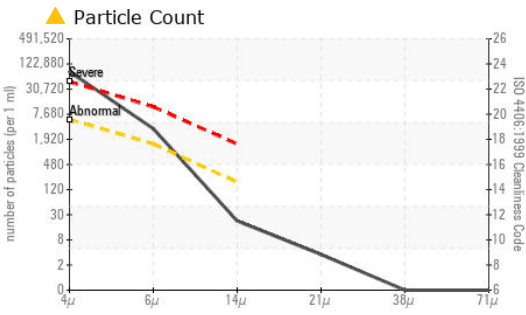

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
 Sample No. : JR0183568 Recieved : 31 Jan 2024
 Lab Number : 06075635 Diagnosed : 06 Feb 2024
 Unique Number : 10857726 Diagnostician : Jonathan Hester
 Test Package : CONST (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - HARRISONBURG
 1332 GARBERS CHURCH RD
 HARRISONBURG, VA
 US 22801
 Contact: JOSH MITCHELL
 jmitchell@jamesriverequipment.com

T: (540)434-4457

F: