



WEAR	ABNORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 3038E 58001247 (S/N 1LV3038EVL131850)

Component
Hydraulic System

Fluid
JOHN DEERE HY-GARD HYD/TRANS (--- LTR)

RECOMMENDATION

We recommend you service the filters on this component. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0183573	---	---
Sample Date		Client Info		30 Jan 2024	---	---
Machine Age	hrs	Client Info		135	---	---
Oil Age	hrs	Client Info		135	---	---
Filter Age	hrs	Client Info		135	---	---
Oil Changed		Client Info		Not Chngd	---	---
Filter Changed		Client Info		Not Chngd	---	---
Sample Status				ABNORMAL	---	---

WEAR

The iron level is abnormal. All other component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	▲ 29	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m		<1	---	---
Aluminum	ppm	ASTM D5185m	>10	4	---	---
Lead	ppm	ASTM D5185m	>10	4	---	---
Copper	ppm	ASTM D5185m	>75	28	---	---
Tin	ppm	ASTM D5185m	>10	<1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	LIGHT	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION











There is a high amount of particulates present in the oil.

Silicon	ppm	ASTM D5185m	>20	14	---	---
Potassium	ppm	ASTM D5185m	>20	3	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	▲ 187761	---	---
Particles >6µm		ASTM D7647	>1300	▲ 22584	---	---
Particles >14µm		ASTM D7647	>160	▲ 231	---	---
Particles >21µm		ASTM D7647	>40	30	---	---
Particles >38µm		ASTM D7647	>10	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ 25/22/15	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oils additive package is suitable for further service.

Sodium	ppm	ASTM D5185m		4	---	---
Boron	ppm	ASTM D5185m	6	4	---	---
Barium	ppm	ASTM D5185m	0	0	---	---
Molybdenum	ppm	ASTM D5185m	0	1	---	---
Manganese	ppm	ASTM D5185m		2	---	---
Magnesium	ppm	ASTM D5185m	145	96	---	---
Calcium	ppm	ASTM D5185m	3570	3209	---	---
Phosphorus	ppm	ASTM D5185m	1290	984	---	---
Zinc	ppm	ASTM D5185m	1640	1150	---	---
Sulfur	ppm	ASTM D5185m		3268	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.8	1.29	---	---
Visc @ 40°C	cSt	ASTM D445	57.0	34.5	---	---

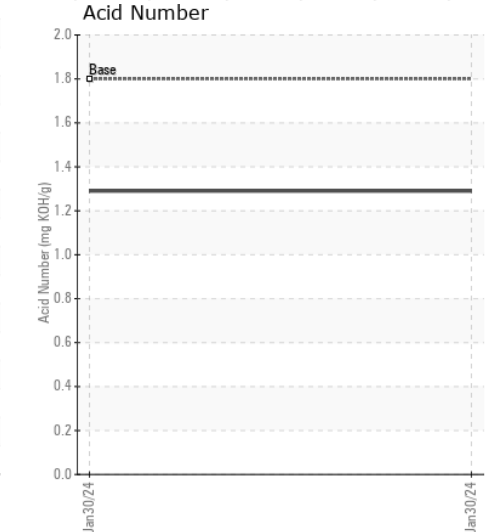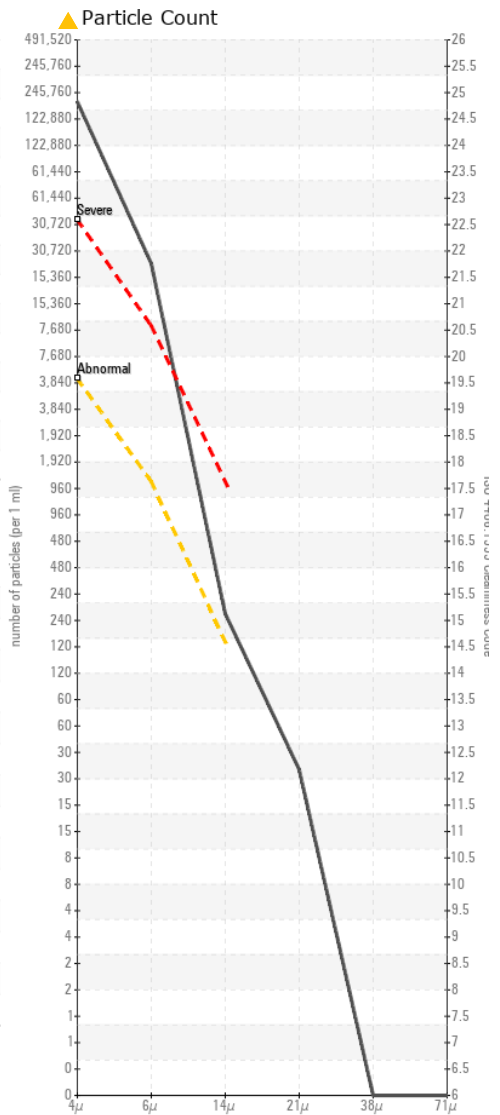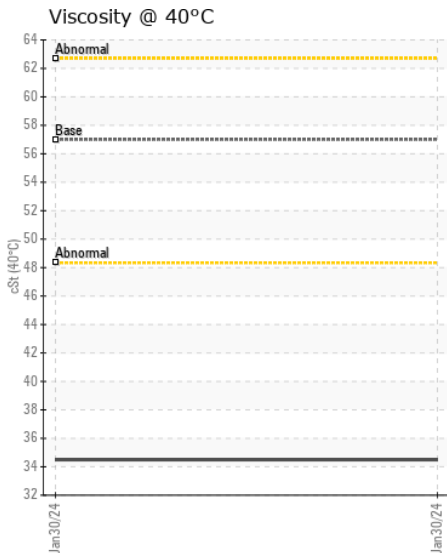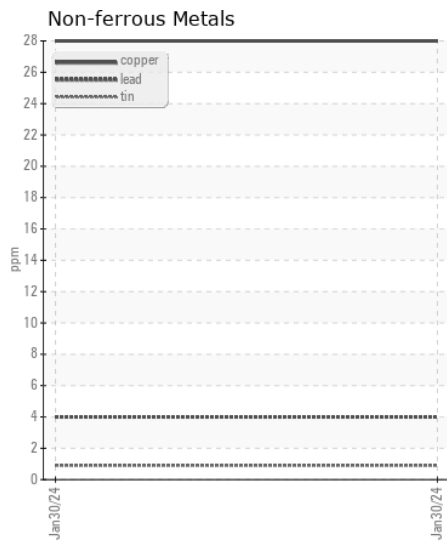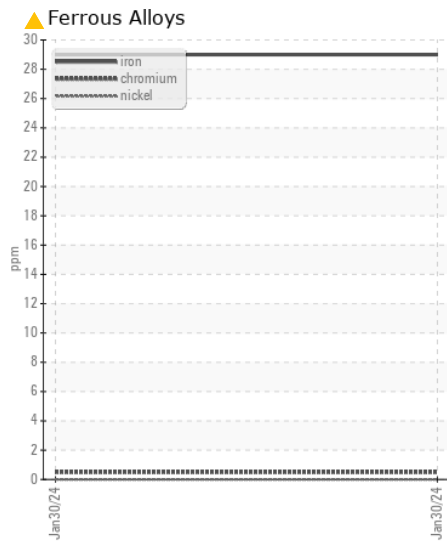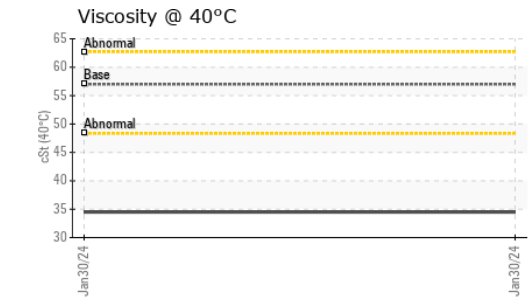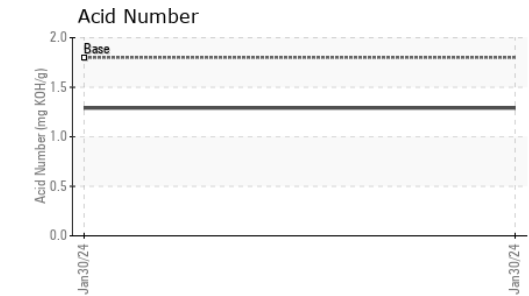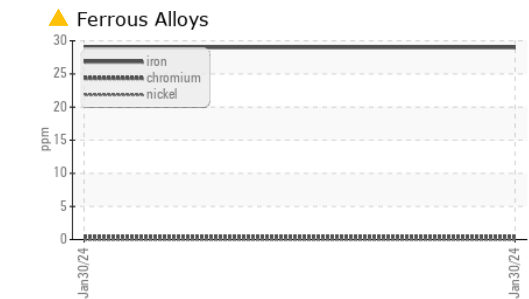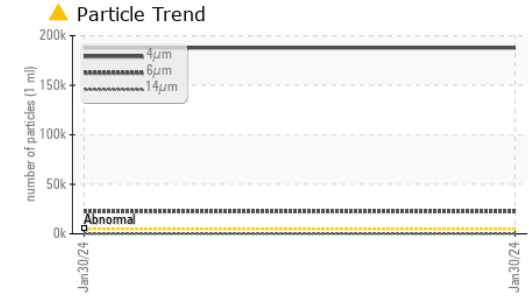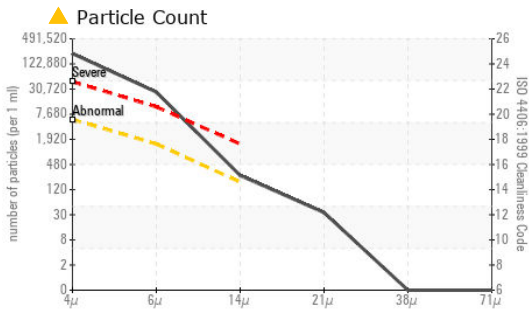

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0183573 **Received** : 31 Jan 2024
Lab Number : 06075637 **Diagnosed** : 02 Feb 2024
Unique Number : 10857728 **Diagnostician** : Jonathan Hester
Test Package : CONST (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - HARRISONBURG
 1332 GARBERS CHURCH RD
 HARRISONBURG, VA
 US 22801

Contact: ETHAN SHEETS
 ETHAN.SHEETS@JAMESRIVEREQUIPMENT.COM

T:
 F: