



WEAR	ABNORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 3034R 28005134
 Component
Hydraulic System
 Fluid
JOHN DEERE HY-GARD HYD/TRANS (--- GAL)

RECOMMENDATION

No corrective action is recommended at this time. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0183575	---	---
Sample Date		Client Info		26 Jan 2024	---	---
Machine Age	hrs	Client Info		711	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Not Chngd	---	---
Filter Changed		Client Info		Not Chngd	---	---
Sample Status				ABNORMAL	---	---

WEAR

The iron level is abnormal. All other component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	▲ 28	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m		<1	---	---
Aluminum	ppm	ASTM D5185m	>10	3	---	---
Lead	ppm	ASTM D5185m	>10	2	---	---
Copper	ppm	ASTM D5185m	>75	20	---	---
Tin	ppm	ASTM D5185m	>10	1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	LIGHT	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION











There is a high amount of silt (particulates < 6 microns in size) present in the oil.

Silicon	ppm	ASTM D5185m	>20	5	---	---
Potassium	ppm	ASTM D5185m	>20	2	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	▲ 23845	---	---
Particles >6µm		ASTM D7647	>1300	683	---	---
Particles >14µm		ASTM D7647	>160	35	---	---
Particles >21µm		ASTM D7647	>40	8	---	---
Particles >38µm		ASTM D7647	>10	1	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ 22/17/12	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oils additive package is suitable for further service.

Sodium	ppm	ASTM D5185m		3	---	---
Boron	ppm	ASTM D5185m	6	2	---	---
Barium	ppm	ASTM D5185m	0	0	---	---
Molybdenum	ppm	ASTM D5185m	0	<1	---	---
Manganese	ppm	ASTM D5185m		1	---	---
Magnesium	ppm	ASTM D5185m	145	91	---	---
Calcium	ppm	ASTM D5185m	3570	3186	---	---
Phosphorus	ppm	ASTM D5185m	1290	997	---	---
Zinc	ppm	ASTM D5185m	1640	1153	---	---
Sulfur	ppm	ASTM D5185m		3282	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.8	1.27	---	---
Visc @ 40°C	cSt	ASTM D445	57.0	30.7	---	---

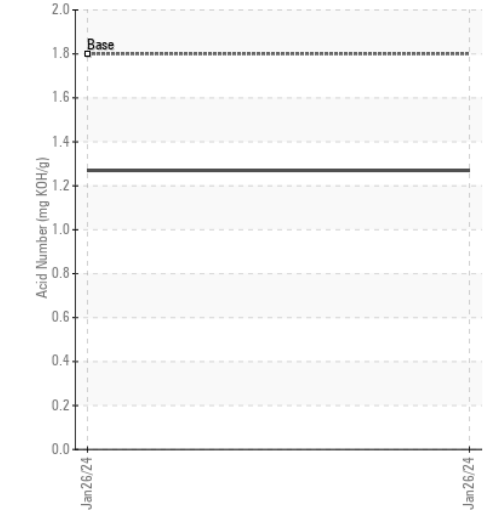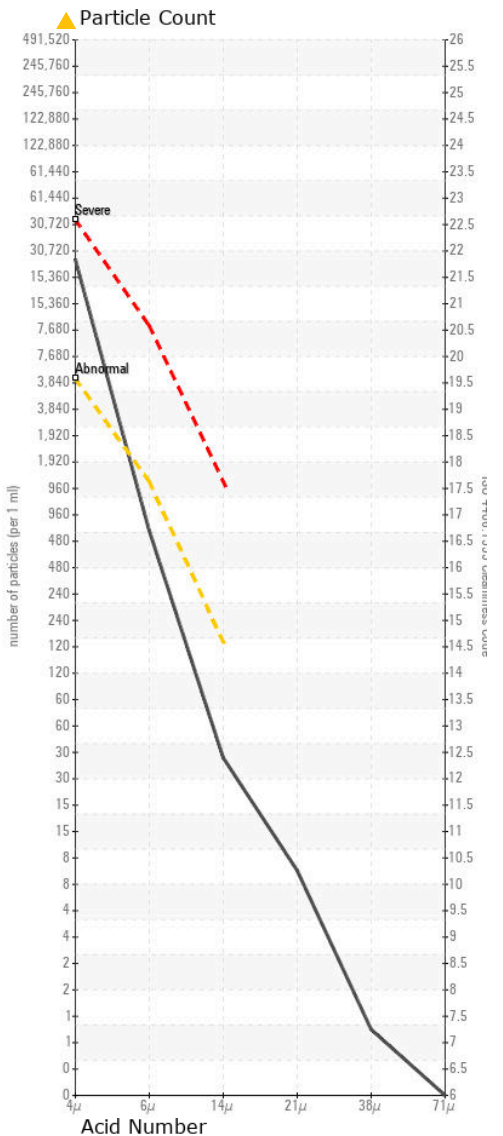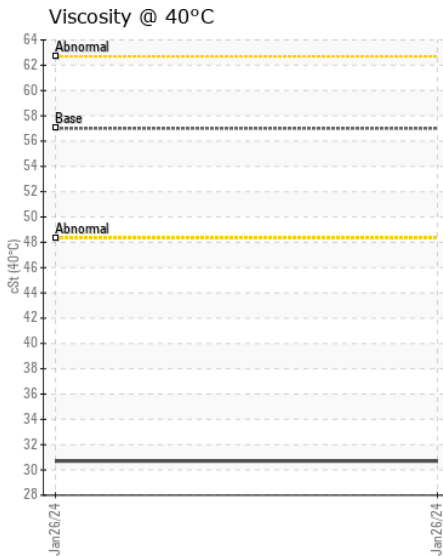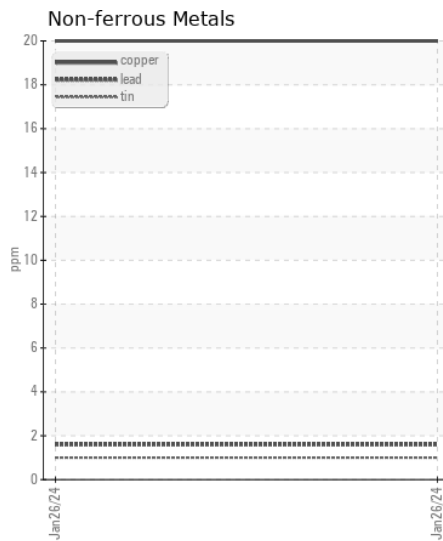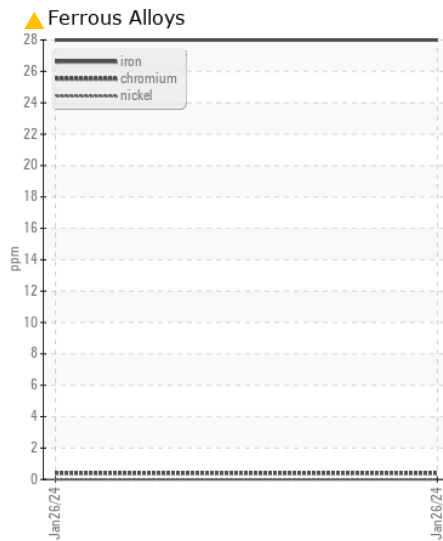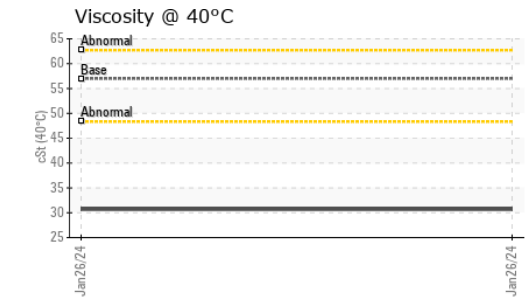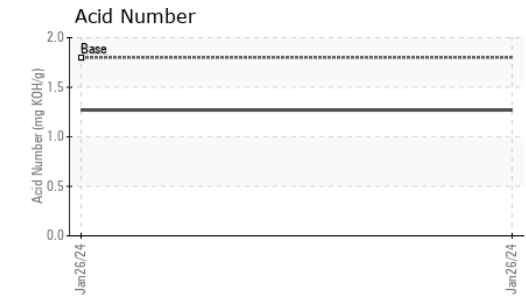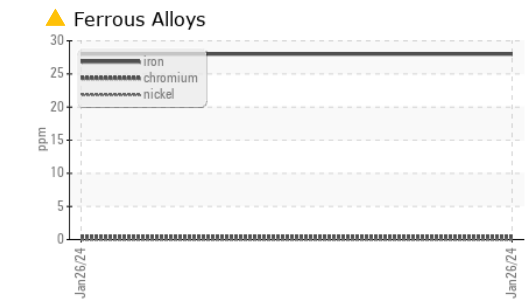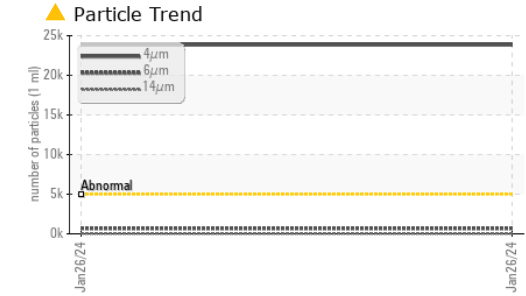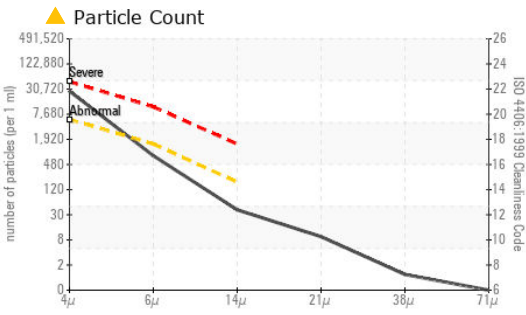

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0183575 **Received** : 31 Jan 2024
Lab Number : 06075639 **Diagnosed** : 02 Feb 2024
Unique Number : 10857730 **Diagnostician** : Jonathan Hester
Test Package : CONST (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - HARRISONBURG
 1332 GARBERS CHURCH RD
 HARRISONBURG, VA
 US 22801
 Contact: JOSH MITCHELL
 jmittchell@jamesriverequipment.com

T: (540)434-4457

F: