


WEAR CONTAMINATION FLUID CONDITION

ABNORMAL ABNORMAL NORMAL

RIG 2

## WHITE STAR 2450 R2-P-01G-NKL

Component Gearbox Fluid							
Gearbox Oil ( GAL)							
RECOMMENDATION	Test	UOM	Method	Limit/Abn	Current	History1	History2
We advise that you check all areas where dirt can enter the system. We recommend you service the filters on this component if applicable. Resample at the next service interval to monitor.	Sample Number		Client Info		KL0013830	KL0014049	KL0013108
	Sample Date		Client Info		24 Jan 2024	29 Dec 2023	17 Nov 202
	Machine Age	days	Client Info		0	45290	45247
	Oil Age	days	Client Info		0	0	0
	Filter Age	days	Client Info		0	0	0
	Oil Changed		Client Info		N/A	N/A	N/A
	Filter Changed		Client Info		N/A	N/A	N/A
	Sample Status				ABNORMAL	ABNORMAL	ABNORMA
WEAR	Iron	ppm	ASTM D5185m	>200	<b>400</b>	<b>△</b> 344	<u></u> 463
VVLAII	Chromium	ppm	ASTM D5185m		3	3	4
Gear wear is indicated.	Nickel	ppm	ASTM D5185m		4	2	3
	Titanium	ppm	ASTM D5185m	710	<1	<1	1
	Silver	ppm	ASTM D5185m		0	0	0
	Aluminum	ppm	ASTM D5185m	>25	<b>▲</b> 15	<b>▲</b> 10	<b>▲</b> 23
	Lead	ppm	ASTM D5185m		0	<1	<1
	Copper	ppm	ASTM D5185m		26	94	93
	Tin	ppm	ASTM D5185m		<1	1	1
	Vanadium	ppm	ASTM D5185m	710	<1	0	<1
	White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
	Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE
CONT A MINI A TION	Ciliana		ACTM DE10E		A CO	A F4	4.00
CONTAMINATION	Silicon Potassium	ppm	ASTM D5185m ASTM D5185m		▲ 63 8	▲ 51 13	108
There is a high amount of particulates present in the oil. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress.	Water	ppm	WC Method		NEG	NEG	NEG
	Particles >4µm		ASTM D7647	>0.2	279999		
	Particles >6µm		ASTM D7647	>5000	△ 213410		
	Particles >14μm		ASTM D7647		▲ 12317		
	Particles >21μm		ASTM D7647		▲ 249		
	Particles >38µm		ASTM D7647		1		
	Particles >71µm		ASTM D7647		0		
	Oil Cleanliness		ISO 4406 (c)		△ 25/21		
	Silt	scalar	*Visual	NONE	NONE	NONE	▲ HEAV
	Debris	scalar	*Visual	NONE	NONE	NONE	NONE
	Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
	Appearance		*Visual	NORML	NORML	NORML	NORM
	Odor	scalar	*Visual	NORML	NORML	NORML	NORM
	Emulsified Water		*Visual	>0.2	NEG	NEG	0.2%
······	Emalonica Water					1420	0.270
FLUID CONDITION	Sodium	ppm	ASTM D5185m		136	150	274
The ANI level is accordable for this first	Boron	ppm	ASTM D5185m		25	31	30
The AN level is acceptable for this fluid.	Barium	ppm	ASTM D5185m		30	56	79
	Molybdenum	ppm	ASTM D5185m		17	330	371
	Manganese	ppm	ASTM D5185m		3	3	4
	Magnesium	ppm	ASTM D5185m		26	18	25
	Calcium	ppm	ASTM D5185m		131	69	238
	Phosphorus	ppm	ASTM D5185m		267	160	237
	Zinc	ppm	ASTM D5185m		48	56	47
	Sulfur	ppm	ASTM D5185m		7101	8046	8387
	Acid Number (AN)	mg KOH/g	ASTM D8045		0.41		0.59
	Visc @ 40°C	cSt	ASTM D445		404	423	425

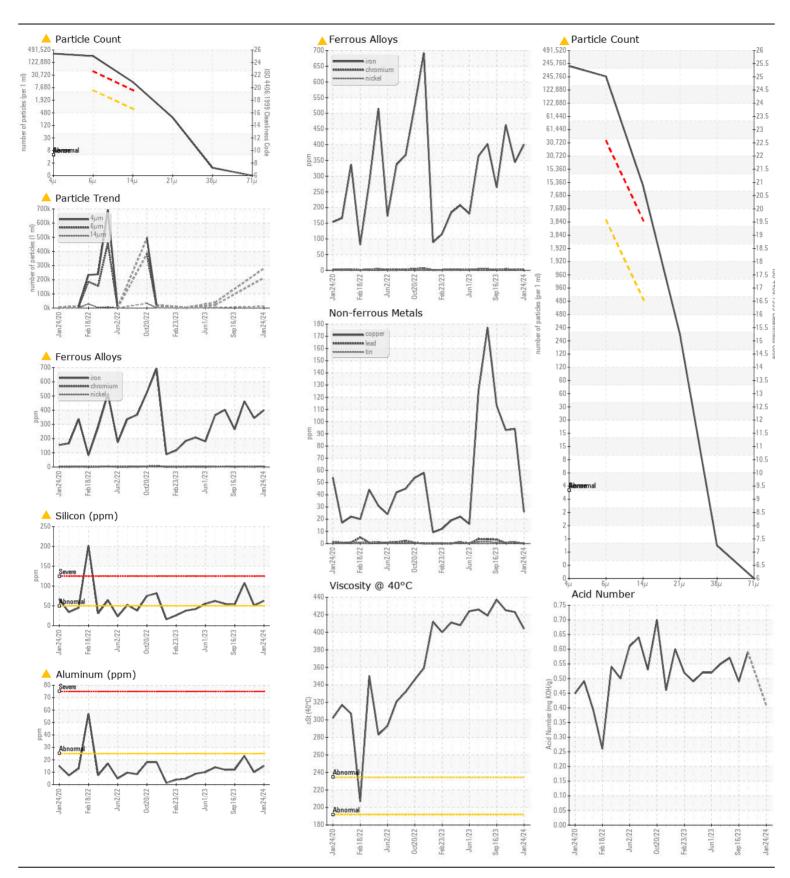



Certificate L2367

Laboratory

Sample No. : 06083057 Lab Number

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 : KL0013830

Unique Number : 10870502

: 07 Feb 2024 Received **Tested** : 08 Feb 2024

: 09 Feb 2024 - Don Baldridge Diagnosed

Test Package : MOB 2 ( Additional Tests: PrtCount ) To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation. Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012) CITADEL DRILLING

7550 W I20 ODESSA, TX US 79763

Contact: MIKE COMBDEN mcombden@citadeldrilling.com

T: (780)955-5509 F: