



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Area
[W00223-HALLGRING]
 Machine Id
JOHN DEERE 5055E 34002118 (S/N 1PY5055EAJJ107064)
 Component
Diesel Engine
 Fluid
JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0159095	JR0148868	---
Sample Date		Client Info		01 Feb 2024	05 Jan 2023	---
Machine Age	hrs	Client Info		215	168	---
Oil Age	hrs	Client Info		100	68	---
Filter Age	hrs	Client Info		100	68	---
Oil Changed		Client Info		Changed	Changed	---
Filter Changed		Client Info		Changed	Changed	---
Sample Status				NORMAL	NORMAL	---

WEAR

Metal levels are typical for a new component breaking in.

Iron	ppm	ASTM D5185m	>51	6	6	---
Chromium	ppm	ASTM D5185m	>11	<1	<1	---
Nickel	ppm	ASTM D5185m	>5	<1	3	---
Titanium	ppm	ASTM D5185m		<1	0	---
Silver	ppm	ASTM D5185m	>3	0	0	---
Aluminum	ppm	ASTM D5185m	>31	3	2	---
Lead	ppm	ASTM D5185m	>26	<1	<1	---
Copper	ppm	ASTM D5185m	>26	1	1	---
Tin	ppm	ASTM D5185m	>4	<1	0	---
Vanadium	ppm	ASTM D5185m		0	<1	---
White Metal	scalar	*Visual	NONE	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	---

CONTAMINATION







There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>22	8	7	---
Potassium	ppm	ASTM D5185m	>20	2	2	---
Fuel		WC Method	>2.1	<1.0	<1.0	---
Water		WC Method	>0.21	NEG	NEG	---
Glycol		WC Method		NEG	NEG	---
Soot %	%	*ASTM D7844	>3	0.1	0.1	---
Nitration	Abs/cm	*ASTM D7624	>20	6.4	6.6	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	19.6	20	---
Silt	scalar	*Visual	NONE	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.21	NEG	NEG	---

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>31	0	4	---
Boron	ppm	ASTM D5185m		314	300	---
Barium	ppm	ASTM D5185m		0	0	---
Molybdenum	ppm	ASTM D5185m		260	247	---
Manganese	ppm	ASTM D5185m		<1	<1	---
Magnesium	ppm	ASTM D5185m		854	779	---
Calcium	ppm	ASTM D5185m		1453	1451	---
Phosphorus	ppm	ASTM D5185m		913	889	---
Zinc	ppm	ASTM D5185m		1125	1097	---
Sulfur	ppm	ASTM D5185m		3147	3379	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	14.9	15.1	---
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	9.7	10.6	---
Visc @ 100°C	cSt	ASTM D445	15.4	14.0	13.8	---

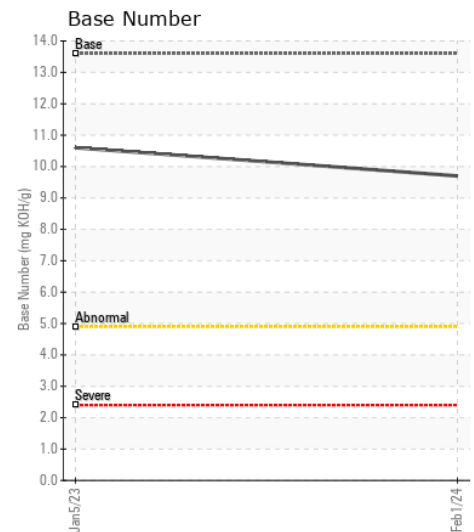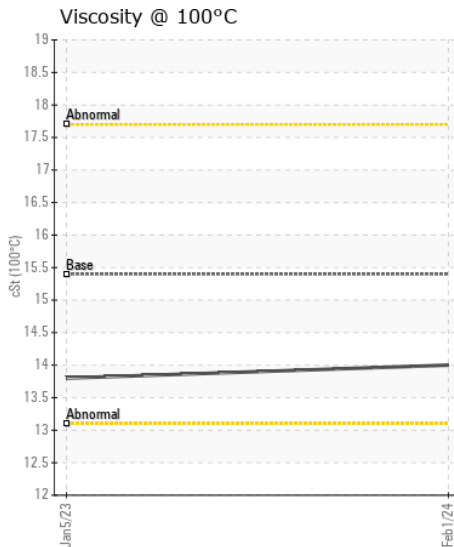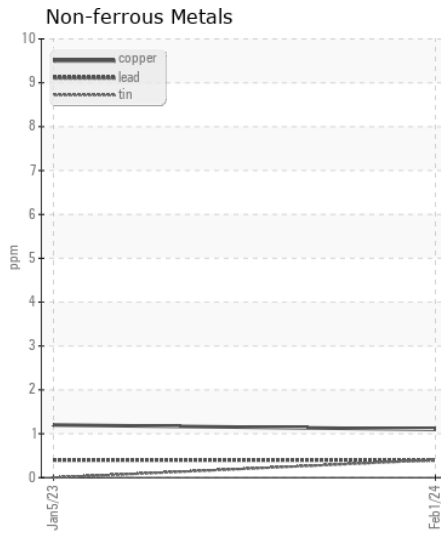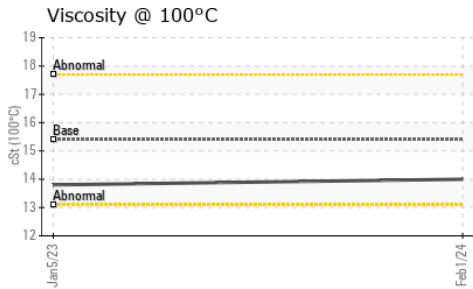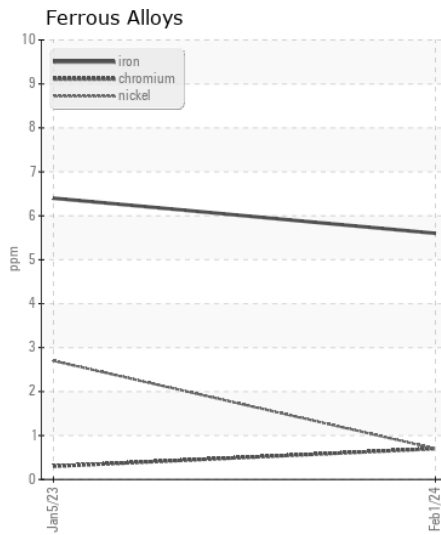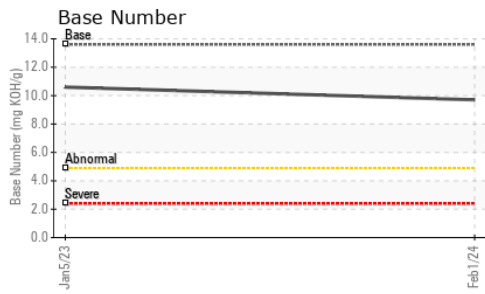

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : JR0159095

Lab Number : 06085256

Unique Number : 10872701

Test Package : CONST (Additional Tests: TBN)

Received : 09 Feb 2024

Tested : 12 Feb 2024

Diagnosed : 12 Feb 2024 - Wes Davis

JRE - DILLWYN

284 MAIN ST

DILLWYN, VA

US 23936

Contact: MIKE FALVELLA

mike.falvella@jamesriverequipment.com

T: (434)983-1633

F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)