



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 6115M 12780
 Component
Hydraulic System
 Fluid
JOHN DEERE HY-GARD HYD/TRANS LOW VIS (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0158712	---	---
Sample Date		Client Info		09 Feb 2024	---	---
Machine Age	hrs	Client Info		1107	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		N/A	---	---
Filter Changed		Client Info		N/A	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	1	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	<1	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	2	---	---
Lead	ppm	ASTM D5185m	>10	<1	---	---
Copper	ppm	ASTM D5185m	>75	<1	---	---
Tin	ppm	ASTM D5185m	>10	<1	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION











There is no indication of any contamination in the oil. The amount and size of particulates present in the system are acceptable.

Silicon	ppm	ASTM D5185m	>20	5	---	---
Potassium	ppm	ASTM D5185m	>20	2	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	2244	---	---
Particles >6µm		ASTM D7647	>1300	377	---	---
Particles >14µm		ASTM D7647	>160	28	---	---
Particles >21µm		ASTM D7647	>40	6	---	---
Particles >38µm		ASTM D7647	>10	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	18/16/12	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

Confirm oil type. The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		0	---	---
Boron	ppm	ASTM D5185m		0	---	---
Barium	ppm	ASTM D5185m		13	---	---
Molybdenum	ppm	ASTM D5185m		1	---	---
Manganese	ppm	ASTM D5185m		<1	---	---
Magnesium	ppm	ASTM D5185m		93	---	---
Calcium	ppm	ASTM D5185m		3279	---	---
Phosphorus	ppm	ASTM D5185m		987	---	---
Zinc	ppm	ASTM D5185m		1162	---	---
Sulfur	ppm	ASTM D5185m		3886	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045		1.35	---	---
Visc @ 40°C	cSt	ASTM D445	32	59.5	---	---

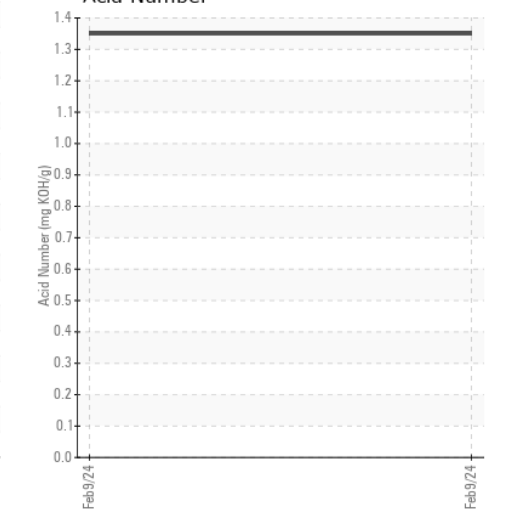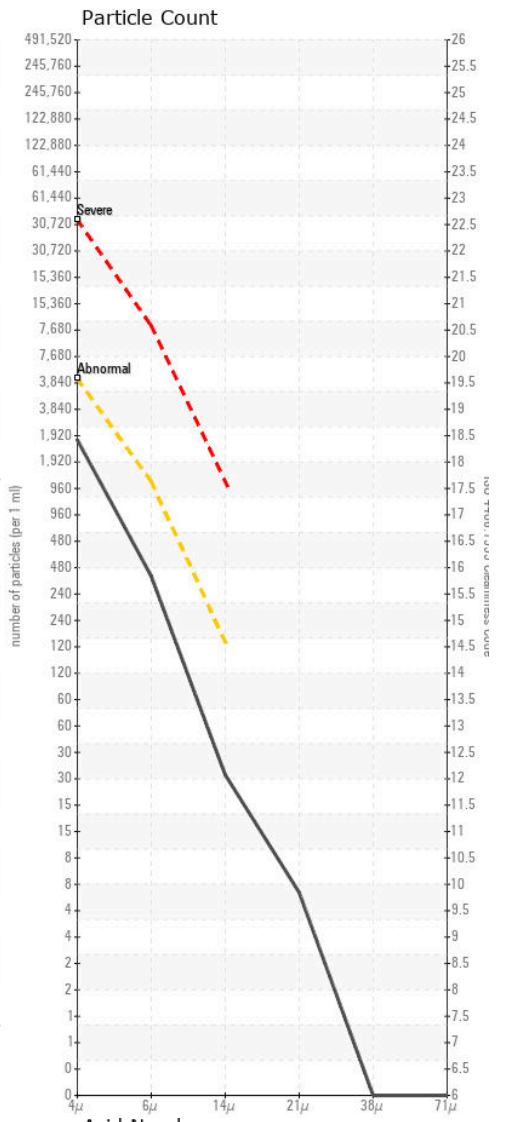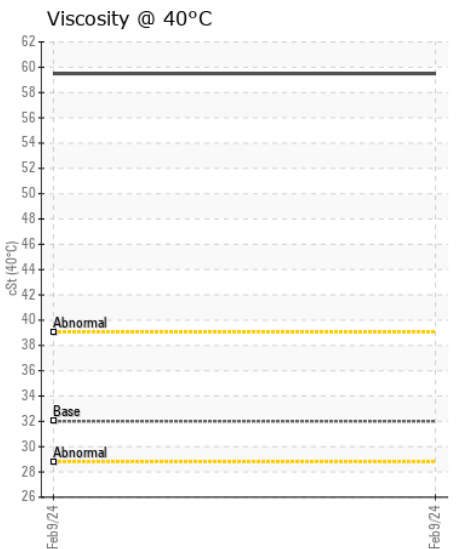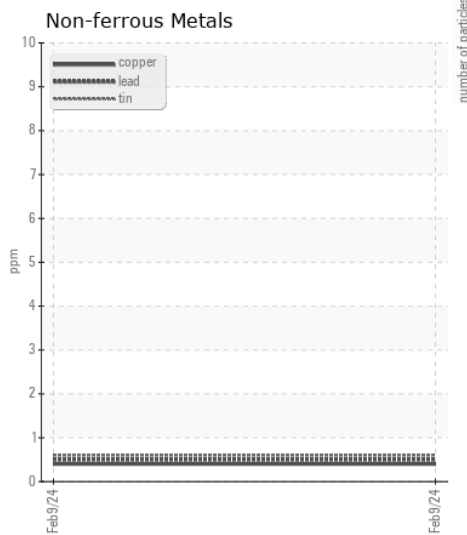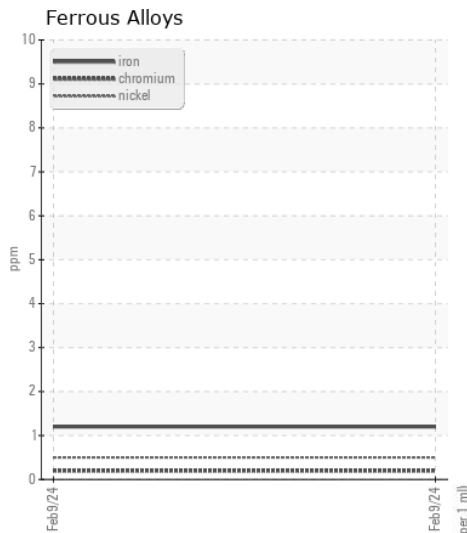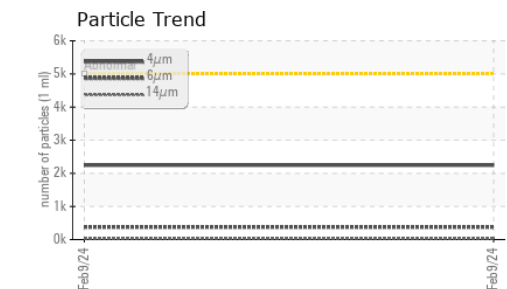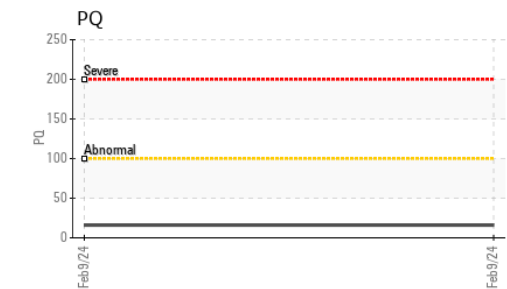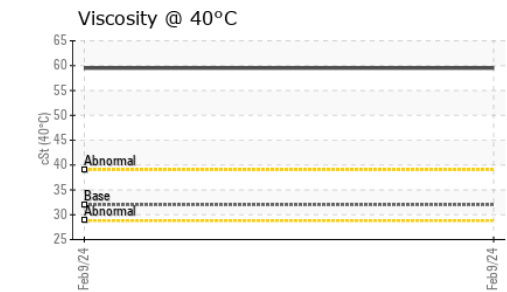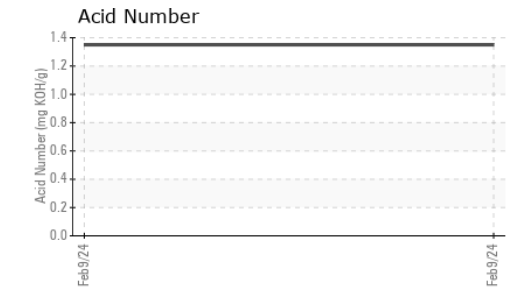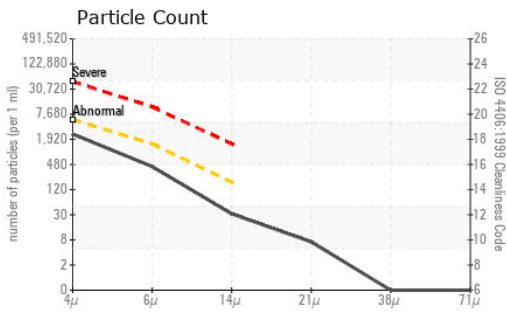

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
 Sample No. : JR0158712 Received : 12 Feb 2024
 Lab Number : 06085980 Tested : 13 Feb 2024
 Unique Number : 10873425 Diagnosed : 13 Feb 2024 - Don Baldrige
 Test Package : MOBCE (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - FISHERSVILLE
 98 EXPO ROAD
 FISHERSVILLE, VA
 US 22939

Contact: MIKE JENKINS
 MIKE.JENKINS@JAMESRIVEREQUIPMENT.COM

T: (540)292-3494
 F: (540)337-1495