



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	ABNORMAL

Machine Id
SZLG730262
Component
Diesel Engine
Fluid
{not provided} (--- GAL)

RECOMMENDATION

The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition. Please specify the component make and model with your next sample. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0868953	WC0614809	WC0422970
Sample Date		Client Info		22 Jan 2024	27 Jul 2021	27 Jan 2020
Machine Age	hrs	Client Info		0	3125	1522
Oil Age	hrs	Client Info		0	0	0
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		Changed	N/A	Changed
Filter Changed		Client Info		Changed	N/A	Changed
Sample Status				ABNORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	6	11	12
Chromium	ppm	ASTM D5185m	>20	0	0	<1
Nickel	ppm	ASTM D5185m	>4	<1	0	0
Titanium	ppm	ASTM D5185m		0	<1	10
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m	>20	3	3	5
Lead	ppm	ASTM D5185m	>40	1	0	<1
Copper	ppm	ASTM D5185m	>330	1	9	17
Tin	ppm	ASTM D5185m	>15	<1	0	<1
Vanadium	ppm	ASTM D5185m		<1	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION








There is a moderate amount of fuel present in the oil. Tests confirm the presence of fuel in the oil.

Silicon	ppm	ASTM D5185m	>25	4	4	5
Potassium	ppm	ASTM D5185m	>20	2	0	2
Fuel	%	ASTM D3524	>5	▲ 6.9	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.1	0.2	0.1
Nitration	Abs/cm	*ASTM D7624	>20	7.1	7.4	8.6
Sulfation	Abs/.1mm	*ASTM D7415	>30	20.7	20.6	18.8
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.

Sodium	ppm	ASTM D5185m		5	3	3
Boron	ppm	ASTM D5185m		285	369	124
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		80	128	54
Manganese	ppm	ASTM D5185m		<1	0	<1
Magnesium	ppm	ASTM D5185m		471	558	603
Calcium	ppm	ASTM D5185m		1367	1549	1447
Phosphorus	ppm	ASTM D5185m		1035	760	663
Zinc	ppm	ASTM D5185m		1280	965	723
Sulfur	ppm	ASTM D5185m		3181	2162	3030
Oxidation	Abs/.1mm	*ASTM D7414	>25	15.8	16.1	14.5
Base Number (BN)	mg KOH/g	ASTM D2896		6.9	7.7	7.7
Visc @ 100°C	cSt	ASTM D445		▲ 11.5	12.7	13.1

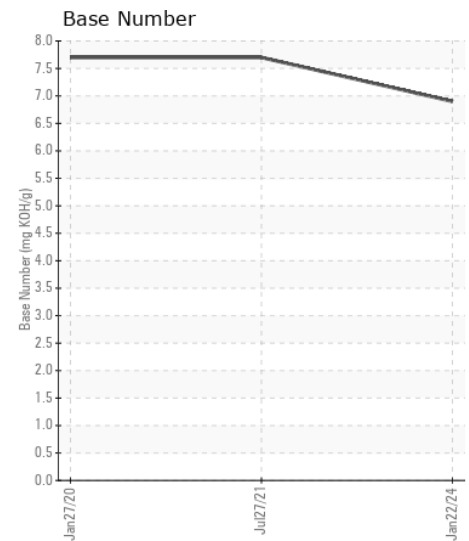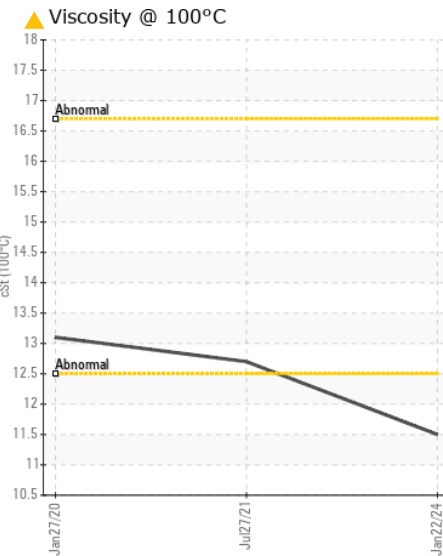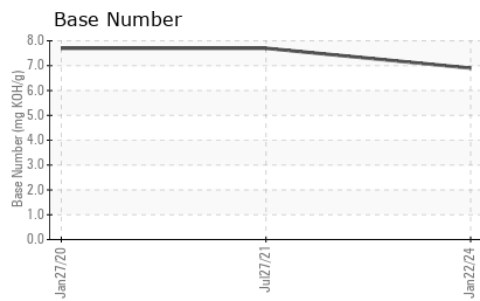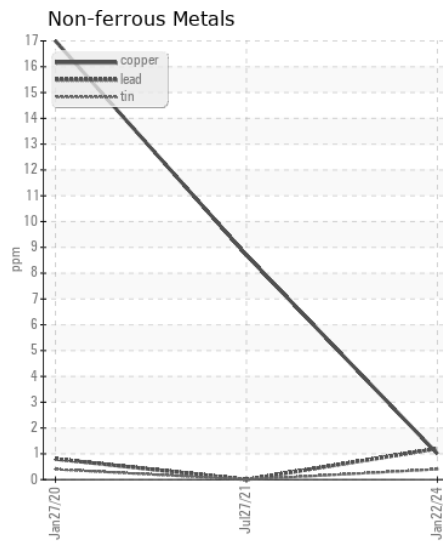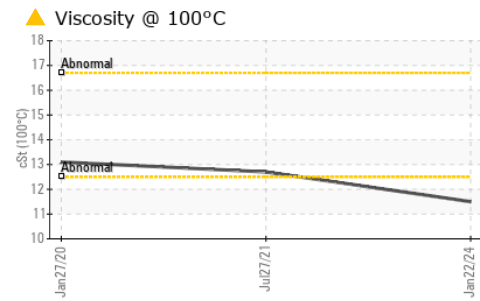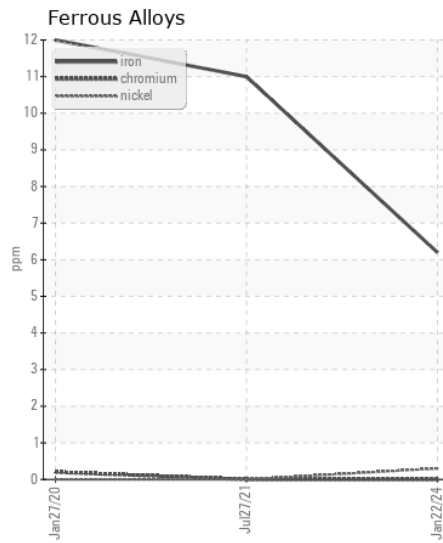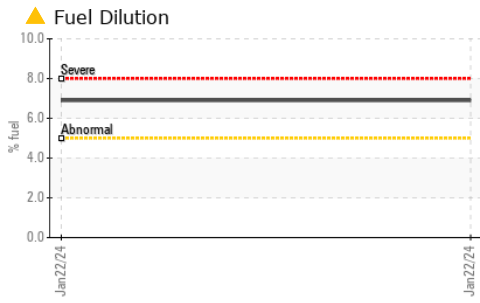

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : WC0868953

Lab Number : 06099742

Unique Number : 10897972

Test Package : FLEET (Additional Tests: FuelDilution, PercentFuel)

Received : 26 Feb 2024

Tested : 28 Feb 2024

Diagnosed : 28 Feb 2024 - Wes Davis

DOLE FRESH FRUIT
 PO BOX 725, ATTN: MAINTENANCE AND REPAIR
 NEW CASTLE, DE
 US 19720

Contact: LUIS LAPIERRE
 luis.lapierre@dole.com

T: (302)652-6344

F: (302)652-6061

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)