



# OIL ANALYSIS REPORT

|                 |        |
|-----------------|--------|
| WEAR            | NORMAL |
| CONTAMINATION   | NORMAL |
| FLUID CONDITION | NORMAL |

Machine Id  
**1769**  
Component  
**Diesel Engine**  
Fluid  
**DIESEL ENGINE OIL SAE 15W40 (--- QTS)**

## RECOMMENDATION

Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

| Test           | UOM | Method      | Limit/Abn | Current            | History1    | History2    |
|----------------|-----|-------------|-----------|--------------------|-------------|-------------|
| Sample Number  |     | Client Info |           | <b>WC0870806</b>   | WC0870848   | WC0821294   |
| Sample Date    |     | Client Info |           | <b>25 Jan 2024</b> | 20 Nov 2023 | 30 May 2023 |
| Machine Age    | mls | Client Info |           | <b>69568</b>       | 64220       | 54386       |
| Oil Age        | mls | Client Info |           | <b>0</b>           | 0           | 0           |
| Filter Age     | mls | Client Info |           | <b>0</b>           | 0           | 0           |
| Oil Changed    |     | Client Info |           | <b>N/A</b>         | Not Changd  | Not Changd  |
| Filter Changed |     | Client Info |           | <b>N/A</b>         | Not Changd  | Not Changd  |
| Sample Status  |     |             |           | <b>NORMAL</b>      | NORMAL      | NORMAL      |

## WEAR

Metal levels are typical for a new component breaking in.

|              |        |             |      |              |      |      |
|--------------|--------|-------------|------|--------------|------|------|
| Iron         | ppm    | ASTM D5185m | >100 | <b>11</b>    | 8    | 10   |
| Chromium     | ppm    | ASTM D5185m | >20  | <b>&lt;1</b> | <1   | <1   |
| Nickel       | ppm    | ASTM D5185m | >4   | <b>0</b>     | 0    | 0    |
| Titanium     | ppm    | ASTM D5185m |      | <b>0</b>     | 0    | 0    |
| Silver       | ppm    | ASTM D5185m | >3   | <b>0</b>     | 0    | 0    |
| Aluminum     | ppm    | ASTM D5185m | >20  | <b>10</b>    | 4    | 7    |
| Lead         | ppm    | ASTM D5185m | >40  | <b>1</b>     | 0    | 0    |
| Copper       | ppm    | ASTM D5185m | >330 | <b>&lt;1</b> | <1   | <1   |
| Tin          | ppm    | ASTM D5185m | >15  | <b>0</b>     | 0    | 0    |
| Vanadium     | ppm    | ASTM D5185m |      | <b>&lt;1</b> | <1   | 0    |
| White Metal  | scalar | *Visual     | NONE | <b>NONE</b>  | NONE | NONE |
| Yellow Metal | scalar | *Visual     | NONE | <b>NONE</b>  | NONE | NONE |

## CONTAMINATION











Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. There is no indication of any contamination in the oil.

|                  |          |             |       |                |       |       |
|------------------|----------|-------------|-------|----------------|-------|-------|
| Silicon          | ppm      | ASTM D5185m | >25   | <b>5</b>       | 4     | 4     |
| Potassium        | ppm      | ASTM D5185m | >20   | <b>10</b>      | 3     | 7     |
| Fuel             |          | WC Method   | >5    | <b>&lt;1.0</b> | <1.0  | <1.0  |
| Water            |          | WC Method   | >0.2  | <b>NEG</b>     | NEG   | NEG   |
| Glycol           |          | WC Method   |       | <b>NEG</b>     | NEG   | NEG   |
| Soot %           | %        | *ASTM D7844 | >3    | <b>0.5</b>     | 0.2   | 0.3   |
| Nitration        | Abs/cm   | *ASTM D7624 | >20   | <b>10.7</b>    | 8.3   | 9.5   |
| Sulfation        | Abs/.1mm | *ASTM D7415 | >30   | <b>21.2</b>    | 18.2  | 19.1  |
| Silt             | scalar   | *Visual     | NONE  | <b>NONE</b>    | NONE  | NONE  |
| Debris           | scalar   | *Visual     | NONE  | <b>NONE</b>    | NONE  | NONE  |
| Sand/Dirt        | scalar   | *Visual     | NONE  | <b>NONE</b>    | NONE  | NONE  |
| Appearance       | scalar   | *Visual     | NORML | <b>NORML</b>   | NORML | NORML |
| Odor             | scalar   | *Visual     | NORML | <b>NORML</b>   | NORML | NORML |
| Emulsified Water | scalar   | *Visual     | >0.2  | <b>NEG</b>     | NEG   | NEG   |

## FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

|                  |          |             |      |              |      |      |
|------------------|----------|-------------|------|--------------|------|------|
| Sodium           | ppm      | ASTM D5185m | >158 | <b>3</b>     | 1    | 2    |
| Boron            | ppm      | ASTM D5185m | 250  | <b>30</b>    | 50   | 40   |
| Barium           | ppm      | ASTM D5185m | 10   | <b>0</b>     | 0    | 0    |
| Molybdenum       | ppm      | ASTM D5185m | 100  | <b>85</b>    | 84   | 81   |
| Manganese        | ppm      | ASTM D5185m |      | <b>&lt;1</b> | 0    | <1   |
| Magnesium        | ppm      | ASTM D5185m | 450  | <b>118</b>   | 108  | 124  |
| Calcium          | ppm      | ASTM D5185m | 3000 | <b>2092</b>  | 2002 | 2243 |
| Phosphorus       | ppm      | ASTM D5185m | 1150 | <b>1016</b>  | 1031 | 1089 |
| Zinc             | ppm      | ASTM D5185m | 1350 | <b>1233</b>  | 1198 | 1327 |
| Sulfur           | ppm      | ASTM D5185m | 4250 | <b>3502</b>  | 3631 | 4647 |
| Oxidation        | Abs/.1mm | *ASTM D7414 | >25  | <b>17.3</b>  | 13.6 | 14.8 |
| Base Number (BN) | mg KOH/g | ASTM D2896  | 8.5  | <b>5.7</b>   | 7.0  | 7.7  |
| Visc @ 100°C     | cSt      | ASTM D445   | 14.4 | <b>12.7</b>  | 13.6 | 13.2 |

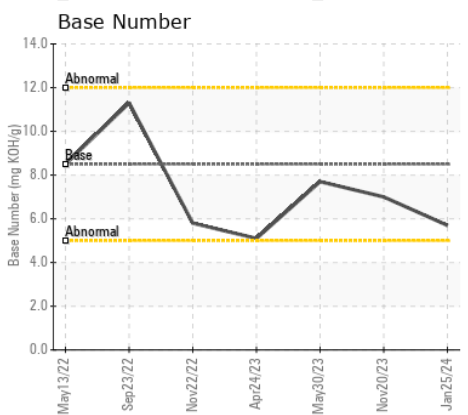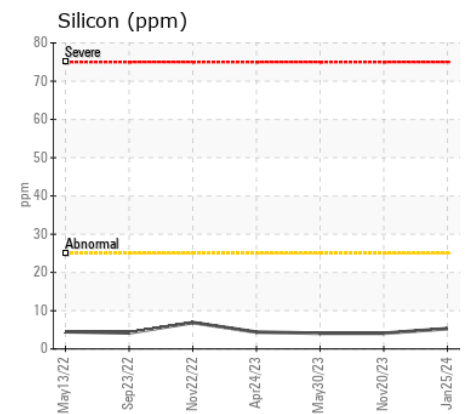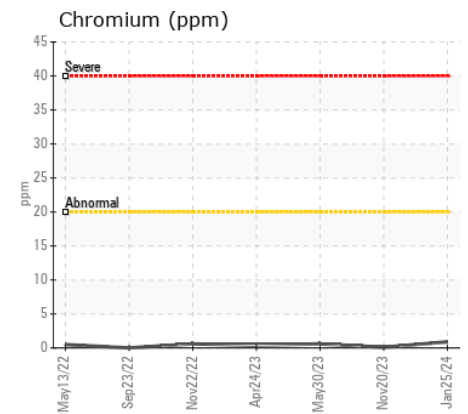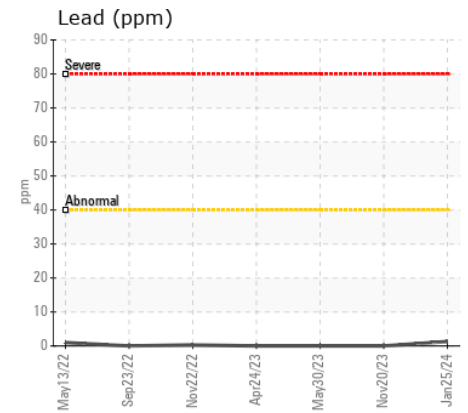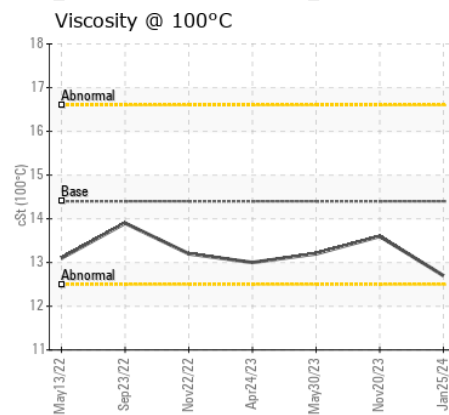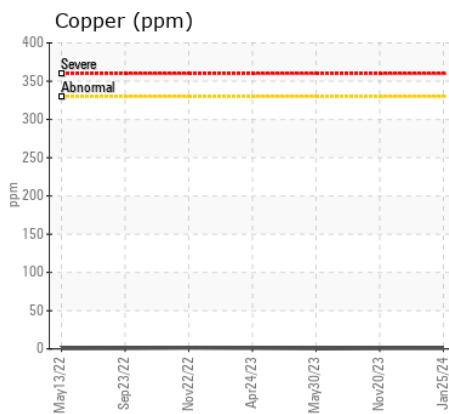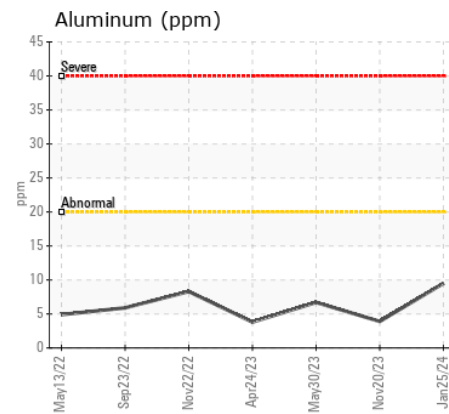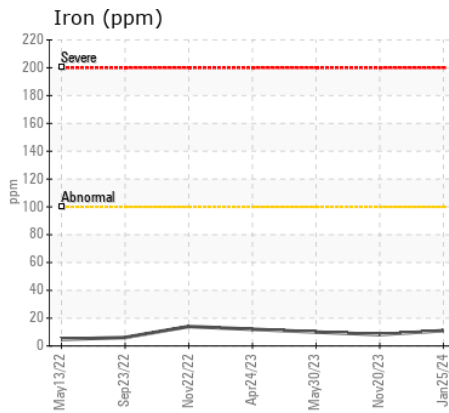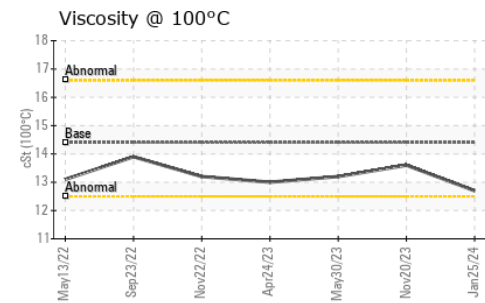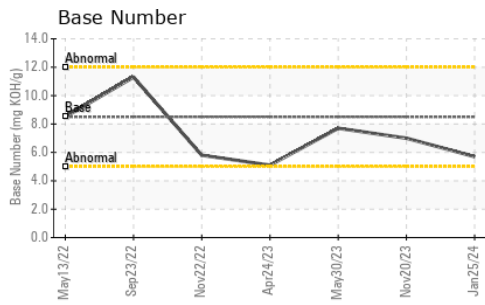

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : WC0870806

Lab Number : 06100788

Unique Number : 10899018

Test Package : MOB 1 ( Additional Tests: TBN )

Received : 26 Feb 2024

Tested : 27 Feb 2024

Diagnosed : 27 Feb 2024 - Wes Davis

WAKE COUNTY PUBLIC SCHOOL SYSTEM

1551 ROCK QUARRY ROAD

RALEIGH, NC

US 27610

Contact: DEVIN WEBER

dweber@wcpss.net

T: (919)856-8076

F: x:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)