



WEAR	<b>NORMAL</b>
CONTAMINATION	<b>ABNORMAL</b>
FLUID CONDITION	<b>NORMAL</b>

Machine Id  
**223030-1**  
 Component  
**Diesel Engine**  
 Fluid  
**PETRO CANADA DURON SHP 15W40 (--- GAL)**

**RECOMMENDATION**

We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Resample at the next service interval to monitor. Note that there appears to be a discrepancy in the total time on this component, when compared to the historical data.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		<b>GFL0110556</b>	GFL0110593	GFL0110559
Sample Date		Client Info		<b>14 Mar 2024</b>	27 Feb 2024	15 Feb 2024
Machine Age	hrs	Client Info		<b>1117</b>	478529	475877
Oil Age	hrs	Client Info		<b>400</b>	0	465379
Filter Age	hrs	Client Info		<b>400</b>	0	0
Oil Changed		Client Info		<b>Not Changd</b>	Not Changd	Not Changd
Filter Changed		Client Info		<b>N/A</b>	Not Changd	Not Changd
Sample Status				<b>ABNORMAL</b>	ABNORMAL	ABNORMAL

**WEAR**

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>80	<b>47</b>	42	35
Chromium	ppm	ASTM D5185m	>5	<b>0</b>	2	<1
Nickel	ppm	ASTM D5185m	>2	<b>0</b>	<1	0
Titanium	ppm	ASTM D5185m		<b>0</b>	<1	0
Silver	ppm	ASTM D5185m	>3	<b>0</b>	0	0
Aluminum	ppm	ASTM D5185m	>30	<b>&lt;1</b>	2	<1
Lead	ppm	ASTM D5185m	>30	<b>0</b>	<1	<1
Copper	ppm	ASTM D5185m	>150	<b>2</b>	1	<1
Tin	ppm	ASTM D5185m	>5	<b>0</b>	<1	<1
Vanadium	ppm	ASTM D5185m		<b>0</b>	0	0
White Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE

**CONTAMINATION**

Elemental level of silicon (Si) above normal.


Silicon	ppm	ASTM D5185m	>20	<b>▲ 48</b>	▲ 46	▲ 38
Potassium	ppm	ASTM D5185m	>20	<b>0</b>	2	0
Fuel		WC Method	>5	<b>&lt;1.0</b>	<1.0	<1.0
Water		WC Method	>0.2	<b>NEG</b>	NEG	NEG
Glycol		WC Method		<b>NEG</b>	NEG	NEG
Soot %	%	*ASTM D7844	>3	<b>2.9</b>	2.4	2.2
Nitration	Abs/cm	*ASTM D7624	>20	<b>10.3</b>	9.6	8.8
Sulfation	Abs/.1mm	*ASTM D7415	>30	<b>24.4</b>	24.5	22.6
Silt	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Debris	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Appearance	scalar	*Visual	NORML	<b>NORML</b>	NORML	NORML
Odor	scalar	*Visual	NORML	<b>NORML</b>	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	<b>NEG</b>	NEG	NEG

**FLUID CONDITION**


The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185m		<b>&lt;1</b>	1	2
Boron	ppm	ASTM D5185m	0	<b>3</b>	4	3
Barium	ppm	ASTM D5185m	0	<b>0</b>	0	0
Molybdenum	ppm	ASTM D5185m	60	<b>63</b>	67	64
Manganese	ppm	ASTM D5185m	0	<b>0</b>	<1	<1
Magnesium	ppm	ASTM D5185m	1010	<b>991</b>	945	910
Calcium	ppm	ASTM D5185m	1070	<b>1106</b>	1040	1024
Phosphorus	ppm	ASTM D5185m	1150	<b>1043</b>	1048	992
Zinc	ppm	ASTM D5185m	1270	<b>1200</b>	1228	1146
Sulfur	ppm	ASTM D5185m	2060	<b>3417</b>	3029	2866
Oxidation	Abs/.1mm	*ASTM D7414	>25	<b>16.2</b>	16.2	15.0
Base Number (BN)	mg KOH/g	ASTM D2896	9.8	<b>7.4</b>	9.0	9.7
Visc @ 100°C	cSt	ASTM D445	15.4	<b>13.8</b>	13.6	13.6


▲ Silicon (ppm)

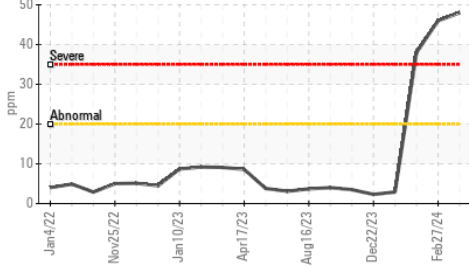


Ferrous Alloys

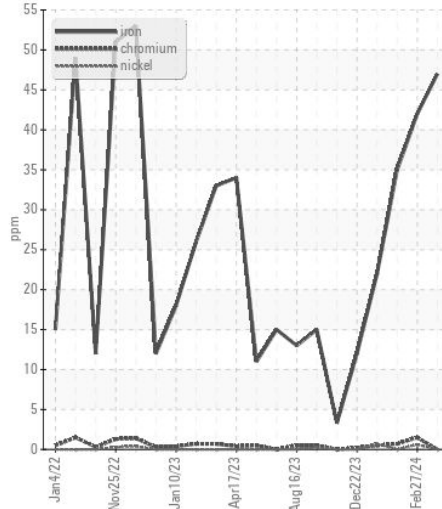


Base Number

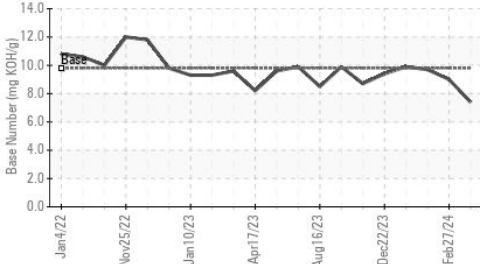


Non-ferrous Metals

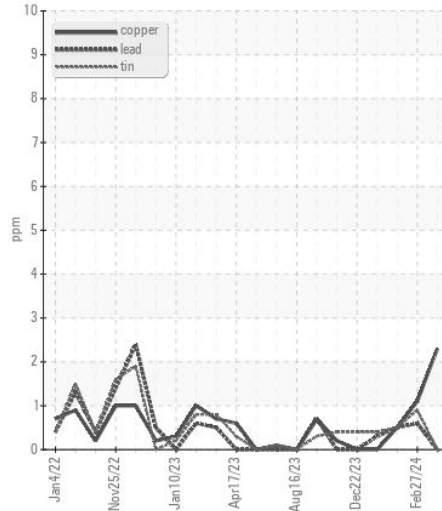


Viscosity @ 100°C

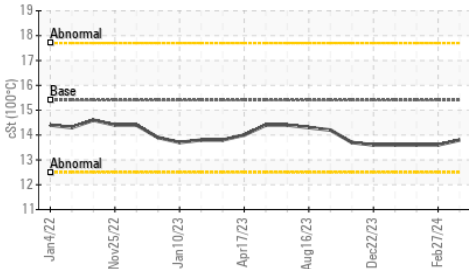

Viscosity @ 100°C

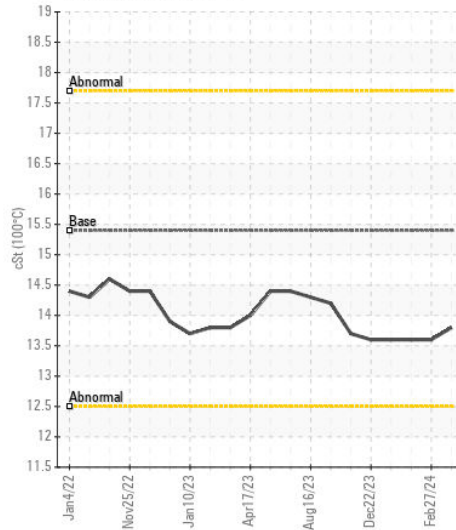

Base Number

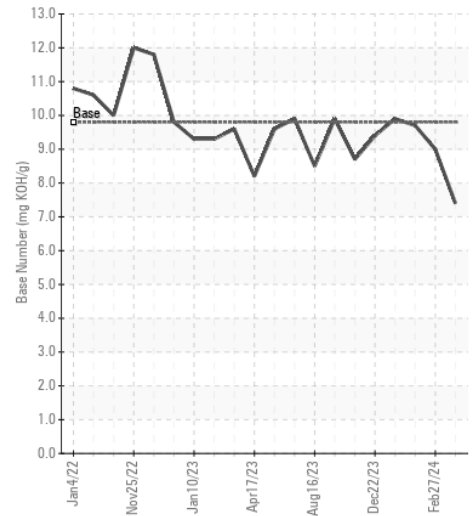

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : GFL0110556

Lab Number : 06122024

Unique Number : 10936175

Test Package : FLEET

Received : 19 Mar 2024

Tested : 19 Mar 2024

Diagnosed : 21 Mar 2024 - Don Baldrige

GFL Environmental - 166 - Phenix City

18 Old Brickyard Rd

Phenix City, AL

US 36869

Contact: DEAN PEACE JR

dean.peace@gflenv.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:

F: