



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
WILLIAM JEFFREY BAYER
Component
Starboard Main Engine
Fluid
DIESEL ENGINE OIL SAE 15W40 (20 GAL)

RECOMMENDATION

Resample at the next service interval to monitor. Please specify the component make and model with your next sample. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		MW0048166	MW0048208	MW0047947
Sample Date		Client Info		18 Mar 2024	09 Jan 2024	30 Oct 2023
Machine Age	hrs	Client Info		15706	14499	13547
Oil Age	hrs	Client Info		1207	952	912
Filter Age	hrs	Client Info		1207	952	912
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				NORMAL	NORMAL	ABNORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>75	14	7	11
Chromium	ppm	ASTM D5185m	>8	<1	<1	<1
Nickel	ppm	ASTM D5185m	>2	0	0	<1
Titanium	ppm	ASTM D5185m	>3	<1	0	<1
Silver	ppm	ASTM D5185m	>2	0	0	0
Aluminum	ppm	ASTM D5185m	>15	3	2	2
Lead	ppm	ASTM D5185m	>18	14	4	6
Copper	ppm	ASTM D5185m	>80	2	<1	1
Tin	ppm	ASTM D5185m	>14	<1	0	<1
Vanadium	ppm	ASTM D5185m		<1	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION







There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>20	5	4	5
Potassium	ppm	ASTM D5185m	>20	3	<1	1
Fuel		WC Method	>4.0	<1.0	1.8	▲ 4.9
Water		WC Method	>0.1	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844		0.4	0.3	0.3
Nitration	Abs/cm	*ASTM D7624	>20	9.4	8.2	8.4
Sulfation	Abs/.1mm	*ASTM D7415	>30	23.9	23.6	23.3
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>158	0	<1	<1
Boron	ppm	ASTM D5185m	250	306	332	318
Barium	ppm	ASTM D5185m	10	2	2	2
Molybdenum	ppm	ASTM D5185m	100	132	127	121
Manganese	ppm	ASTM D5185m		<1	0	0
Magnesium	ppm	ASTM D5185m	450	632	641	596
Calcium	ppm	ASTM D5185m	3000	1560	1400	1450
Phosphorus	ppm	ASTM D5185m	1150	702	683	636
Zinc	ppm	ASTM D5185m	1350	854	821	795
Sulfur	ppm	ASTM D5185m	4250	2606	2442	3274
Oxidation	Abs/.1mm	*ASTM D7414	>25	20.1	18.4	18.1
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	8.3	8.9	8.5
Visc @ 100°C	cSt	ASTM D445	14.4	12.5	12.8	▲ 12.1

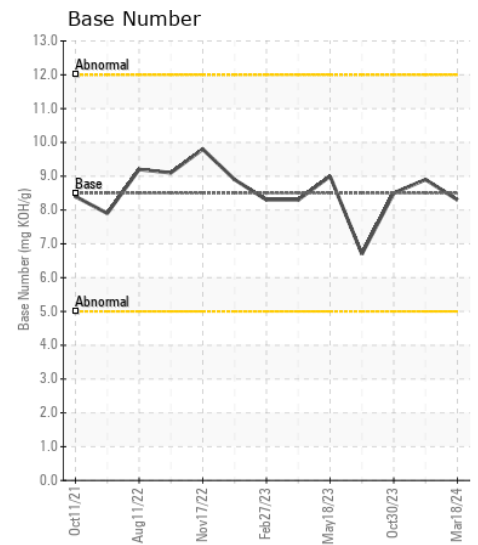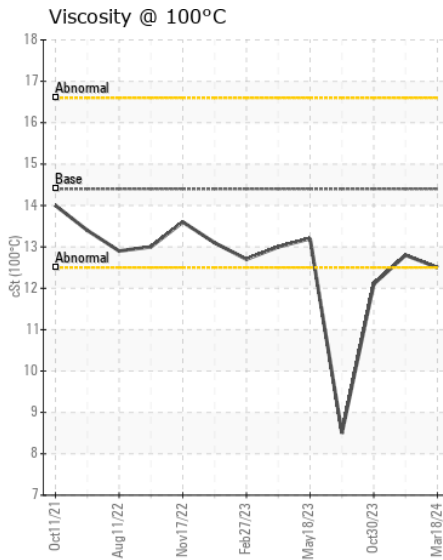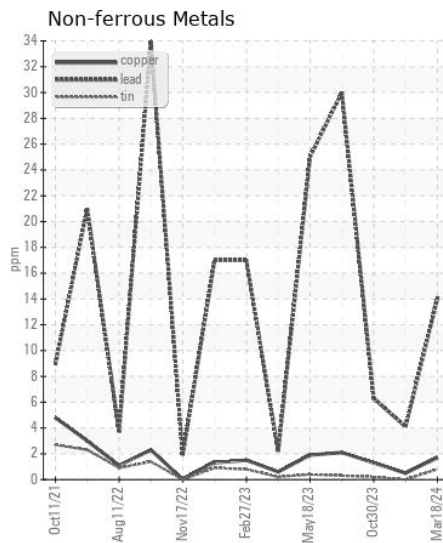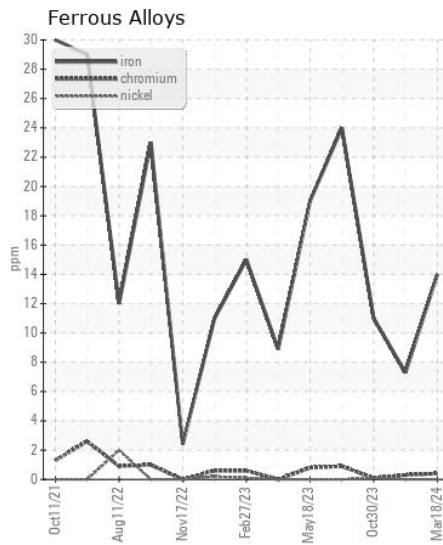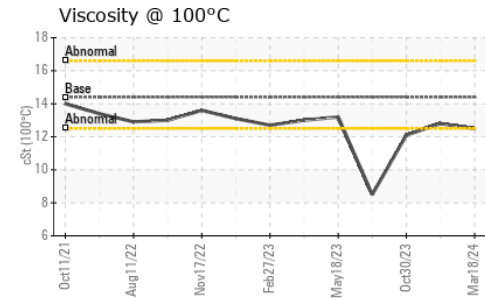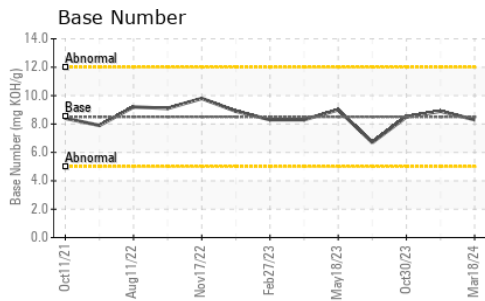

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : MW0048166
Lab Number : 06124713
Unique Number : 10938864
Test Package : MAR 2

Received : 21 Mar 2024
Tested : 22 Mar 2024
Diagnosed : 22 Mar 2024 - Wes Davis

ARTCO - ADM AG SERVICES & OIL SEEDS
 2505 BLUFF ROAD
 MT VERNON, IN
 US 47620
 Contact: JOE FLOYD
 joseph.floyd@adm.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:
F: