



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	ABNORMAL



Machine Id
JOHN DEERE 824K 1DW824KXAJF692402

Component
Diesel Engine

Fluid
JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (--- GAL)

RECOMMENDATION

Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0209108	JR0202673	JR0182999
Sample Date		Client Info		10 Apr 2024	26 Jan 2024	31 Oct 2023
Machine Age	hrs	Client Info		6000	5509	4996
Oil Age	hrs	Client Info		491	513	500
Filter Age	hrs	Client Info		491	0	500
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				ABNORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>51	14	7	7
Chromium	ppm	ASTM D5185m	>11	0	0	<1
Nickel	ppm	ASTM D5185m	>5	<1	0	0
Titanium	ppm	ASTM D5185m		<1	<1	<1
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m	>31	6	6	5
Lead	ppm	ASTM D5185m	>26	10	3	3
Copper	ppm	ASTM D5185m	>26	4	4	9
Tin	ppm	ASTM D5185m	>4	1	1	2
Vanadium	ppm	ASTM D5185m		<1	<1	<1
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION

Light fuel dilution occurring.


Silicon	ppm	ASTM D5185m	>22	7	7	9
Potassium	ppm	ASTM D5185m	>20	3	3	<1
Fuel	%	ASTM D3524	>8.0	6.3	<1.0	<1.0
Water		WC Method	>0.21	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.2	0.2	0.1
Nitration	Abs/cm	*ASTM D7624	>20	10.3	8.9	8.5
Sulfation	Abs/.1mm	*ASTM D7415	>30	25.3	22.4	21.2
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.21	NEG	NEG	NEG

FLUID CONDITION


Fuel is present in the oil and is lowering the viscosity. The BN result indicates that there is suitable alkalinity remaining in the oil.

Sodium	ppm	ASTM D5185m	>31	7	4	<1
Boron	ppm	ASTM D5185m		115	259	225
Barium	ppm	ASTM D5185m		0	<1	0
Molybdenum	ppm	ASTM D5185m		247	255	249
Manganese	ppm	ASTM D5185m		<1	<1	<1
Magnesium	ppm	ASTM D5185m		801	851	838
Calcium	ppm	ASTM D5185m		1352	1339	1401
Phosphorus	ppm	ASTM D5185m		780	895	902
Zinc	ppm	ASTM D5185m		967	1058	1108
Sulfur	ppm	ASTM D5185m		3447	3050	2981
Oxidation	Abs/.1mm	*ASTM D7414	>25	22.1	17.9	16.3
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	7.0	8.3	8.7
Visc @ 100°C	cSt	ASTM D445	15.4	▲ 11.8	12.5	12.6


▲ Viscosity @ 100°C

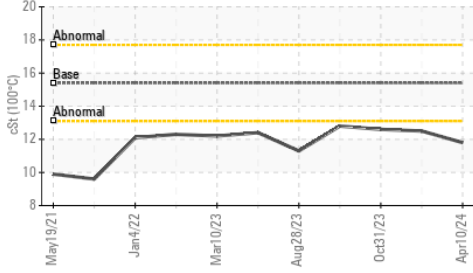


Ferrous Alloys

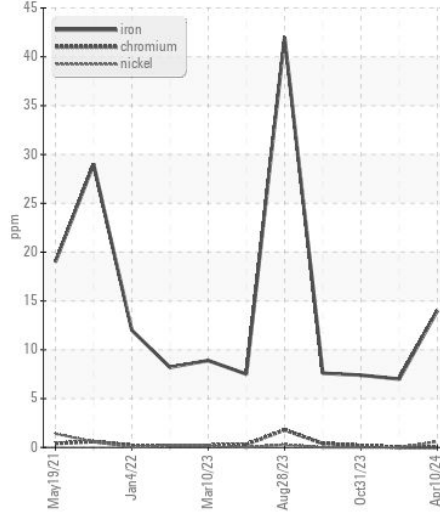


Fuel Dilution

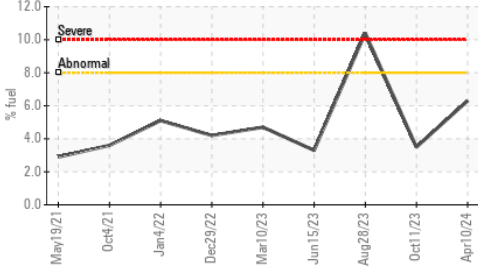


Non-ferrous Metals

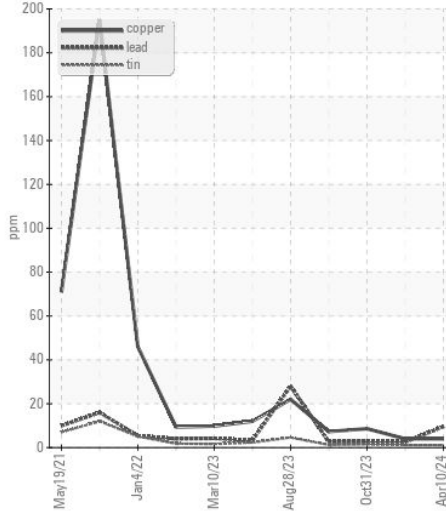


FT-IR (Direct Trend)

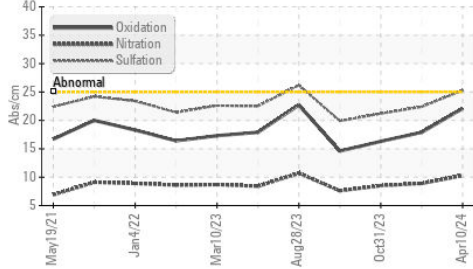


Base Number

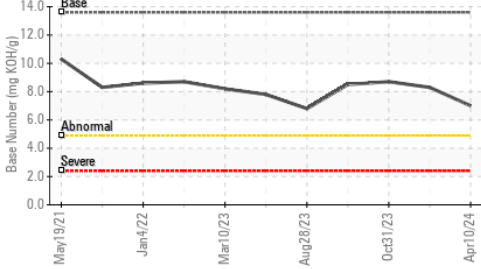

▲ Viscosity @ 100°C

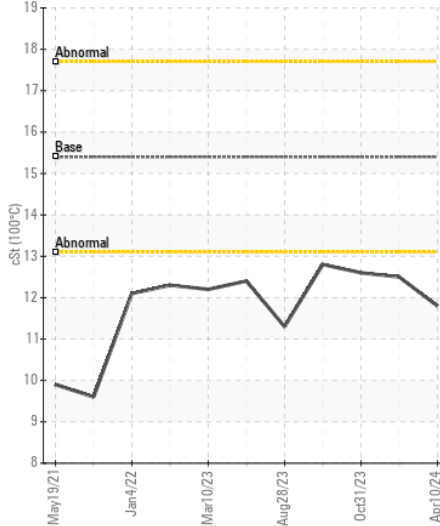

Base Number

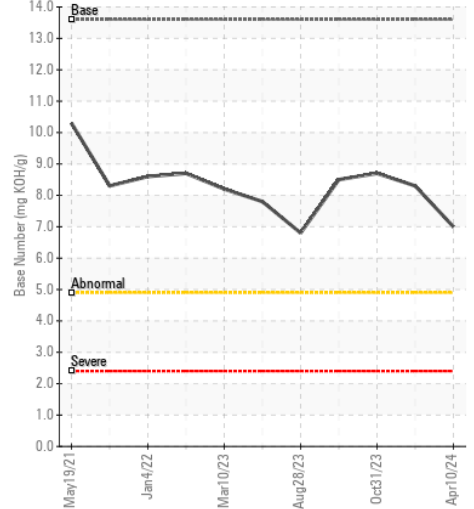

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0209108 **Received** : 10 Apr 2024
Lab Number : 06145225 **Tested** : 15 Apr 2024
Unique Number : 10970033 **Diagnosed** : 15 Apr 2024 - Jonathan Hester
Test Package : CONST (Additional Tests: FuelDilution, PercentFuel, TBN)

JRE - GARNER
 4161 AUBURN CHURCH RD
 GARNER, NC
 US 27529
 Contact: RALEIGH SHOP
 sean.betts@jamesriverequipment.com; catherine.anastasio@wearcheck.com
 T: (919)614-2260
 F: (919)779-5432

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)