

History1

- - -

.

History2

_ _ _ _

Machine Id JOHN DEERE 7230 L07230H586384 Component Hydraulic System

JOHN DEERE HY-GARD HYD/TRANS (--- GAL)

RECOMMENDATION	Test	UOM	Method	Limit/Abn	Current
	Sample Number		Client Info		JR0070482
Resample at the next service interval to monitor.	Sample Date		Client Info		28 Mar 2024
	Machine Age	hrs	Client Info		4600
	Oil Age	hrs	Client Info		0
	Filter Age	hrs	Client Info		0
	Oil Changed		Client Info		N/A
	Filter Changed		Client Info		N/A
	Sample Status				NORMAL
WEAR	PQ		ASTM D8184		16
All component wear rates are normal.	Iron	ppm	ASTM D5185m	>20	13
	Chromium	ppm	ASTM D5185m	>10	0
	Nickel	ppm	ASTM D5185m	>10	0
	Titanium	ppm	ASTM D5185m		0
	Silver	ppm	ASTM D5185m		0
	Aluminum	ppm	ASTM D5185m	>10	<1
	Lead	ppm	ASTM D5185m	>10	1
	Copper	ppm	ASTM D5185m	>75	16
	Tin	ppm	ASTM D5185m	>10	<1
	Vanadium	ppm	ASTM D5185m		0
	White Metal	scalar	*Visual	NONE	NONE
	Yellow Metal	scalar	*Visual	NONE	NONE
CONTAMINATION	Silicon	ppm	ASTM D5185m	<20	5
CONTAMINATION	Potassium	ppm	ASTM D5185m		0
There is no indication of any contamination in the oil. The amount and size of particulates present in the system are acceptable.	Water	ppiii	WC Method		NEG
	Particles >4µm		ASTM D7647		2002
	Particles >6µm		ASTM D7647		580
	Particles >14µm		ASTM D7647		55
	Particles >21µm		ASTM D7647		14
	Particles >38µm		ASTM D7647		1
	Particles >71µm		ASTM D7647		0
	Oil Cleanliness		ISO 4406 (c)	>19/17/14	18/16/13
	Silt	scalar	*Visual	NONE	NONE
	Debris	scalar	*Visual	NONE	NONE
	Sand/Dirt	scalar	*Visual	NONE	NONE
	Appearance	scalar	*Visual	NORML	NORML
	Odor	scalar	*Visual	NORML	NORML
	Emulsified Water	scalar	*Visual	>0.1	NEG
					_
FLUID CONDITION	Sodium	ppm	ASTM D5185m	0	3
The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.	Boron	ppm	ASTM D5185m		16
	Barium	ppm	ASTM D5185m		0
	Molybdenum	ppm	ASTM D5185m	0	1
	Manganese	ppm	ASTM D5185m	145	1
	Magnesium	ppm	ASTM D5185m		27
	Calcium	ppm	ASTM D5185m	3570	2758
	Phosphorus	ppm	ASTM D5185m	1290	982

Zinc

Sulfur

1079

3820

1.48

45.3


ASTM D5185m 1640

ppm

Acid Number (AN) mg KOH/g ASTM D8045 1.8

Visc @ 40°C cSt ASTM D445 57.0

ppm ASTM D5185m

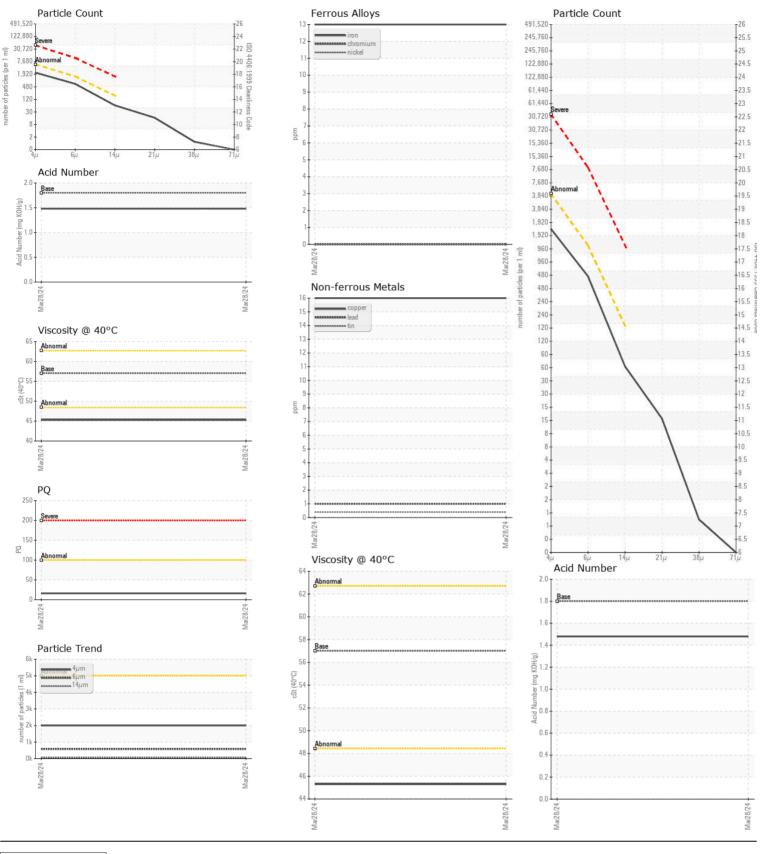

Contact/Location: ETHAN SHEETS - JAMROCVA Page 2 of 2