



WEAR	<b>NORMAL</b>
CONTAMINATION	<b>SEVERE</b>
FLUID CONDITION	<b>NORMAL</b>

Machine Id  
**1T0331GMHPF444531**

Component  
**Hydraulic System**

Fluid  
**JOHN DEERE HYDRAU (--- QTS)**

### RECOMMENDATION

We advise that you check all areas where contaminants can enter the system. We advise that you perform a filter service, and use off-line filtration to improve the cleanliness of the system fluid. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. Resample in 30-45 days to monitor this situation. Please specify the component make and model with your next sample.

### WEAR

All component wear rates are normal.











### CONTAMINATION

There is a high amount of particulates (2 to 100 microns in size) present in the oil.

### FLUID CONDITION

The AN level is acceptable for this fluid. The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		<b>JR0208235</b>	---	---
Sample Date		Client Info		<b>10 Apr 2024</b>	---	---
Machine Age	hrs	Client Info		<b>465</b>	---	---
Oil Age	hrs	Client Info		<b>465</b>	---	---
Filter Age	hrs	Client Info		<b>465</b>	---	---
Oil Changed		Client Info		<b>Not Chngd</b>	---	---
Filter Changed		Client Info		<b>Not Chngd</b>	---	---
Sample Status				<b>SEVERE</b>	---	---
PQ		ASTM D8184		<b>22</b>	---	---
Iron	ppm	ASTM D5185m	>20	<b>0</b>	---	---
Chromium	ppm	ASTM D5185m	>10	<b>0</b>	---	---
Nickel	ppm	ASTM D5185m	>10	<b>0</b>	---	---
Titanium	ppm	ASTM D5185m		<b>0</b>	---	---
Silver	ppm	ASTM D5185m		<b>0</b>	---	---
Aluminum	ppm	ASTM D5185m	>10	<b>&lt;1</b>	---	---
Lead	ppm	ASTM D5185m	>10	<b>2</b>	---	---
Copper	ppm	ASTM D5185m	>75	<b>1</b>	---	---
Tin	ppm	ASTM D5185m	>10	<b>0</b>	---	---
Vanadium	ppm	ASTM D5185m		<b>0</b>	---	---
White Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---
Silicon	ppm	ASTM D5185m	>20	<b>5</b>	---	---
Potassium	ppm	ASTM D5185m	>20	<b>1</b>	---	---
Water		WC Method	>0.1	<b>NEG</b>	---	---
Particles >4µm		ASTM D7647	>5000	<b>▲ 148356</b>	---	---
Particles >6µm		ASTM D7647	>1300	<b>▲ 82605</b>	---	---
Particles >14µm		ASTM D7647	>160	<b>▲ 11347</b>	---	---
Particles >21µm		ASTM D7647	>40	<b>▲ 2721</b>	---	---
Particles >38µm		ASTM D7647	>10	<b>▲ 94</b>	---	---
Particles >71µm		ASTM D7647	>3	<b>2</b>	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	<b>▲ 24/24/21</b>	---	---
Silt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Debris	scalar	*Visual	NONE	<b>NONE</b>	---	---
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Appearance	scalar	*Visual	NORML	<b>NORML</b>	---	---
Odor	scalar	*Visual	NORML	<b>NORML</b>	---	---
Emulsified Water	scalar	*Visual	>0.1	<b>NEG</b>	---	---
Sodium	ppm	ASTM D5185m		<b>3</b>	---	---
Boron	ppm	ASTM D5185m		<b>0</b>	---	---
Barium	ppm	ASTM D5185m		<b>0</b>	---	---
Molybdenum	ppm	ASTM D5185m		<b>0</b>	---	---
Manganese	ppm	ASTM D5185m		<b>&lt;1</b>	---	---
Magnesium	ppm	ASTM D5185m		<b>&lt;1</b>	---	---
Calcium	ppm	ASTM D5185m	87	<b>81</b>	---	---
Phosphorus	ppm	ASTM D5185m	727	<b>550</b>	---	---
Zinc	ppm	ASTM D5185m	900	<b>922</b>	---	---
Sulfur	ppm	ASTM D5185m	1500	<b>3269</b>	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	<b>1.08</b>	---	---
Visc @ 40°C	cSt	ASTM D445	65	<b>63.0</b>	---	---

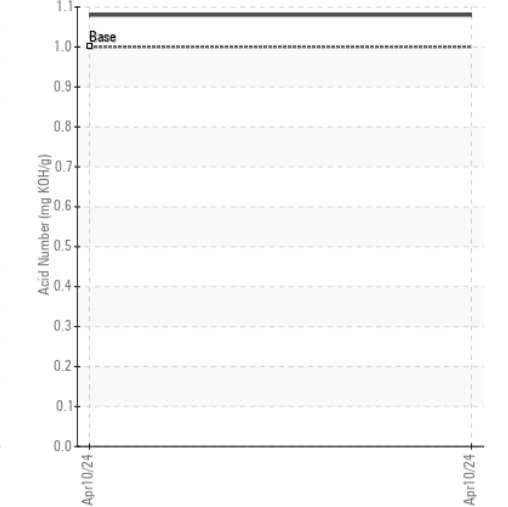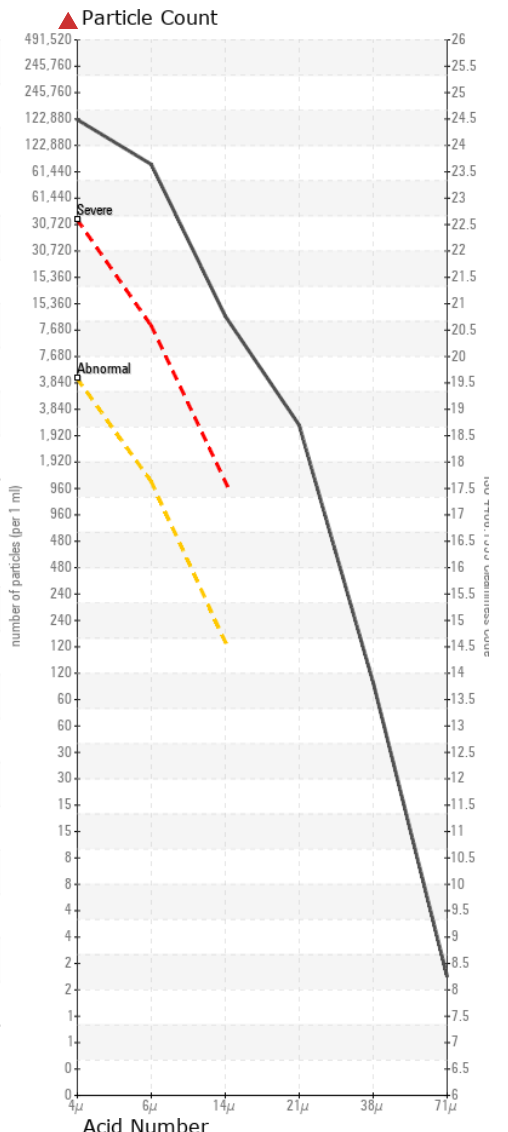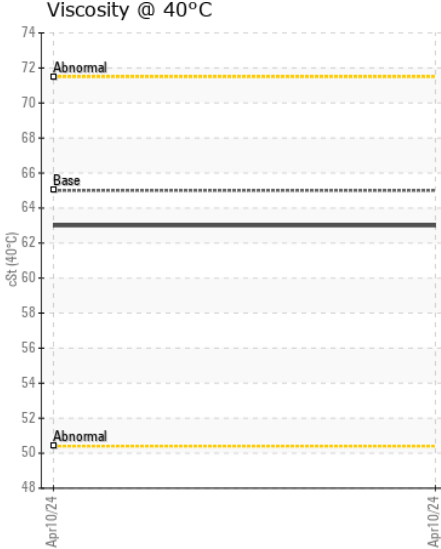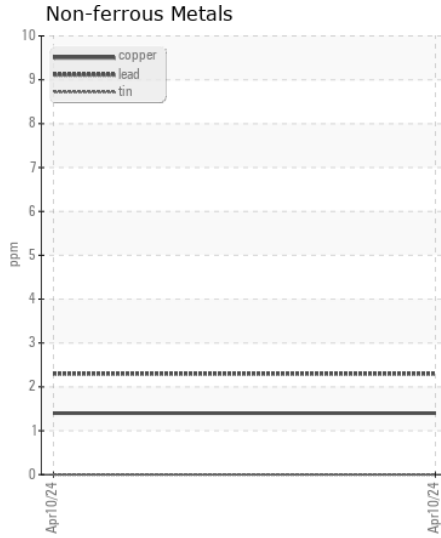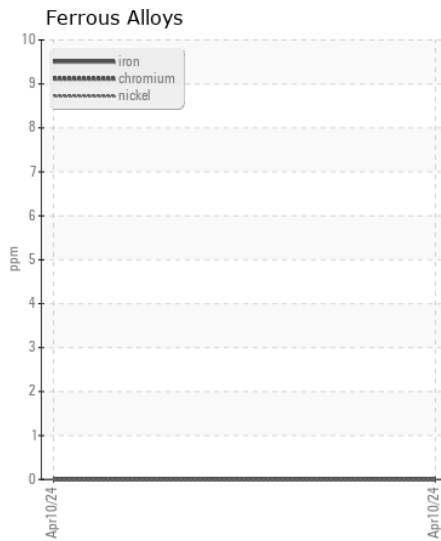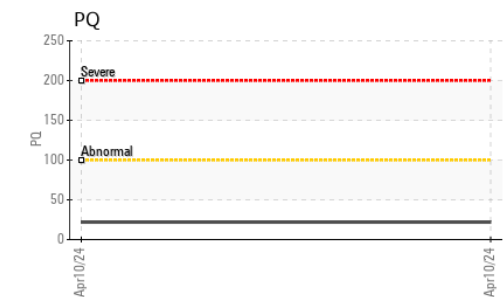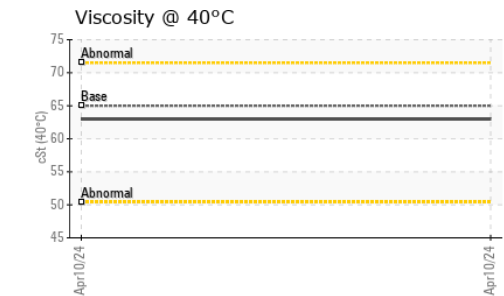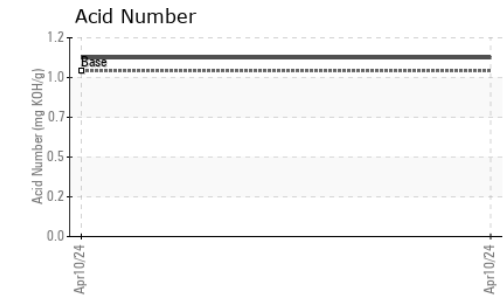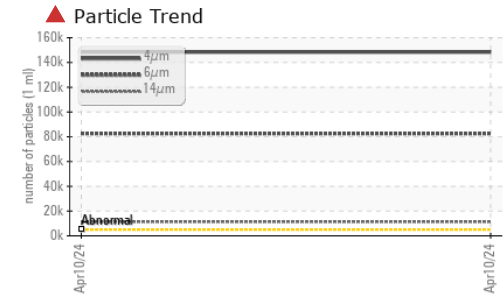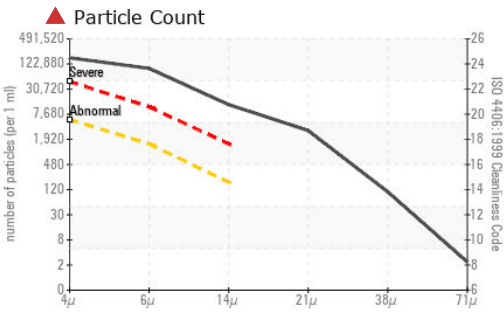

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : JR0208235 **Received** : 11 Apr 2024  
**Lab Number** : 06145768 **Tested** : 12 Apr 2024  
**Unique Number** : 10975846 **Diagnosed** : 12 Apr 2024 - Wes Davis  
**Test Package** : CONST ( Additional Tests: PQ )

**JRE - MANASSAS PARK**  
 9107 OWENS DRIVE  
 MANASSAS PARK, VA  
 US 20111  
 Contact: TECHNICIAN ACCOUNT  
 catherine.anastasio@wearcheck.com  
 T:  
 F: (703)631-4715

To discuss this sample report, contact Customer Service at 1-800-237-1369.  
 \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.  
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)