



WEAR	ABNORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Area
[W65889]

Machine Id
JOHN DEERE 350G 1FF350GXAMF815323

Component
Diesel Engine

Fluid
JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (7 GAL)

RECOMMENDATION

Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition. (Customer Sample Comment: W65889)

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0206800	JR0119792	---
Sample Date		Client Info		08 Apr 2024	19 Apr 2022	---
Machine Age	hrs	Client Info		4105	543	---
Oil Age	hrs	Client Info		3562	500	---
Filter Age	hrs	Client Info		0	500	---
Oil Changed		Client Info		Changed	Changed	---
Filter Changed		Client Info		Changed	Changed	---
Sample Status				ABNORMAL	NORMAL	---

WEAR

Cylinder, crank, or cam shaft wear is indicated. Exhaust valve wear is indicated.

Iron	ppm	ASTM D5185m	>51	▲ 88	40	---
Chromium	ppm	ASTM D5185m	>11	2	<1	---
Nickel	ppm	ASTM D5185m	>5	▲ 49	2	---
Titanium	ppm	ASTM D5185m		0	<1	---
Silver	ppm	ASTM D5185m	>3	0	0	---
Aluminum	ppm	ASTM D5185m	>31	4	2	---
Lead	ppm	ASTM D5185m	>26	<1	2	---
Copper	ppm	ASTM D5185m	>26	17	8	---
Tin	ppm	ASTM D5185m	>4	2	3	---
Vanadium	ppm	ASTM D5185m		0	0	---
White Metal	scalar	*Visual	NONE	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	---

CONTAMINATION










There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>22	11	7	---
Potassium	ppm	ASTM D5185m	>20	1	8	---
Fuel	%	ASTM D3524	>2.1	<1.0	0.2	---
Water		WC Method	>0.21	NEG	NEG	---
Glycol		WC Method		NEG	NEG	---
Soot %	%	*ASTM D7844	>3	1	0.3	---
Nitration	Abs/cm	*ASTM D7624	>20	8.4	8.9	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	23.6	25.1	---
Silt	scalar	*Visual	NONE	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.21	NEG	NEG	---

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185m	>31	4	3	---
Boron	ppm	ASTM D5185m		124	234	---
Barium	ppm	ASTM D5185m		0	0	---
Molybdenum	ppm	ASTM D5185m		101	195	---
Manganese	ppm	ASTM D5185m		2	2	---
Magnesium	ppm	ASTM D5185m		448	725	---
Calcium	ppm	ASTM D5185m		1489	1478	---
Phosphorus	ppm	ASTM D5185m		1006	850	---
Zinc	ppm	ASTM D5185m		1295	1046	---
Sulfur	ppm	ASTM D5185m		3185	2323	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	16.6	20.3	---
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	6.9	9.4	---
Visc @ 100°C	cSt	ASTM D445	15.4	12.8	11.2	---

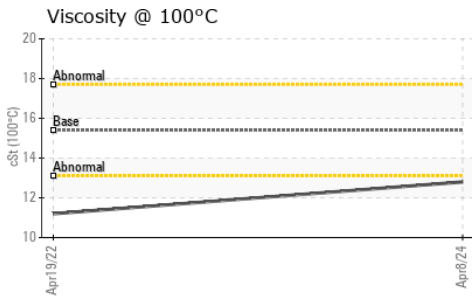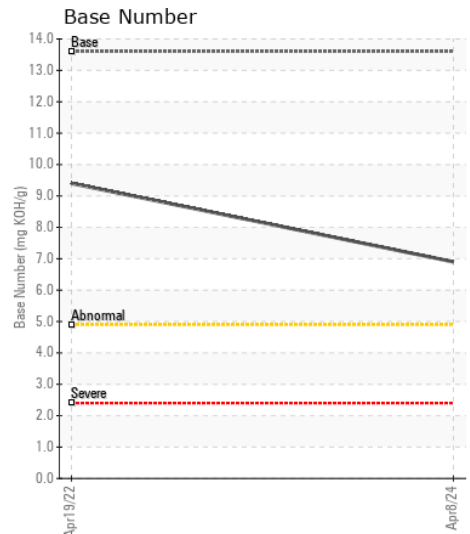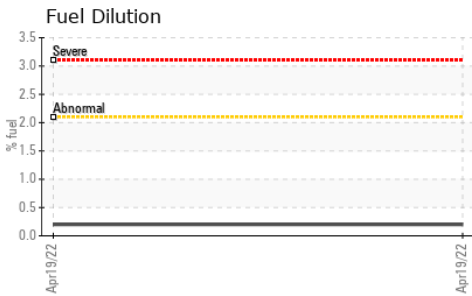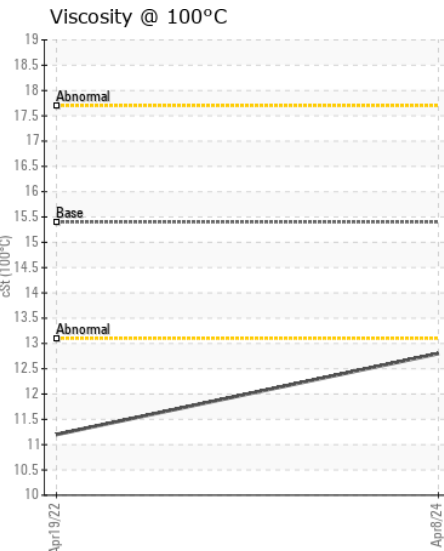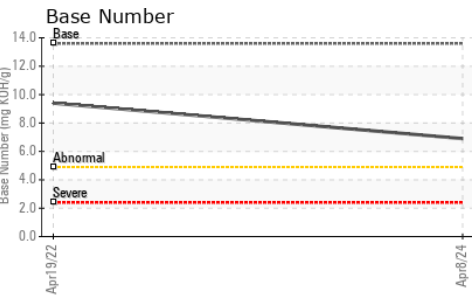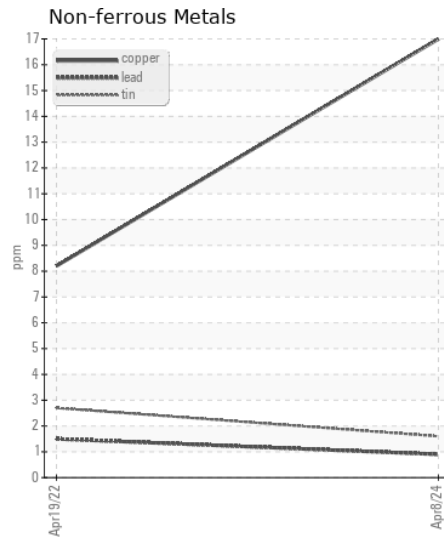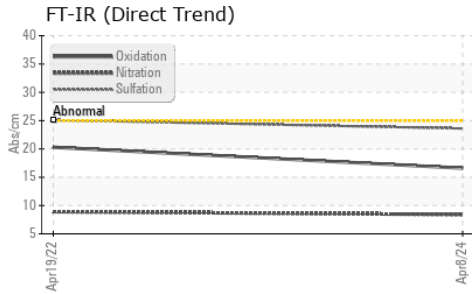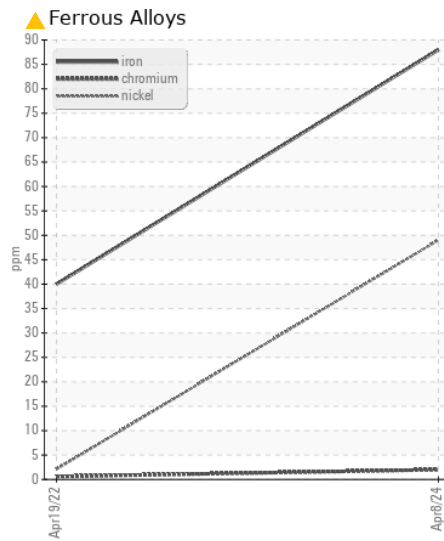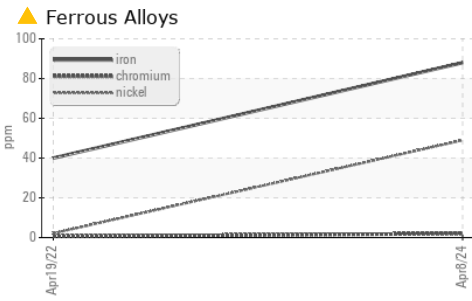

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0206800 **Received** : 12 Apr 2024
Lab Number : 06147172 **Tested** : 15 Apr 2024
Unique Number : 10977250 **Diagnosed** : 16 Apr 2024 - Sean Felton
Test Package : CONST (Additional Tests: FuelDilution, TBN)

JRE - CHARLOTTE
 9550 STATESVILLE ROAD
 CHARLOTTE, NC
 US 28269
 Contact: CHARLOTTE SHOP
 myoung@jamesriverequipment.com
 T: (704)597-0211
 F: (704)596-6198

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)