



LEAHY-WOLF
Lubricating specialists since 1946

OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	SEVERE
FLUID CONDITION	ABNORMAL

Machine Id
CCC 4010
Component
Diesel Engine
Fluid
DIESEL ENGINE OIL SAE 40 (--- GAL)

RECOMMENDATION

We advise that you check the fuel injection system. We recommend that you drain the oil from the component if this has not already been done. We recommend an early resample to monitor this condition.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LW0008999	LW0008623	LW0007255
Sample Date		Client Info		09 Apr 2024	27 Jan 2024	06 Nov 2023
Machine Age	mls	Client Info		0	0	0
Oil Age	mls	Client Info		0	0	0
Filter Age	mls	Client Info		0	0	0
Oil Changed		Client Info		N/A	N/A	N/A
Filter Changed		Client Info		N/A	N/A	N/A
Sample Status				SEVERE	NORMAL	SEVERE

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	72	17	10
Chromium	ppm	ASTM D5185m	>20	4	<1	<1
Nickel	ppm	ASTM D5185m	>4	<1	0	0
Titanium	ppm	ASTM D5185m		<1	<1	0
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m	>20	2	2	<1
Lead	ppm	ASTM D5185m	>40	<1	0	0
Copper	ppm	ASTM D5185m	>330	2	2	<1
Tin	ppm	ASTM D5185m	>15	<1	<1	0
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION













There is a high amount of fuel present in the oil. Tests confirm the presence of fuel in the oil.

Silicon	ppm	ASTM D5185m	>25	5	2	3
Potassium	ppm	ASTM D5185m	>20	2	2	0
Fuel	%	ASTM D3524	>5	▲ 9.1	1.8	▲ 62.1
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	2.4	0.7	0.3
Nitration	Abs/cm	*ASTM D7624	>20	13.6	8.9	9.0
Sulfation	Abs/.1mm	*ASTM D7415	>30	25.7	20.4	15.2
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.

Sodium	ppm	ASTM D5185m	>216	0	0	<1
Boron	ppm	ASTM D5185m	250	<1	<1	0
Barium	ppm	ASTM D5185m	10	0	<1	0
Molybdenum	ppm	ASTM D5185m	100	64	60	26
Manganese	ppm	ASTM D5185m		<1	0	0
Magnesium	ppm	ASTM D5185m	450	926	907	420
Calcium	ppm	ASTM D5185m	3000	1071	1010	▲ 455
Phosphorus	ppm	ASTM D5185m	1150	995	1017	▲ 465
Zinc	ppm	ASTM D5185m	1350	1160	1175	▲ 563
Sulfur	ppm	ASTM D5185m	4250	2712	3261	1298
Oxidation	Abs/.1mm	*ASTM D7414	>25	22.9	16.5	10.3
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	6.8	9.2	9.4
Visc @ 100°C	cSt	ASTM D445	14.4	▲ 11.3	12.3	▲ 3.8

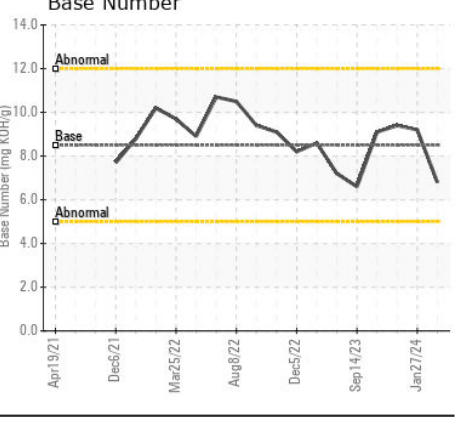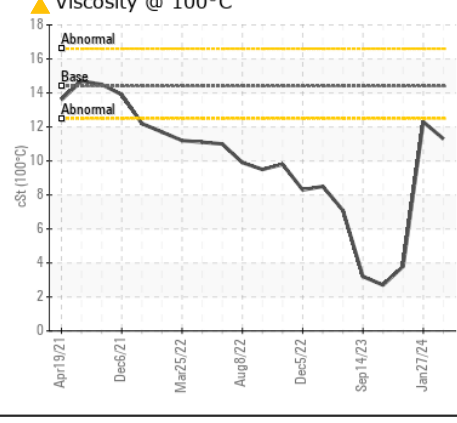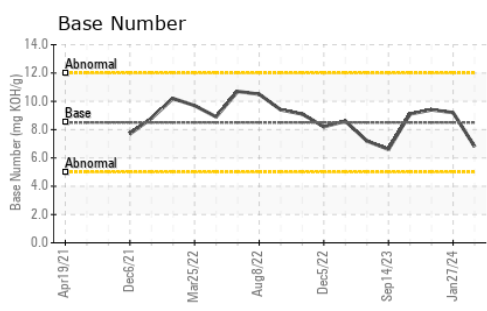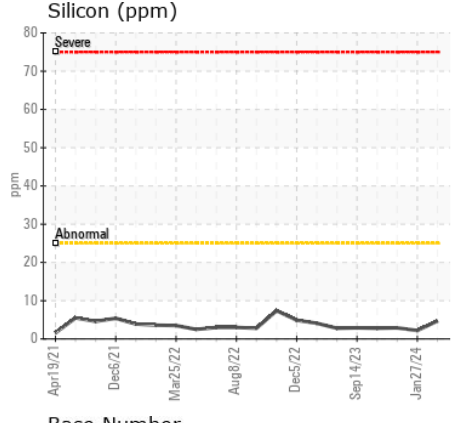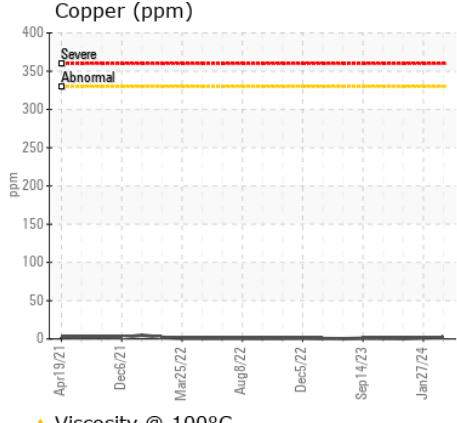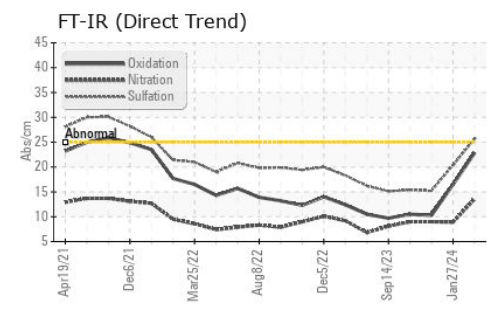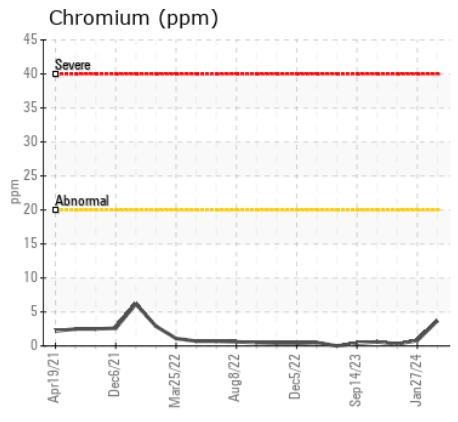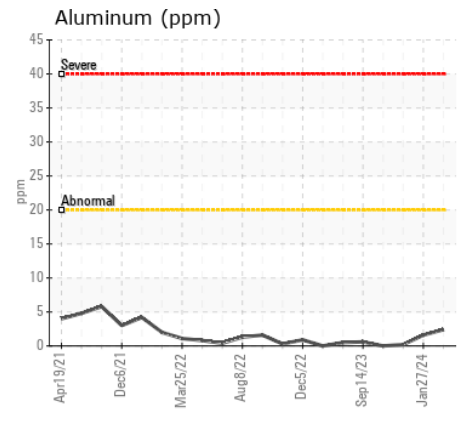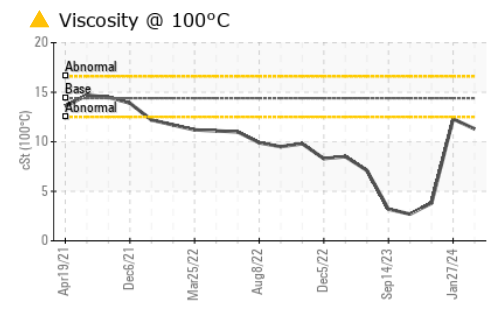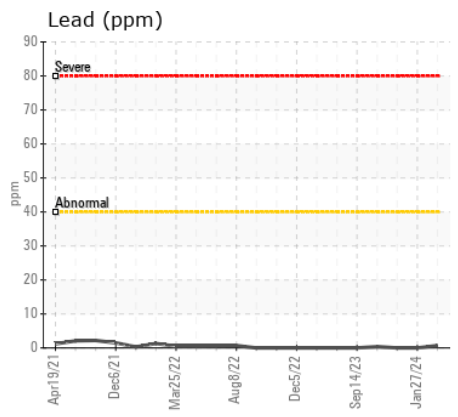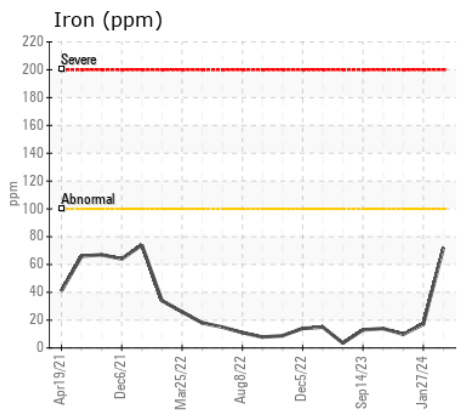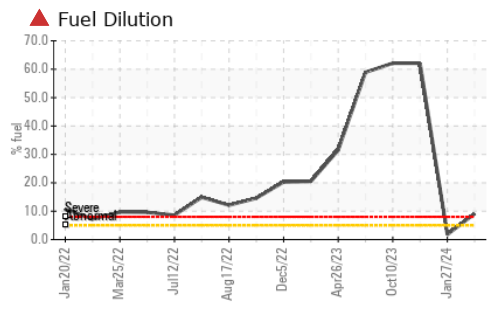

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : LW0008999 **Received** : 15 Apr 2024
Lab Number : 06148431 **Tested** : 18 Apr 2024
Unique Number : 10978509 **Diagnosed** : 18 Apr 2024 - Wes Davis
Test Package : MOB 1 (Additional Tests: FuelDilution, PercentFuel, TBN)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

LRs - NILES
 33541 REUM RD
 NILES, MI
 US 49120
 Contact: JOHN HUGHES
 johnh@michianarecyclinganddisposal.com
 T: (269)684-0900 X:124
 F: