



WEAR	<b>ABNORMAL</b>
CONTAMINATION	<b>NORMAL</b>
FLUID CONDITION	<b>NORMAL</b>



Machine Id  
**JOHN DEERE 644 P 1DW644PAVNLZ13993**  
Component  
**Rear Differential**  
Fluid  
**MOBIL MOBILGARD 424 (--- GAL)**

### RECOMMENDATION

No corrective action is recommended at this time. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		<b>JR0149331</b>	---	---
Sample Date		Client Info		<b>08 Apr 2024</b>	---	---
Machine Age	hrs	Client Info		<b>2798</b>	---	---
Oil Age	hrs	Client Info		<b>500</b>	---	---
Filter Age	hrs	Client Info		<b>500</b>	---	---
Oil Changed		Client Info		<b>Not Changed</b>	---	---
Filter Changed		Client Info		<b>Not Changed</b>	---	---
Sample Status				<b>ABNORMAL</b>	---	---

### WEAR

Bearing and/or bushing wear is indicated.

PQ		ASTM D8184		<b>16</b>	---	---
Iron	ppm	ASTM D5185m	>500	<b>32</b>	---	---
Chromium	ppm	ASTM D5185m	>10	<b>&lt;1</b>	---	---
Nickel	ppm	ASTM D5185m	>10	<b>&lt;1</b>	---	---
Titanium	ppm	ASTM D5185m		<b>&lt;1</b>	---	---
Silver	ppm	ASTM D5185m		<b>0</b>	---	---
Aluminum	ppm	ASTM D5185m	>25	<b>3</b>	---	---
Lead	ppm	ASTM D5185m	>25	<b>▲ 31</b>	---	---
Copper	ppm	ASTM D5185m	>100	<b>▲ 161</b>	---	---
Tin	ppm	ASTM D5185m	>10	<b>▲ 11</b>	---	---
Vanadium	ppm	ASTM D5185m		<b>&lt;1</b>	---	---
White Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---

### CONTAMINATION








There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>75	<b>8</b>	---	---
Potassium	ppm	ASTM D5185m	>20	<b>2</b>	---	---
Water		WC Method	>.2	<b>NEG</b>	---	---
Silt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Debris	scalar	*Visual	NONE	<b>NONE</b>	---	---
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Appearance	scalar	*Visual	NORML	<b>NORML</b>	---	---
Odor	scalar	*Visual	NORML	<b>NORML</b>	---	---
Emulsified Water	scalar	*Visual	>.2	<b>NEG</b>	---	---

### FLUID CONDITION

The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185m		<b>2</b>	---	---
Boron	ppm	ASTM D5185m		<b>91</b>	---	---
Barium	ppm	ASTM D5185m		<b>2</b>	---	---
Molybdenum	ppm	ASTM D5185m		<b>4</b>	---	---
Manganese	ppm	ASTM D5185m		<b>1</b>	---	---
Magnesium	ppm	ASTM D5185m		<b>65</b>	---	---
Calcium	ppm	ASTM D5185m		<b>3473</b>	---	---
Phosphorus	ppm	ASTM D5185m		<b>1171</b>	---	---
Zinc	ppm	ASTM D5185m		<b>1406</b>	---	---
Sulfur	ppm	ASTM D5185m		<b>7230</b>	---	---
Visc @ 40°C	cSt	ASTM D445	158	<b>54.8</b>	---	---

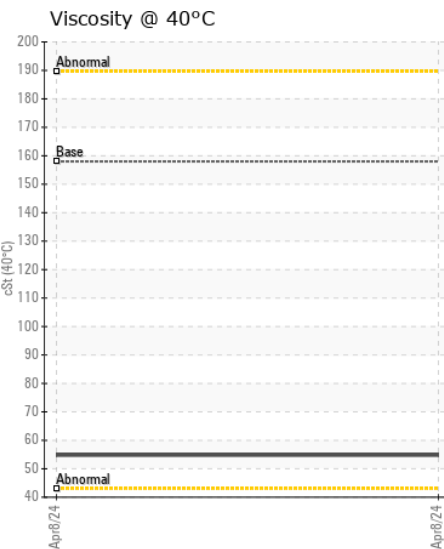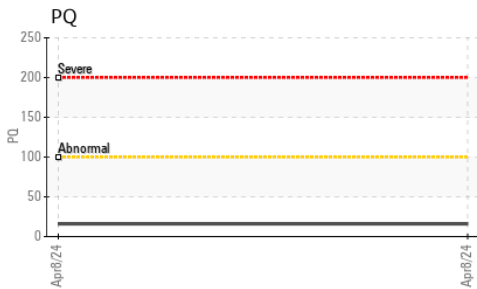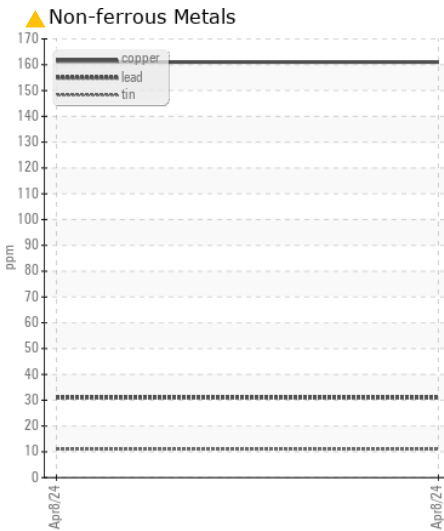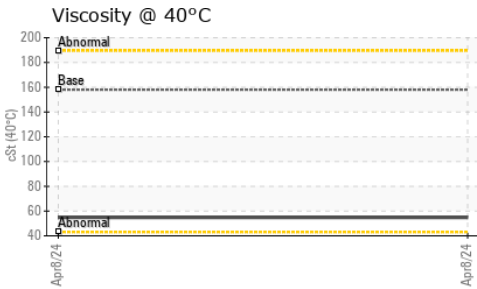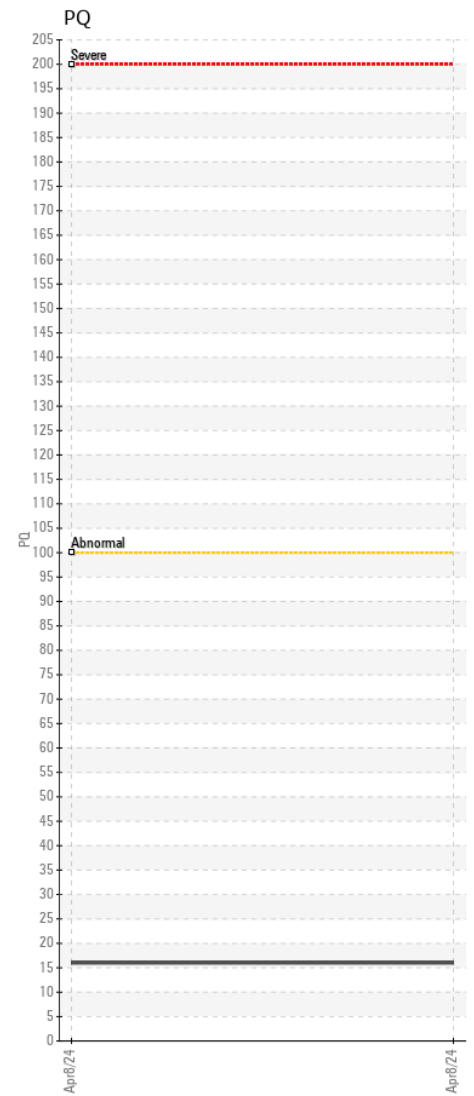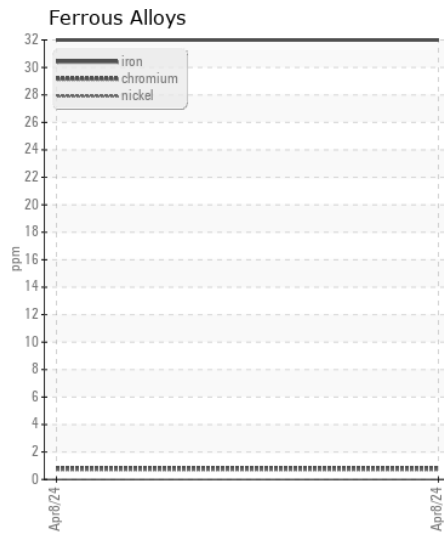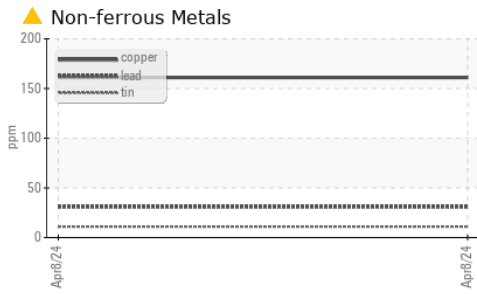

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : JR0149331 **Received** : 15 Apr 2024  
**Lab Number** : 06148969 **Tested** : 16 Apr 2024  
**Unique Number** : 10979047 **Diagnosed** : 17 Apr 2024 - Sean Felton  
**Test Package** : CONST ( Additional Tests: PQ )

**SCOTTS EARTH GROW**  
 7601 GENERAL MAHONE HWY  
 WAVERLY, VA  
 US 23890  
 Contact: JW  
 jerald.tappiii@scotts.com  
 T: (804)834-3986  
 F: (804)834-3989

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)