



Machine Id
4622M
Component
Diesel Engine
Fluid
PETRO CANADA DURON SHP 15W40 (--- GAL)

RECOMMENDATION

We advise that you check for the source of the coolant leak. The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		GFL0104456	GFL0104492	GFL0109999
Sample Date		Client Info		11 Apr 2024	02 Apr 2024	11 Jan 2024
Machine Age	hrs	Client Info		22603	25345	21052
Oil Age	hrs	Client Info		300	300	600
Filter Age	hrs	Client Info		300	300	600
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				SEVERE	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>80	13	23	27
Chromium	ppm	ASTM D5185m	>5	<1	2	2
Nickel	ppm	ASTM D5185m	>2	0	<1	0
Titanium	ppm	ASTM D5185m		0	<1	<1
Silver	ppm	ASTM D5185m	>3	0	<1	0
Aluminum	ppm	ASTM D5185m	>30	2	3	6
Lead	ppm	ASTM D5185m	>30	0	<1	<1
Copper	ppm	ASTM D5185m	>150	3	2	1
Tin	ppm	ASTM D5185m	>5	0	<1	0
Vanadium	ppm	ASTM D5185m		0	<1	<1
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION









Test for glycol is positive. There is a high concentration of glycol present in the oil.

Silicon	ppm	ASTM D5185m	>20	13	6	16
Potassium	ppm	ASTM D5185m	>20	4	2	2
Fuel		WC Method	>5	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol	%	*ASTM D2982		▲ 0.10	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.2	0.4	0.6
Nitration	Abs/cm	*ASTM D7624	>20	8.2	10.6	18.2
Sulfation	Abs/.1mm	*ASTM D7415	>30	19.0	21.7	29.5
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The oil is no longer serviceable due to the presence of contaminants.

Sodium	ppm	ASTM D5185m		● 592	7	7
Boron	ppm	ASTM D5185m	0	23	1	<1
Barium	ppm	ASTM D5185m	0	0	0	<1
Molybdenum	ppm	ASTM D5185m	60	82	64	51
Manganese	ppm	ASTM D5185m	0	<1	<1	<1
Magnesium	ppm	ASTM D5185m	1010	999	991	836
Calcium	ppm	ASTM D5185m	1070	1087	1102	916
Phosphorus	ppm	ASTM D5185m	1150	1140	1020	923
Zinc	ppm	ASTM D5185m	1270	1309	1292	1133
Sulfur	ppm	ASTM D5185m	2060	3729	2956	2472
Oxidation	Abs/.1mm	*ASTM D7414	>25	14.9	20.2	39.8
Base Number (BN)	mg KOH/g	ASTM D2896	9.8	10.3	6.3	4.0
Visc @ 100°C	cSt	ASTM D445	15.4	14.1	14.0	15.4

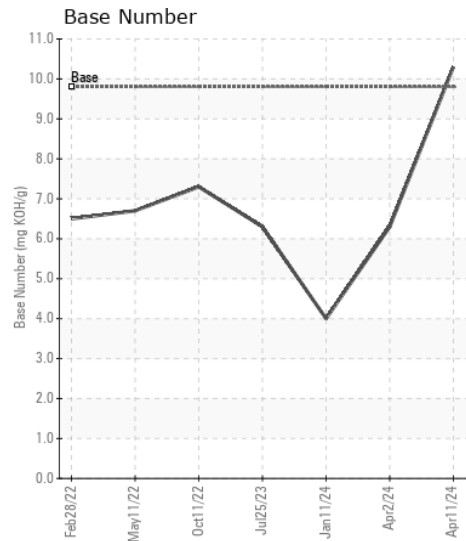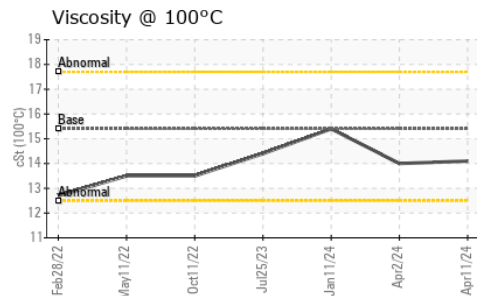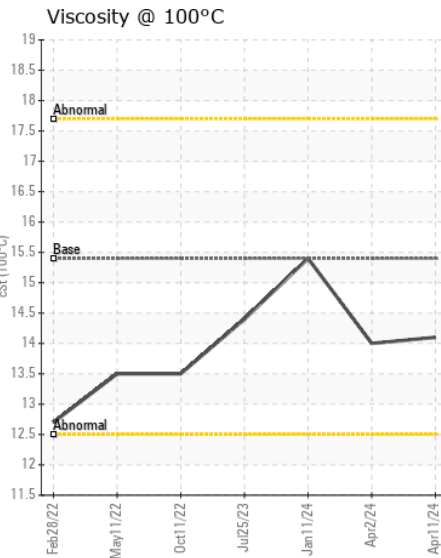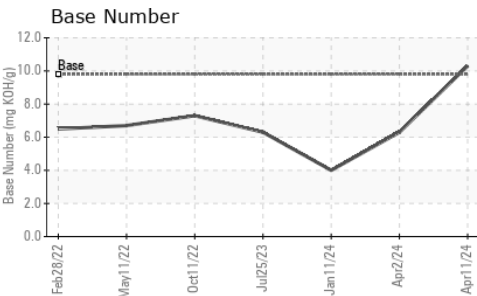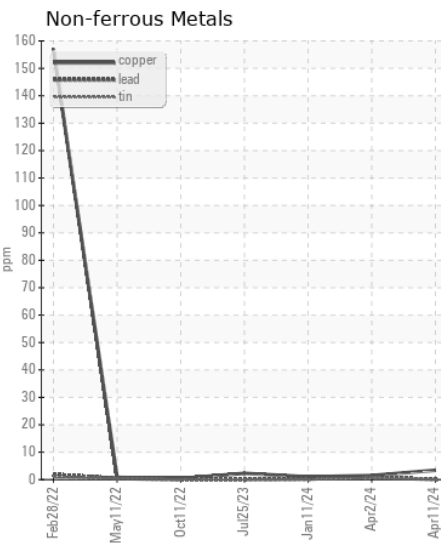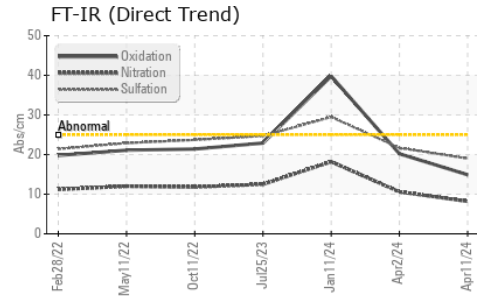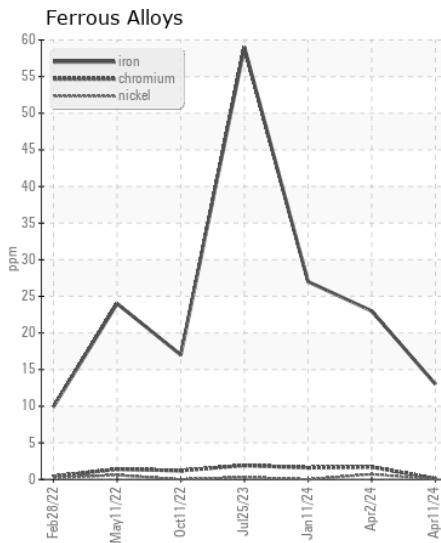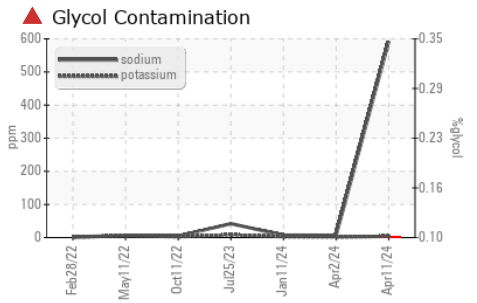

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0104456 **Received** : 16 Apr 2024
Lab Number : 06150087 **Tested** : 17 Apr 2024
Unique Number : 10980165 **Diagnosed** : 17 Apr 2024 - Wes Davis
Test Package : FLEET (Additional Tests: Glycol)

GFL Environmental - 410 - Michigan West
 39000 Van Born Rd
 Wayne, MI
 US 48184
 Contact: Belal Dgheish
 bdgheish@gflenv.com
 T: (734)714-2340
 F:

Certificate L2367
 To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)