

Machine Id VOLVO L30G 3224073

Rear Axle

{not provided} (--- GAL)

RE	\sim	N/ N	$A = \mathbb{N}$	עמוו	 \boldsymbol{ONL}

We advise that you check for the source of water entry. We recommend that you drain the oil from the component if this has not already been done. We recommend an early resample to monitor this condition.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		ASC0004544		
Sample Date		Client Info		25 Mar 2024		
Machine Age	hrs	Client Info		3618		
Oil Age	hrs	Client Info		1000		
Filter Age	hrs	Client Info		0		
Oil Changed		Client Info		Not Changd		
Filter Changed		Client Info		N/A		
Sample Status				SEVERE		
Iron	ppm	ASTM D5185m	>500	<u></u> 555		
Chromium	ppm	ASTM D5185m	>20	5		
Nickel	ppm	ASTM D5185m	>10	2		
Titanium	ppm	ASTM D5185m		<1		

0

2

0

2

1

ASTM D5185m

ASTM D5185m >30

ASTM D5185m >50

ASTM D5185m >120

ASTM D5185m >20

ASTM D5185m

ppm

ppm

ppm

ppm

ppm

Silver

Lead

Tin

Copper

Vanadium

Aluminum

WEAR

Gear wear is indicated.

റവ	NTAI	MINI	Λ TIC	ואו
\mathbf{C}	A I AI		7110	

Appearance is hazy. There is a high concentration of water present in the oil.


White Metal	scalar	*Visual	NONE	NONE	
Yellow Metal	scalar	*Visual	NONE	NONE	
Silicon	ppm	ASTM D5185m	>50	34	
Potassium	ppm	ASTM D5185m	>20	0	
Water	%	ASTM D6304	>0.2	1.73	
ppm Water	ppm	ASTM D6304	>2000	17300	
Silt	scalar	*Visual	NONE	NONE	
Debris	scalar	*Visual	NONE	NONE	
Sand/Dirt	scalar	*Visual	NONE	NONE	
Appearance	scalar	*Visual	NORML	HAZY	
Odor	scalar	*Visual	NORML	NORML	
Emulsified Water	scalar	*Visual	>0.2	0.2%	

FLUID CONDITION

The oil is no longer serviceable due to the presence of contaminants.

1-1						
Odor	scalar	*Visual	NORML	NORML		
Emulsified Water	scalar	*Visual	>0.2	4 0.2%		
Sodium	ppm	ASTM D5185m		0		
Boron	ppm	ASTM D5185m		9		
Barium	ppm	ASTM D5185m		28		
Molybdenum	ppm	ASTM D5185m		<1		
Manganese	ppm	ASTM D5185m		6		
Magnesium	ppm	ASTM D5185m		18		
Calcium	ppm	ASTM D5185m		2887		
Phosphorus	ppm	ASTM D5185m		1171		
Zinc	ppm	ASTM D5185m		1013		
Sulfur	ppm	ASTM D5185m		14402		
Visc @ 40°C	cSt	ASTM D445		187)	
				Subm	itted Bv: AMA	NDA KARI

Report Id: VOLVO8531 [WUSCAR] 06150698 (Generated: 04/18/2024 14:48:40) Rev: 1

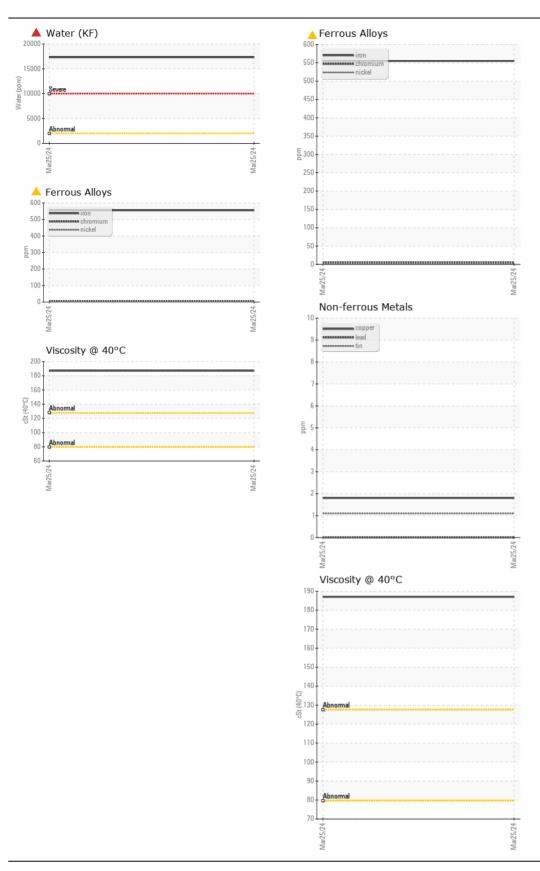



Certificate L2367

Laboratory Sample No.

: ASC0004544 Lab Number : 06150698 Unique Number : 10980776

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 Received **Tested**

: 16 Apr 2024 : 18 Apr 2024 Diagnosed : 18 Apr 2024 - Sean Felton

365 - ASCENDUM MACHINERY INC - SAVANNAH 54 MEDLINE DR RICHMOND HILL, GA US 31324

Contact: AMANDA KARI amanda.kari@ascendummachinery.com

To discuss this sample report, contact Customer Service at 1-800-237-1369. * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Test Package : CONST (Additional Tests: KF)

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012) F: (912)964-9515

T: