



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Area
Store 5 - Cross Lanes [149833]
 Machine Id
HAMM HC120I WGH0H252PHAA00208
 Component
Hydraulic System
 Fluid
WIRTGEN GROUP HYDRAULIC OIL HVLP 46 (28 GAL)

RECOMMENDATION

The filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LEC0031414	---	---
Sample Date		Client Info		11 Apr 2024	---	---
Machine Age	hrs	Client Info		53	---	---
Oil Age	hrs	Client Info		53	---	---
Filter Age	hrs	Client Info		53	---	---
Oil Changed		Client Info		Not Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				ABNORMAL	---	---

WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	<1	---	---
Chromium	ppm	ASTM D5185m	>10	0	---	---
Nickel	ppm	ASTM D5185m	>10	<1	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	<1	---	---
Lead	ppm	ASTM D5185m	>10	0	---	---
Copper	ppm	ASTM D5185m	>75	2	---	---
Tin	ppm	ASTM D5185m	>10	<1	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION











There is a moderate amount of silt (particulates < 14 microns in size) present in the oil.

Silicon	ppm	ASTM D5185m	>20	4	---	---
Potassium	ppm	ASTM D5185m	>20	1	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	▲ 11800	---	---
Particles >6µm		ASTM D7647	>1300	▲ 3449	---	---
Particles >14µm		ASTM D7647	>160	● 228	---	---
Particles >21µm		ASTM D7647	>40	54	---	---
Particles >38µm		ASTM D7647	>10	2	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ 21/19/15	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	LIGHT	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

Sodium	ppm	ASTM D5185m		2	---	---
Boron	ppm	ASTM D5185m		0	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		0	---	---
Manganese	ppm	ASTM D5185m		1	---	---
Magnesium	ppm	ASTM D5185m		67	---	---
Calcium	ppm	ASTM D5185m		21	---	---
Phosphorus	ppm	ASTM D5185m		295	---	---
Zinc	ppm	ASTM D5185m		358	---	---
Sulfur	ppm	ASTM D5185m		1062	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045		0.42	---	---
Visc @ 40°C	cSt	ASTM D445		45.7	---	---

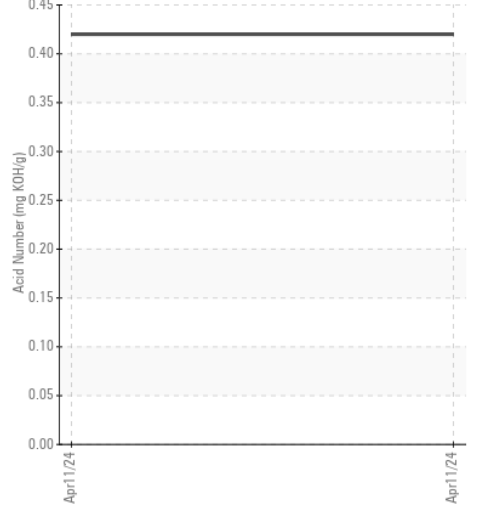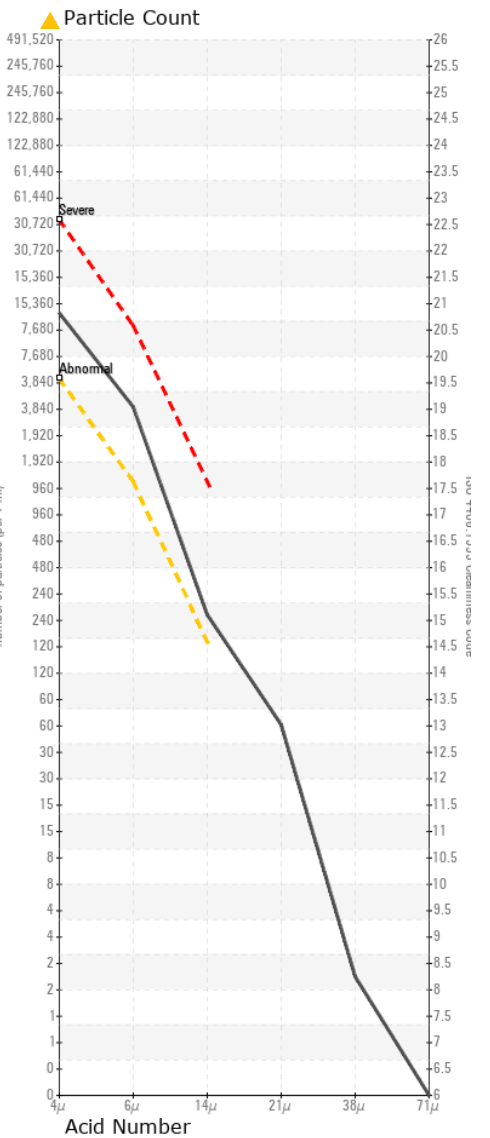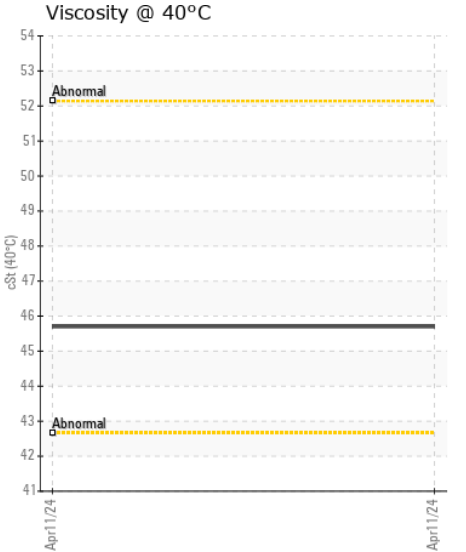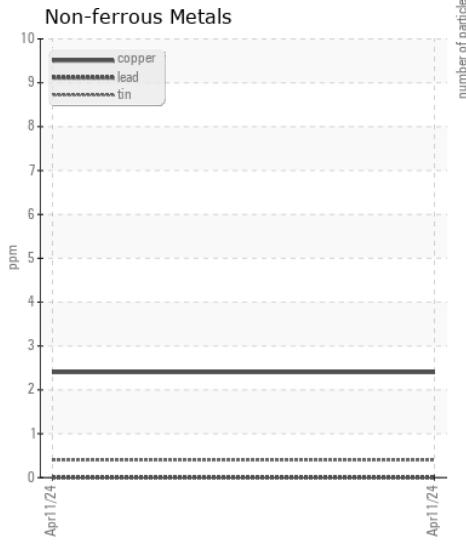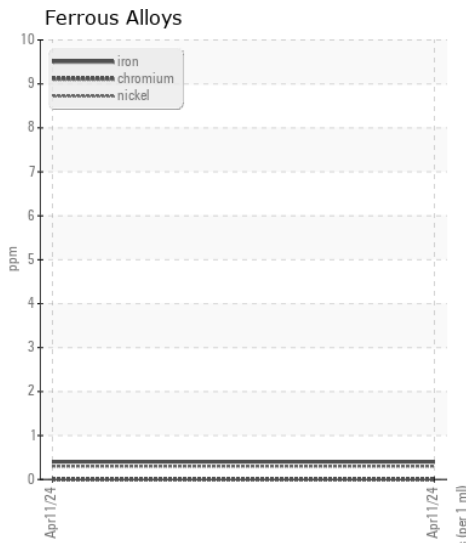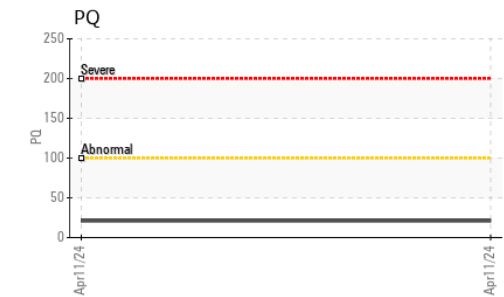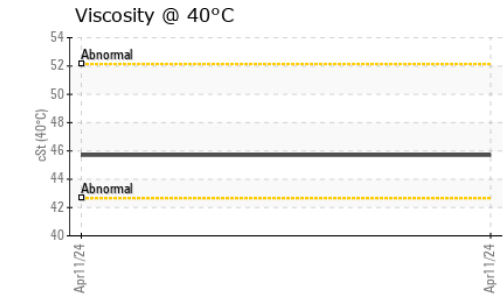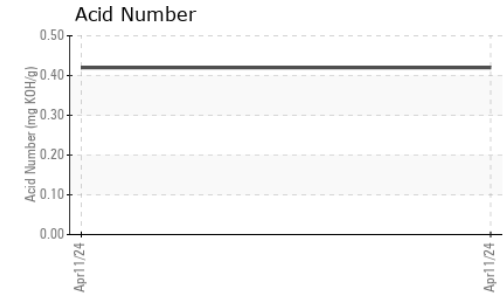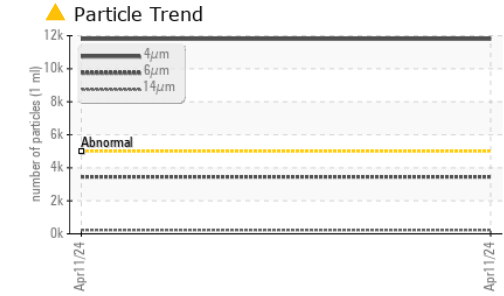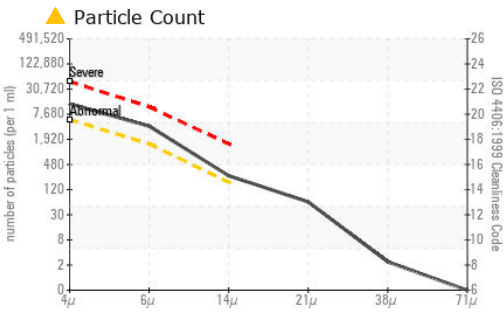

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : LEC0031414 **Received** : 16 Apr 2024
Lab Number : 06151041 **Tested** : 17 Apr 2024
Unique Number : 10981119 **Diagnosed** : 17 Apr 2024 - Wes Davis
Test Package : CONST (Additional Tests: PQ)

LESLIE EQUIPMENT COMPANY
 105 TENNIS CENTER DR.
 MARIETTA, OH
 US 45750-9765
 Contact: LEANNE KENDALL
 KendalLeanne@lec1.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (740)373-5570