



WEAR	ABNORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 135G 1FF135GXPMF503176
 Component
Diesel Engine
 Fluid
JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (--- GAL)

RECOMMENDATION

Oil and filter change at the time of sampling has been noted. No corrective action is recommended at this time. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0209120	JR0183334	---
Sample Date		Client Info		14 Apr 2024	06 Oct 2023	---
Machine Age	hrs	Client Info		1550	1032	---
Oil Age	hrs	Client Info		518	1032	---
Filter Age	hrs	Client Info		0	0	---
Oil Changed		Client Info		Changed	Changed	---
Filter Changed		Client Info		Changed	Changed	---
Sample Status				ABNORMAL	NORMAL	---

WEAR

The copper level is abnormal. In the absence of other significant wear metals, suspect copper due to sources other than wear (i.e. cooling core). All other component wear rates are normal.

Iron	ppm	ASTM D5185m	>51	5	0	---
Chromium	ppm	ASTM D5185m	>11	<1	<1	---
Nickel	ppm	ASTM D5185m	>5	0	<1	---
Titanium	ppm	ASTM D5185m		0	0	---
Silver	ppm	ASTM D5185m	>3	0	0	---
Aluminum	ppm	ASTM D5185m	>31	6	8	---
Lead	ppm	ASTM D5185m	>26	0	1	---
Copper	ppm	ASTM D5185m	>26	▲ 58	13	---
Tin	ppm	ASTM D5185m	>4	0	0	---
Vanadium	ppm	ASTM D5185m		0	<1	---
White Metal	scalar	*Visual	NONE	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	---

CONTAMINATION

There is no indication of any contamination in the oil.


Silicon	ppm	ASTM D5185m	>22	7	11	---
Potassium	ppm	ASTM D5185m	>20	3	2	---
Fuel		WC Method	>2.1	<1.0	<1.0	---
Water		WC Method	>0.21	NEG	NEG	---
Glycol		WC Method		NEG	NEG	---
Soot %	%	*ASTM D7844	>3	0.1	0.1	---
Nitration	Abs/cm	*ASTM D7624	>20	7.9	7.4	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	20.7	19.5	---
Silt	scalar	*Visual	NONE	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.21	NEG	NEG	---

FLUID CONDITION


The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>31	<1	<1	---
Boron	ppm	ASTM D5185m		243	255	---
Barium	ppm	ASTM D5185m		0	3	---
Molybdenum	ppm	ASTM D5185m		256	230	---
Manganese	ppm	ASTM D5185m		0	<1	---
Magnesium	ppm	ASTM D5185m		755	711	---
Calcium	ppm	ASTM D5185m		1547	1483	---
Phosphorus	ppm	ASTM D5185m		986	932	---
Zinc	ppm	ASTM D5185m		1126	1132	---
Sulfur	ppm	ASTM D5185m		3040	3387	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	15.0	13.9	---
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	8.8	8.3	---
Visc @ 100°C	cSt	ASTM D445	15.4	13.0	12.9	---


▲ Non-ferrous Metals

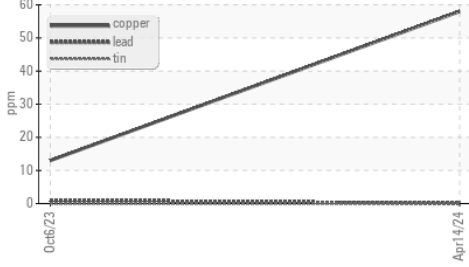


Ferrous Alloys

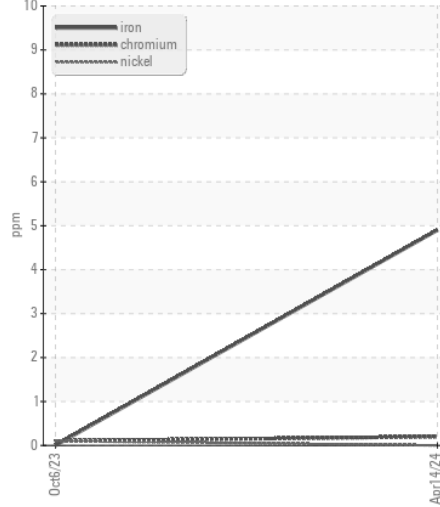


FT-IR (Direct Trend)

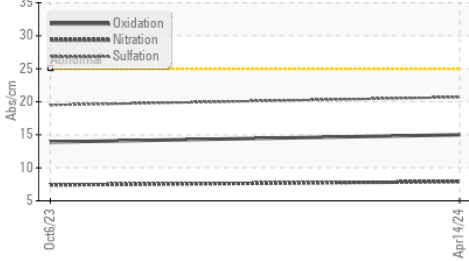


Base Number

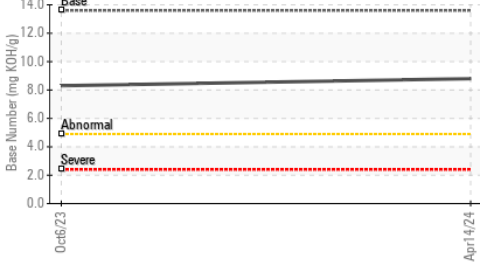


▲ Non-ferrous Metals

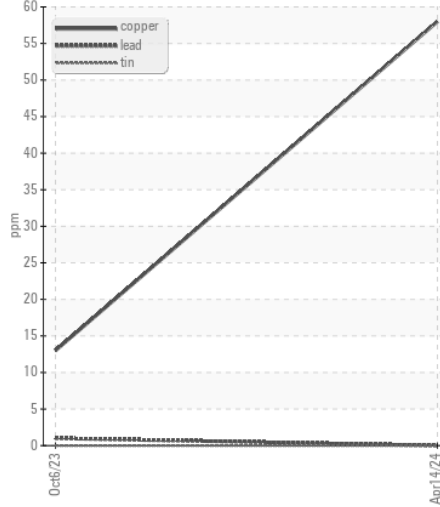


Viscosity @ 100°C

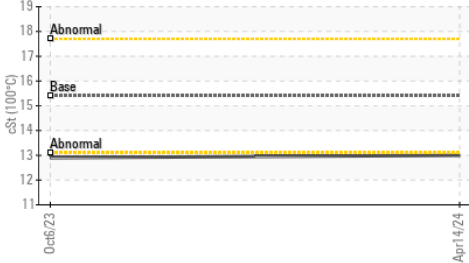

Viscosity @ 100°C

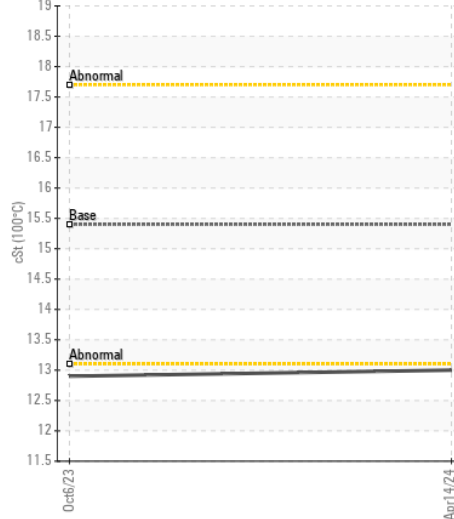

Base Number

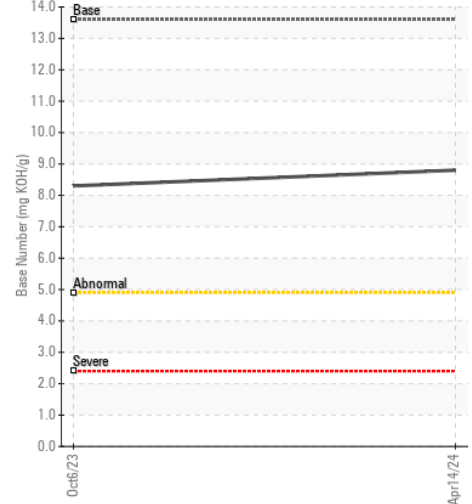

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0209120 **Received** : 17 Apr 2024
Lab Number : 06151745 **Tested** : 18 Apr 2024
Unique Number : 10981823 **Diagnosed** : 19 Apr 2024 - Sean Felton
Test Package : CONST (Additional Tests: TBN)

JRE - GARNER
 4161 AUBURN CHURCH RD
 GARNER, NC
 US 27529

Contact: RALEIGH SHOP
 sean.betts@jamesriverequipment.com; catherine.anastasio@wearcheck.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (919)614-2260
 F: (919)779-5432