



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area
[W66408-4]
 Machine Id
JOHN DEERE 325G 1T0325GKCPJ445713
 Component
Hydraulic System
 Fluid
JOHN DEERE HYDRAU (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0205851	---	---
Sample Date		Client Info		19 Apr 2024	---	---
Machine Age	hrs	Client Info		495	---	---
Oil Age	hrs	Client Info		495	---	---
Filter Age	hrs	Client Info		495	---	---
Oil Changed		Client Info		Not Chngd	---	---
Filter Changed		Client Info		Not Chngd	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

PQ		ASTM D8184	>50	15	---	---
Iron	ppm	ASTM D5185m	>32	10	---	---
Chromium	ppm	ASTM D5185m	>9	0	---	---
Nickel	ppm	ASTM D5185m	>5	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>9	<1	---	---
Lead	ppm	ASTM D5185m	>28	0	---	---
Copper	ppm	ASTM D5185m	>50	5	---	---
Tin	ppm	ASTM D5185m	>5	0	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION










The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>11	3	---	---
Potassium	ppm	ASTM D5185m	>20	<1	---	---
Water		WC Method	>0.075	NEG	---	---
Particles >4µm		ASTM D7647	>80000	57329	---	---
Particles >6µm		ASTM D7647	>20000	5388	---	---
Particles >14µm		ASTM D7647	>640	41	---	---
Particles >21µm		ASTM D7647	>160	8	---	---
Particles >38µm		ASTM D7647	>40	0	---	---
Particles >71µm		ASTM D7647	>10	0	---	---
Oil Cleanliness		ISO 4406 (c)	>23/21/16	23/20/13	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.075	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>21	1	---	---
Boron	ppm	ASTM D5185m		0	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		0	---	---
Manganese	ppm	ASTM D5185m		<1	---	---
Magnesium	ppm	ASTM D5185m		<1	---	---
Calcium	ppm	ASTM D5185m	87	121	---	---
Phosphorus	ppm	ASTM D5185m	727	397	---	---
Zinc	ppm	ASTM D5185m	900	465	---	---
Sulfur	ppm	ASTM D5185m	1500	1536	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.53	---	---
Visc @ 40°C	cSt	ASTM D445	65	51.1	---	---

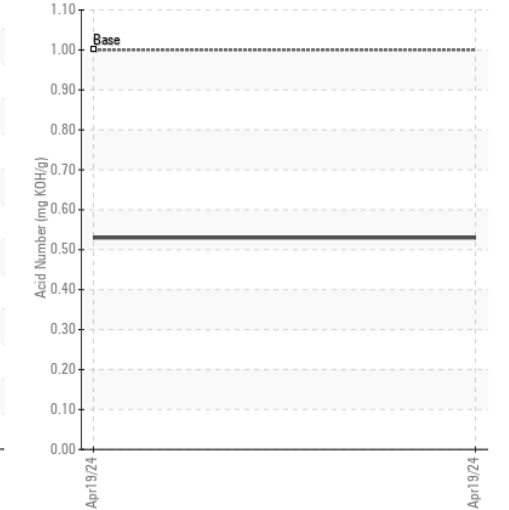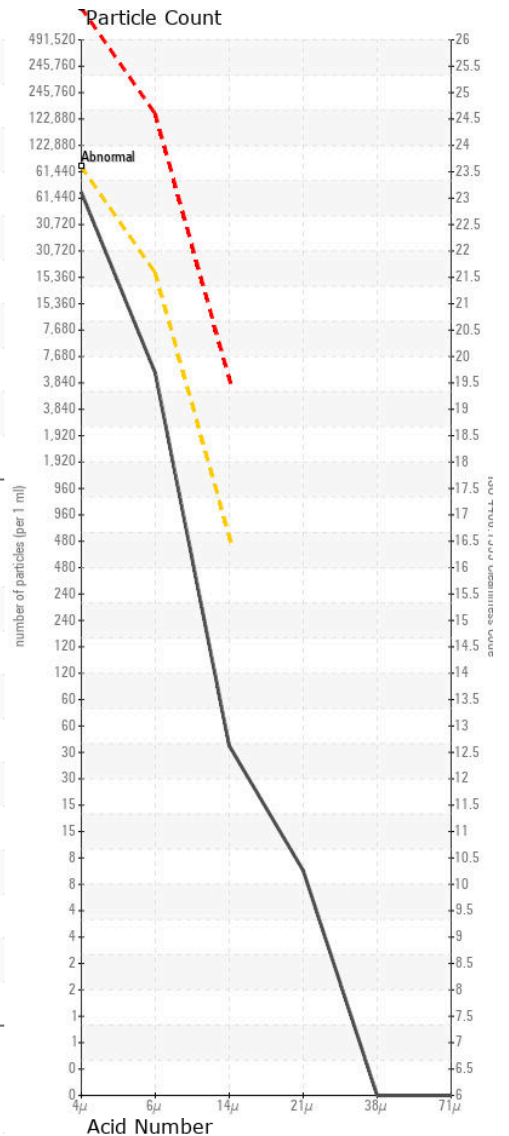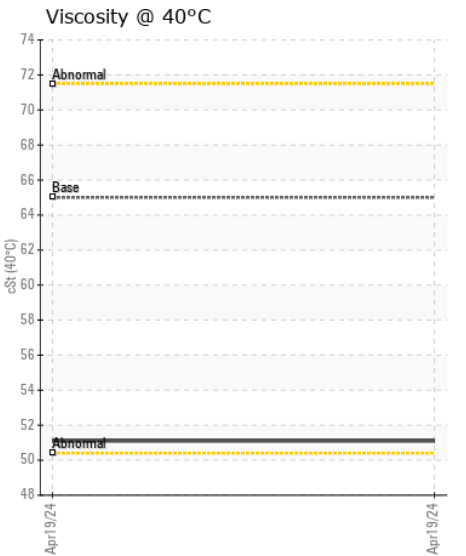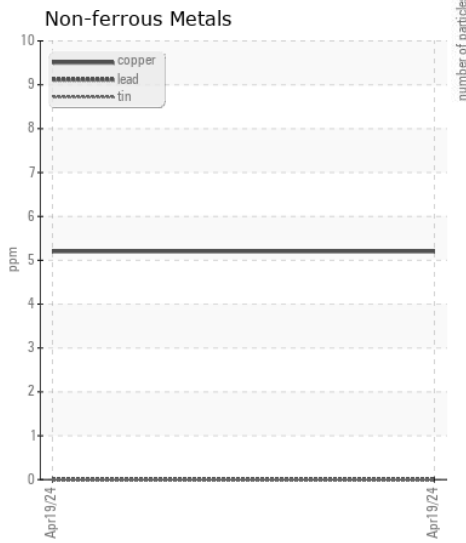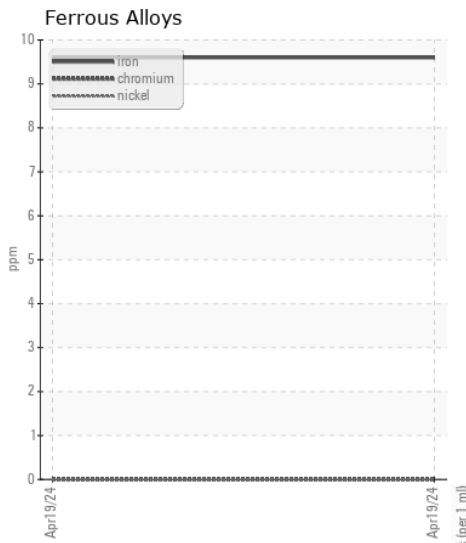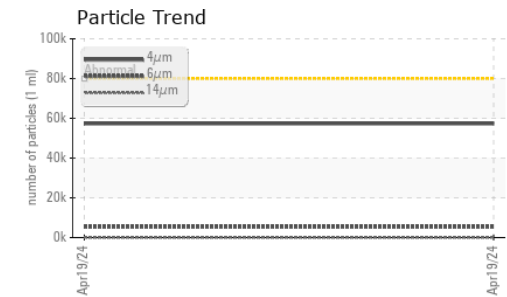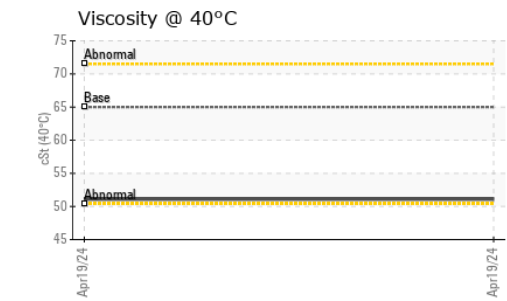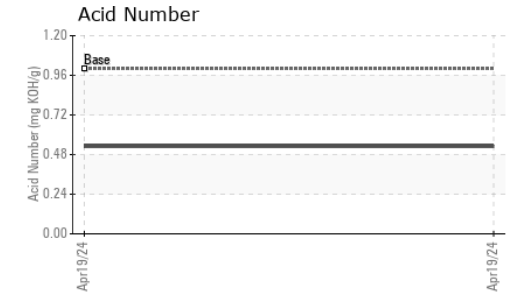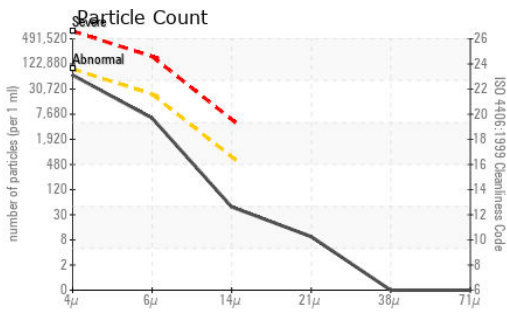

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : JR0205851

Lab Number : 06160269

Unique Number : 10995692

Test Package : CONST (Additional Tests: PQ)

Received : 25 Apr 2024

Tested : 26 Apr 2024

Diagnosed : 26 Apr 2024 - Wes Davis

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - CHARLOTTE

9550 STATESVILLE ROAD

CHARLOTTE, NC

US 28269

Contact: CHARLOTTE SHOP

myoung@jamesriverequipment.com

T: (704)597-0211

F: (704)596-6198