



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Area  
**Store 5 - Cross Lanes [150047]**  
 Machine Id  
**John Deere 323E 1T0323EBVEJ263385**  
 Component  
**Diesel Engine**  
 Fluid  
**JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (3 GAL)**

**RECOMMENDATION**

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LEC0047565	---	---
Sample Date		Client Info		23 Apr 2024	---	---
Machine Age	hrs	Client Info		1749	---	---
Oil Age	hrs	Client Info		1749	---	---
Filter Age	hrs	Client Info		1749	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				NORMAL	---	---

**WEAR**

Metal levels are typical for a components first oil change.

Iron	ppm	ASTM D5185m	>51	36	---	---
Chromium	ppm	ASTM D5185m	>11	1	---	---
Nickel	ppm	ASTM D5185m	>5	<1	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m	>3	0	---	---
Aluminum	ppm	ASTM D5185m	>31	11	---	---
Lead	ppm	ASTM D5185m	>26	<1	---	---
Copper	ppm	ASTM D5185m	>26	8	---	---
Tin	ppm	ASTM D5185m	>4	<1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

**CONTAMINATION**








There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>120	16	---	---
Potassium	ppm	ASTM D5185m	>20	4	---	---
Fuel		WC Method	>2.1	<1.0	---	---
Water		WC Method	>0.21	NEG	---	---
Glycol		WC Method		NEG	---	---
Soot %	%	*ASTM D7844	>3	0.5	---	---
Nitration	Abs/cm	*ASTM D7624	>20	10.6	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	22.8	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.21	NEG	---	---

**FLUID CONDITION**

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>31	2	---	---
Boron	ppm	ASTM D5185m		220	---	---
Barium	ppm	ASTM D5185m		2	---	---
Molybdenum	ppm	ASTM D5185m		199	---	---
Manganese	ppm	ASTM D5185m		1	---	---
Magnesium	ppm	ASTM D5185m		679	---	---
Calcium	ppm	ASTM D5185m		1550	---	---
Phosphorus	ppm	ASTM D5185m		930	---	---
Zinc	ppm	ASTM D5185m		1093	---	---
Sulfur	ppm	ASTM D5185m		3302	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	18.1	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	8.7	---	---
Visc @ 100°C	cSt	ASTM D445	15.4	13.7	---	---

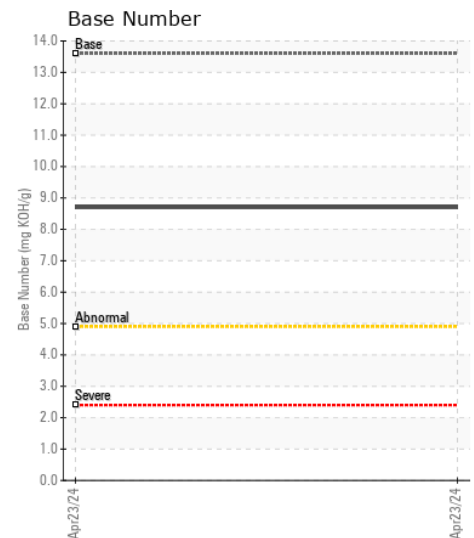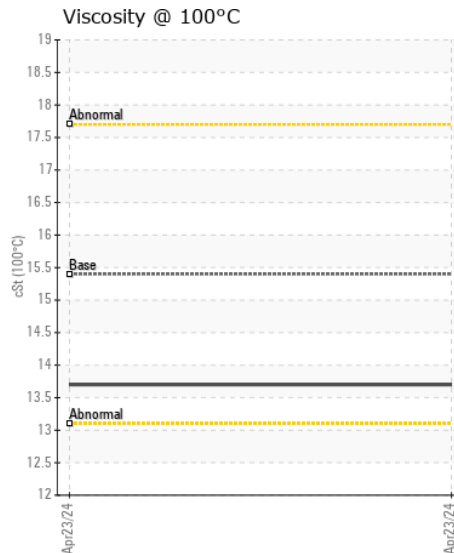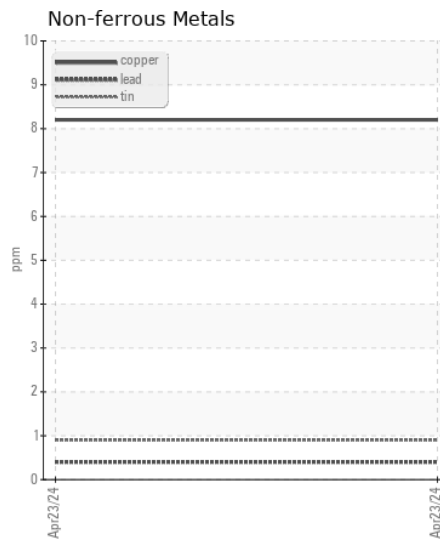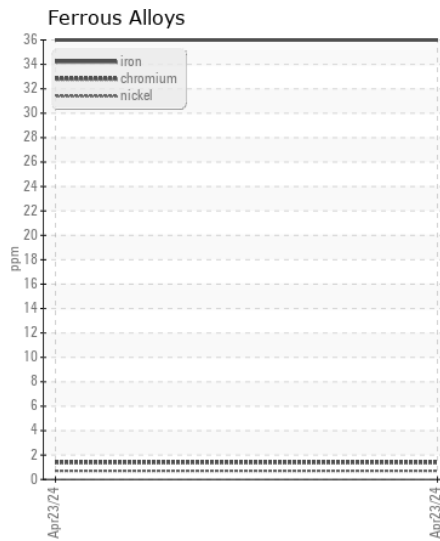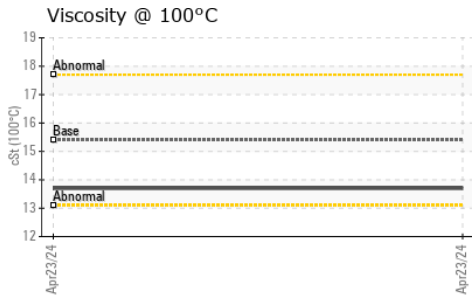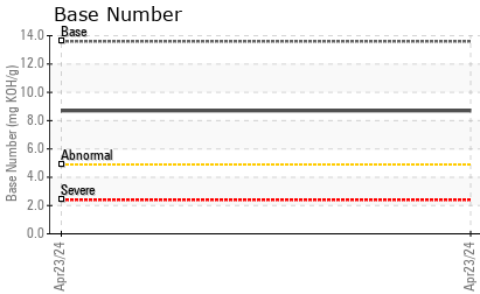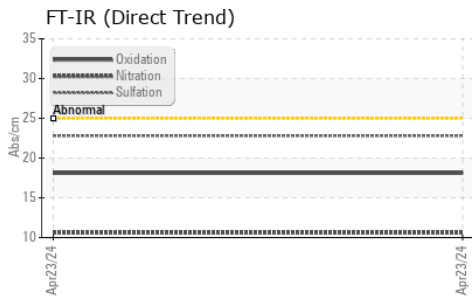

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : LEC0047565 **Received** : 26 Apr 2024  
**Lab Number** : **06161302** **Tested** : 28 Apr 2024  
**Unique Number** : 10996725 **Diagnosed** : 28 Apr 2024 - Wes Davis  
**Test Package** : CONST ( Additional Tests: TBN )

**LESLIE EQUIPMENT COMPANY**  
 105 TENNIS CENTER DR.  
 MARIETTA, OH  
 US 45750-9765  
 Contact: LEANNE KENDALL  
 KendalLeanne@lec1.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:  
 F: (740)373-5570