



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area

[W02008179]

Machine Id

VOLVO A25G 752867

Component

Front Differential

Fluid

VOLVO SUPER GEAR OIL 75W-80-GO102 (10 GAL)

RECOMMENDATION

The oil change at the time of sampling has been noted. Resample at the next service interval to monitor. (Customer Sample Comment: W02008179)

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		ML0001004	---	---
Sample Date		Client Info		22 Apr 2024	---	---
Machine Age	hrs	Client Info		1084	---	---
Oil Age	hrs	Client Info		1084	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		N/A	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>900	262	---	---
Chromium	ppm	ASTM D5185m	>20	6	---	---
Nickel	ppm	ASTM D5185m	>10	4	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>30	2	---	---
Lead	ppm	ASTM D5185m	>50	0	---	---
Copper	ppm	ASTM D5185m	>150	25	---	---
Tin	ppm	ASTM D5185m	>20	1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION





There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>50	7	---	---
Potassium	ppm	ASTM D5185m	>20	6	---	---
Water		WC Method	>0.2	NEG	---	---
Silt	scalar	*Visual	NONE	MODER	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---	---

FLUID CONDITION

The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185m		<1	---	---
Boron	ppm	ASTM D5185m		316	---	---
Barium	ppm	ASTM D5185m		7	---	---
Molybdenum	ppm	ASTM D5185m		8	---	---
Manganese	ppm	ASTM D5185m		11	---	---
Magnesium	ppm	ASTM D5185m		5	---	---
Calcium	ppm	ASTM D5185m		732	---	---
Phosphorus	ppm	ASTM D5185m		1464	---	---
Zinc	ppm	ASTM D5185m		324	---	---
Sulfur	ppm	ASTM D5185m		21730	---	---
Visc @ 40°C	cSt	ASTM D445		89.7	---	---

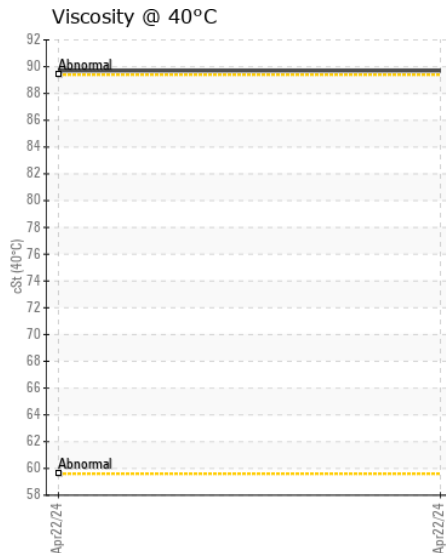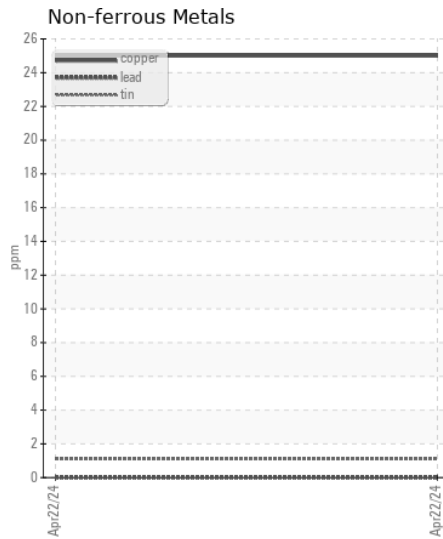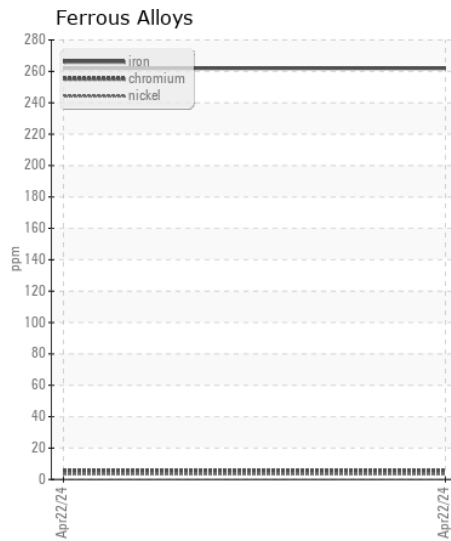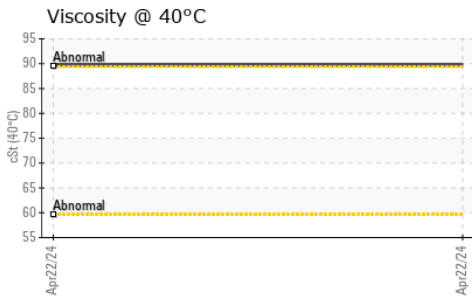

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : ML0001004
Lab Number : 06174378
Unique Number : 11020431
Test Package : CONST

Received : 09 May 2024
Tested : 10 May 2024
Diagnosed : 13 May 2024 - Don Baldrige

MCCLUNG-LOGAN EQUIPMENT CO - MANASSAS
 8450 QUARRY ROAD
 MANASSAS, VA
 US 20110

Contact: DARRELL ANDES
 dandes@mcclung-logan.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:
 F: (703)393-7844