



WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	ABNORMAL

Area

[W66860]

Machine Id

JOHN DEERE 470G 1FF470GXEJF235245

Component

Diesel Engine

Fluid

JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (11 GAL)

RECOMMENDATION

We advise that you check the fuel injection system. Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor. (Customer Sample Comment: W66860)

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0215000	JR0188048	JR0145335
Sample Date		Client Info		08 May 2024	26 Oct 2023	22 Jun 2023
Machine Age	hrs	Client Info		4605	4075	3535
Oil Age	hrs	Client Info		530	4026	500
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		Changed	Changed	Not Changd
Filter Changed		Client Info		Changed	Changed	Not Changd
Sample Status				ABNORMAL	ABNORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>51	34	48	22
Chromium	ppm	ASTM D5185m	>11	<1	<1	<1
Nickel	ppm	ASTM D5185m	>5	0	<1	<1
Titanium	ppm	ASTM D5185m		<1	0	<1
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m	>31	8	7	3
Lead	ppm	ASTM D5185m	>26	19	▲ 31	7
Copper	ppm	ASTM D5185m	>26	9	14	9
Tin	ppm	ASTM D5185m	>4	3	3	1
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION









Light fuel dilution occurring.

Silicon	ppm	ASTM D5185m	>22	14	17	13
Potassium	ppm	ASTM D5185m	>20	6	8	4
Fuel	%	ASTM D3524	>2.1	▲ 2.4	▲ 3.4	1.2
Water		WC Method	>0.21	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.6	0.7	0.2
Nitration	Abs/cm	*ASTM D7624	>20	10.4	10.9	7.6
Sulfation	Abs/.1mm	*ASTM D7415	>30	27.4	26.7	20.6
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.21	NEG	NEG	NEG

FLUID CONDITION

Fuel is present in the oil and is lowering the viscosity. The BN result indicates that there is suitable alkalinity remaining in the oil.

Sodium	ppm	ASTM D5185m	>31	9	11	0
Boron	ppm	ASTM D5185m		50	28	346
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		247	215	279
Manganese	ppm	ASTM D5185m		<1	<1	<1
Magnesium	ppm	ASTM D5185m		825	702	900
Calcium	ppm	ASTM D5185m		1424	1519	1727
Phosphorus	ppm	ASTM D5185m		935	958	1105
Zinc	ppm	ASTM D5185m		1070	1030	1266
Sulfur	ppm	ASTM D5185m		3094	2463	3609
Oxidation	Abs/.1mm	*ASTM D7414	>25	23.4	23.9	15.3
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	6.1	4.0	9.5
Visc @ 100°C	cSt	ASTM D445	15.4	▲ 12.1	▲ 12.0	13.1

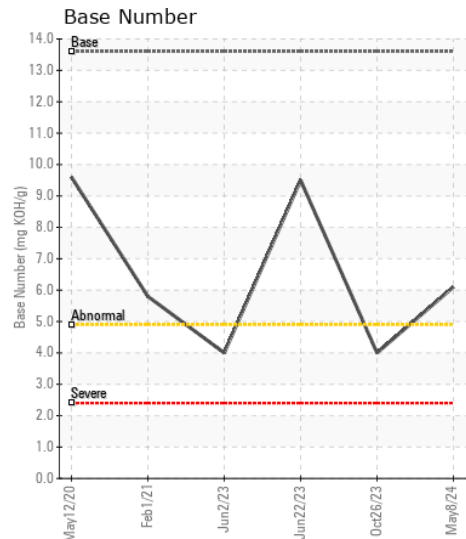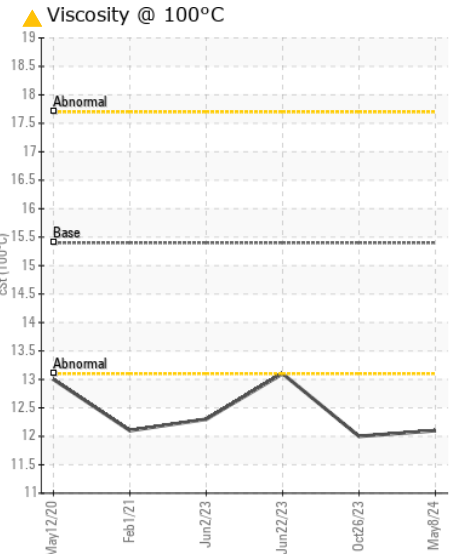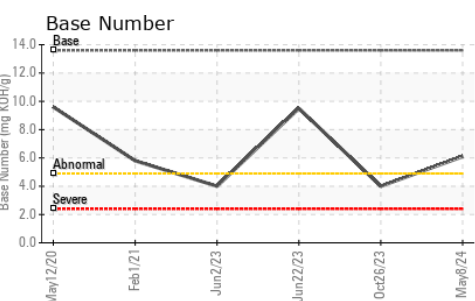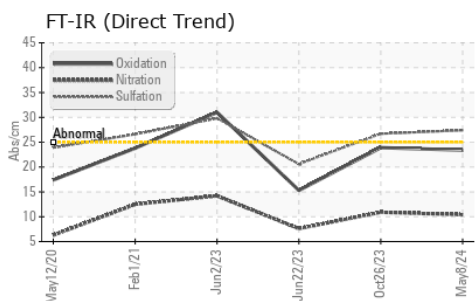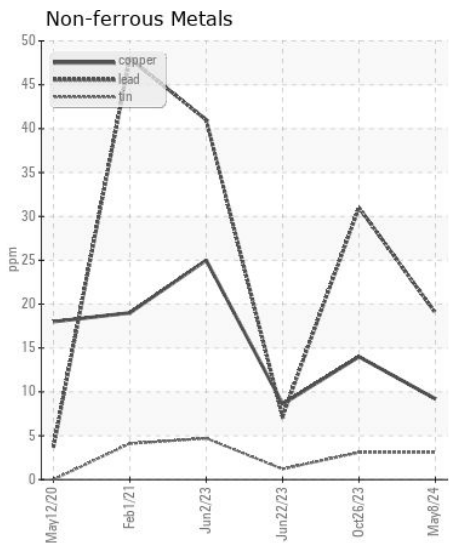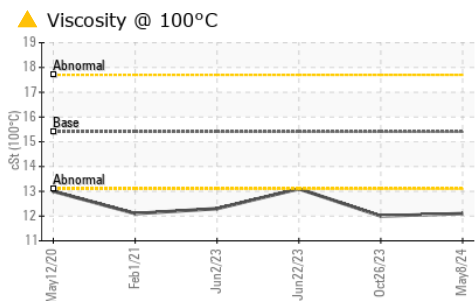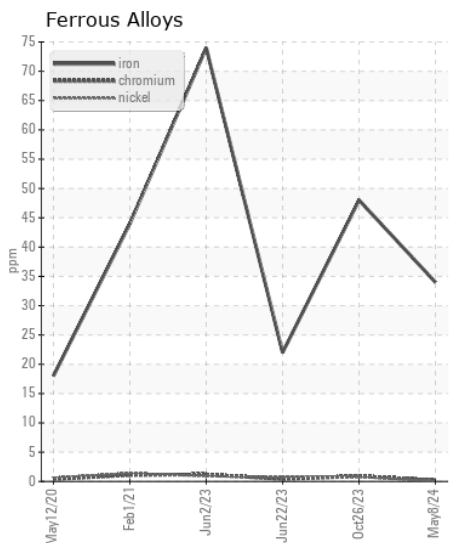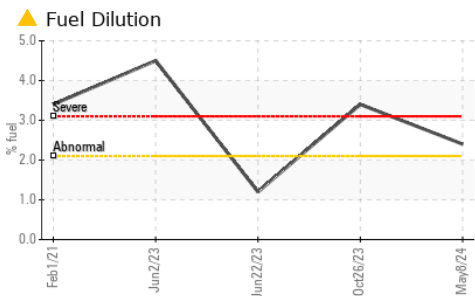

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0215000 **Received** : 10 May 2024
Lab Number : 06175235 **Tested** : 15 May 2024
Unique Number : 11021288 **Diagnosed** : 15 May 2024 - Sean Felton
Test Package : CONST (Additional Tests: PercentFuel, TBN)

JRE - CHARLOTTE
 9550 STATESVILLE ROAD
 CHARLOTTE, NC
 US 28269
 Contact: CHARLOTTE SHOP
 myoung@jamesriverequipment.com
 T: (704)597-0211
 F: (704)596-6198

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)